

**DIVERSITY IN STRUCTURE, COMPOSITION AND PROPERTIES OF  
SILK FROM AFRICAN WILD SILKMOTHS**

**BY**

**ADDIS TESHOME KEBEDE**

**(M. Sc, HARAMAYA UNIVERSITY, ETHIOPIA)**

**THESIS SUBMITTED IN FULFILMENT OF THE REQUIREMENTS FOR THE  
AWARD OF THE DEGREE OF DOCTOR OF PHILOSOPHY IN ENTOMOLOGY,  
SCHOOL OF BIOLOGICAL SCIENCES**

**UNIVERSITY OF NAIROBI**

**OCTOBER 2012**


## DECLARATION AND APPROVAL

This work is my original work and has not been presented for an award of degree in any other university.

**Name:** Addis Teshome Kebede

**Registration No.:** I80/80201/11

**Signature:** \_\_\_\_\_



**Date:** 13<sup>th</sup> October, 2012


### APPROVAL BY SUPERVISORS

This thesis has been submitted to the University of Nairobi with our approval as supervisors.

**Dr. Jacques M. Kabaru**

University of Nairobi, School of Biological Sciences,  
P. O. Box: 30197-00100, Nairobi, Kenya

**Signature** \_\_\_\_\_



**Date :** October, 15<sup>th</sup>, 2012

**Dr. John M. Onyari**

University of Nairobi, Department of Chemistry,  
P. O. Box: 30197-00100, Nairobi, Kenya

**Signature** \_\_\_\_\_




**Date:** October 15<sup>th</sup>, 2012

**Prof. Suresh K. Raina**

*icipe*- African Insect Science for Food and Health,  
Commercial Insects Programme,  
P.O. Box: 30772-00100, Nairobi, Kenya

**Signature** \_\_\_\_\_



**Date:** 15<sup>th</sup> Oct 2012

**Professor Fritz Vollrath**

University of Oxford, Department of Zoology,  
South Parks Road, Oxford OX1 3PS, UK.

**Signature** \_\_\_\_\_



**Date:** October 14<sup>th</sup>, 2012

**DEDICATOIN**

**TO**

**MY BELOVED FAMILY AND FRIENDS**

## ACKNOWLEDGENTS

I wish to acknowledge and express my gratitude to several people and institutions that assisted and encouraged me in one or another way throughout this study. I could not have completed this study without them.

My sincere appreciation goes to Drs. J. M. Kabaru and J. M. Onyari, both from University of Nairobi, for accepting to serve as my university supervisors and for their great input, critical criticism, supply of literature and numerous valuable suggestions that have shaped this thesis and the publications so far. They tirelessly and in the shortest time possible reviewed, corrected and brought in critical decisions into the drafts of this thesis.

It is my pleasure to thank Professor Suresh K. Raina, who went well beyond the call of duty as ICIPE (International Centre of Insect Physiology and Ecology) supervisor for giving me a chance at the Commercial Insects Program, for his endless optimism and being cheerful and encouraging throughout it all. His constant moral support, guidance and encouragement are highly appreciated.

Many thanks to Professor Fritz Vollrath, from University of Oxford, and the Oxford Silk Research Group members for providing me with excellent research facilities and patience in familiarizing me with laboratory equipments and analyses software. All my supervisors contributed a lot through their valuable comments and expert suggestions throughout the research work and the preparation of this thesis.

I wish to express my profound gratitude to all colleagues at the Commercial Insect Program for their support and friendship. I also would like to thank my fellow scholars and staff of ICIPE, who were always helping and encouraging me in social interactions and research undertakings. Conversations and mutual support from them not only stimulated new insights, but also provided necessary encouragement along the way. The time I spent with them will be precious and unforgettable.

Many thanks are due to German Academic Exchange Service (DAAD) for providing the scholarship and to International Fund for Agricultural Development (IFAD) for funding the research project. Thanks are also due to ICIPE and the African Regional Postgraduate

Program in Insect Science (ARPPIS) for providing logistical and research support. Many thanks are also to Capacity Building and Institutional Development (CBID) staff especially Mrs Lillian Igweta, Lisa Omondi and Margaret Ochenda for their constant support.

Finally, I want to appreciate my family and friends for their care, unfailing encouragement, and loving support with their priceless prayers, tireless assistance and encouraging words during my whole life. It is not possible to thank everybody, but I want to thank all people who contributed to this thesis through their support and invaluable friendship. Above all, this thesis will not be complete without giving thanks and adoration to the Almighty God for his divine guidance throughout my life.

## TABLE OF CONTENTS

	Pages
<b>DECLARATION AND APPROVAL</b> .....	i
<b>DEDICATOIN</b> .....	ii
<b>ACKNOWLEDGENTS</b> .....	iii
<b>TABLE OF CONTENTS</b> .....	v
<b>LIST OF FIGURES</b> .....	xi
<b>LIST OF TABLES</b> .....	xiii
<b>ABBREVIATIONS AND ACRONYMS</b> .....	xiv
<b>ABSTRACT</b> .....	xv
<b>CHAPTER ONE</b> .....	1
<b>GENERAL INTRODUCTION</b> .....	1
<b>1.1. Background information</b> .....	1
<b>1.2. Statement of the problem</b> .....	4
<b>1.3. Justification</b> .....	5
<b>1.4. Hypotheses</b> .....	6
<b>1.5. Objectives</b> .....	7
1.5.1. General objective.....	7
1.5.2. Specific objectives.....	7

<b>CHAPTER TWO .....</b>	<b>8</b>
<b>LITERATURE REVIEW.....</b>	<b>8</b>
<b>2.1. Seri-biodiversity .....</b>	<b>8</b>
2.1.1 Silkworms .....	9
2.1.2. Silk from spiders.....	10
2.1.3. Other silk producing arthropods.....	11
<b>2.2. Composition of silk.....</b>	<b>13</b>
2.2.1 Fibroin.....	14
2.2.2. Sericin .....	15
2.2.3. Other components of silk .....	16
2.2.4. Amino acid composition .....	16
<b>2.3. Properties of silk.....</b>	<b>19</b>
2.3.1. Tensile properties .....	19
2.3.2. Solubility and thermal properties .....	20
<b>2.4. Applications of silk.....</b>	<b>21</b>
2.4.1. Dietary and medicinal applications .....	21
2.4.2. Cosmetic application .....	22
2.4.3. Applications in pharmaceuticals, biomaterials and biomedical materials.....	23
2.4.3.1. Applications of fibroin .....	23
2.4.3.2. Applications of sericin .....	25

<b>CHAPTER THREE</b> .....	26
<b>GENERAL MATERIALS AND METHODS</b> .....	26
<b>3.1. Silkmths and cocoon shells</b> .....	26
<b>3.2. Cleaning of cocoon shells</b> .....	26
<b>3.3. Degumming of cocoon shells</b> .....	27
<b>3.4. Chemicals</b> .....	27
<b>3.5. Data analysis</b> .....	27
<b>CHAPTER FOUR</b> .....	30
<b>MICROSTRUCTURES OF COCOON SHELLS AND DEGUMMED FIBERS</b> .....	30
<b>4.1. INTRODUCTION</b> .....	30
<b>4.2. MATERIALS AND METHODS</b> .....	32
4.2.1. Surface and cross sectional study of cocoon shells .....	32
4.2.2. Longitudinal and cross-sectional study of degummed fibers.....	32
4.2.3. Fourier Transform Infrared Spectroscopy (FTIR) study .....	33
<b>4.3. RESULTS</b> .....	34
4.3.1. Surface and cross sections of cocoon shells.....	34
4.3.2. Fiber surfaces, cross sections and voids .....	43
<b>4.4. DISCUSSION</b> .....	45
<b>CHAPTER FIVE</b> .....	50
<b>AMINO ACID COMPOSITION OF SILK FIBERS</b> .....	50
<b>5.1. INTRODUCTION</b> .....	50



<b>5.2. MATERIALS AND METHODS.....</b>	<b>53</b>
5.2.1. Sample preparation .....	53
5.2.2. Hydrolysis of silk .....	53
5.2.3. Amino acid analysis.....	54
<b>5.3. RESULTS AND DISCUSSION .....</b>	<b>55</b>
<b>CHAPTER SIX .....</b>	<b>59</b>
<b>WEIGHT LOSS AND MOISTURE REGAIN OF COCOON SHELLS AND DEGUMMED FIBERS.....</b>	<b>59</b>
<b>6.1. INTRODUCTION.....</b>	<b>59</b>
<b>6.2. MATERIALS AND METHODS.....</b>	<b>61</b>
6.2.1. Determination of weight loss from cocoon shells and cocoon shell layers .....	61
6.2.2. Determination of moisture regain of cocoon shells, degummed fibers and cocoon shell layers.....	62
<b>6.3. RESULTS .....</b>	<b>63</b>
6.3.1. Weight loss and moisture regain of cocoon shells and degummed fibers .....	63
6.3.2. Moisture regain and weight loss of cocoon shell layers .....	66
<b>6.4. DISCUSSION .....</b>	<b>69</b>
<b>CHAPTER SEVEN.....</b>	<b>72</b>
<b>DISSOLUTION PROPERTIES OF COCOON SHELLS AND DEGUMMED FIBERS .....</b>	<b>72</b>
<b>7.1. INTRODUCTION.....</b>	<b>72</b>
<b>7.2. MATERIALS AND METHODS.....</b>	<b>74</b>

7.2.1. Determination of dissolution of cocoon shells and degummed fibers.....	74
7.2.2. Scanning Electron Microscope observation of fibers after dissolution .....	75
<b>7.3. RESULTS .....</b>	<b>76</b>
7.3.1. Solubility of cocoon shells.....	76
7.3.2. Solubility of degummed fibers.....	78
<b>7.4. DISCUSSION .....</b>	<b>81</b>
<b>CHAPTER EIGHT .....</b>	<b>83</b>
<b>TENSILE PROPERTIES AND THERMAL DEGRADATION BEHAVIOURS OF COCOON SHELLS AND DEGUMMED FIBERS.....</b>	<b>83</b>
<b>8.1. INTRODUCTION.....</b>	<b>83</b>
<b>8.2. MATERIALS AND METHODS.....</b>	<b>85</b>
8.2.1. Determination of tensile properties of cocoon shells .....	85
8.2.2. Determination of tensile properties of degummed fibers .....	85
8.2.2.1. Measurement of cross sectional area of fibers .....	86
8.2.3. Analysis of fracture behaviour of cocoons and fibers .....	88
8.2.4. Determination of thermal degradation behaviours of cocoon shells and degummed fibers .....	88
<b>8.3. RESULTS .....</b>	<b>89</b>
8.3.1. Tensile properties of cocoon shells .....	89
8.3.2. Tensile properties of degummed fibers .....	93
8.3.3. Thermal degradation behaviour of cocoon shells.....	98
8.3.4. Thermal degradation behaviour of degummed fibers.....	102

<b>8.4. DISCUSSION .....</b>	<b>107</b>
<b>CONCLUSIONS AND RECOMMENDATIONS.....</b>	<b>110</b>
<b>    GENERAL CONCLUSIONS .....</b>	<b>110</b>
<b>    RECOMMENDATIONS .....</b>	<b>113</b>
<b>REFERENCES.....</b>	<b>115</b>
<b>APPENDICES.....</b>	<b>138</b>

## LIST OF FIGURES

	Pages
Figure 1: Cocoon shells of the four African wild and <i>Bombyx mori</i> silkmoths .....	29
Figure 2: SEM micrographs of hairs and spines from the surfaces of <i>Anaphe panda</i> and <i>Gonometa postica</i> cocoon shells.....	35
Figure 3: SEM micrographs of surface (a) and cross section (b) of <i>Epiphora bauhiniae</i> cocoon peduncle.....	36
Figure 4: SEM micrographs of attachment surfaces of cocoon shells of <i>Argema mimosae</i> and <i>Gonometa postica</i> .....	36
Figure 5: SEM micrographs of cocoon shell crystals of <i>Epiphora bauhiniae</i> and <i>Gonometa postica</i> .....	37
Figure 6: FTIR spectroscopy of outer (i) and inner (ii) cocoon shell surfaces of (a) <i>Anaphe panda</i> , (b) <i>Argema mimosae</i> , (c) <i>Bombyx mori</i> , (d) <i>Epiphora bauhiniae</i> , (e) <i>Gonometa postica</i> , (f) Calcium oxalate hydrate .....	38
Figure 7: SEM micrographs of outer (a) and inner (b) surfaces of hole/perforations of <i>Argema mimosae</i> cocoon shells .....	39
Figure 8: SEM micrographs of the outer (a-e), inner (f-j) surfaces and cross sections (k-o) of cocoon shells of African wild and <i>Bombyx mori</i> .....	42
Figure 9: SEM micrographs of the surface (a-e), cross section (f-j) and macrovoids (k-o) of African wild and <i>Bombyx mori</i> silk fibers.....	44
Figure 10: SEM micrographs of remnant sericin coating on African wild and <i>Bombyx mori</i> fibers after degumming.....	65
Figure 11: Percentage weight loss of layers of <i>A. panda</i> and <i>E. bauhiniae</i> cocoon shells.....	68
Figure 12: SEM micrographs of <i>Anaphe panda</i> , <i>Epiphora bauhiniae</i> and <i>Argema mimosae</i> fibers after dissolution with 9M LiBr.....	80

Figure 13: Imagej software images of the cross sectional area of African wild and <i>Bombyx mori</i> silk fibers .....	87
Figure 14: Stress-strain curves for <i>Gonometa postica</i> , <i>Argema mimosae</i> and <i>Bombyx mori</i> cocoon shells.....	91
Figure 15: SEM micrographs of fracture surfaces of <i>Gonometa postica</i> , <i>Argema mimosae</i> and <i>Bombyx mori</i> cocoon shells after tensile failure .....	92
Figure 16: Stress- strain curves for African wild and <i>Bombyx mori</i> degummed single silk fibers.....	95
Figure 17: SEM micrographs of fracture surfaces of degummed fibers after tensile failure..	97
Figure 18: TGA curves for cocoon shells of African wild and <i>Bombyx mori</i> silkmoths.....	100
Figure 19: SEM micrographs of cocoon shells discs of African wild and <i>Bombyx mori</i> silkmoths after TG analysis .....	101
Figure 20: TGA curves of African wild and <i>Bombyx mori</i> degummed silk fibers.....	103
Figure 21: SEM micrographs of African wild and <i>Bombyx mori</i> degummed silk fibers after TG analysis .....	105
Figure 22: High magnification SEM micrographs of <i>Argema mimosae</i> and <i>Epiphora bauhinae</i> fibers after TG analysis .....	106
Figure 23: Decomposition on-set temperatures for cocoon shells and degummed fibers of African wild and <i>Bombyx mori</i> silks.....	106

## LIST OF TABLES

	Pages
Table 1: Percentage amino acid composition of silks from selected arthropods.....	18
Table 2: Cocoon shells thickness of African wild and <i>Bombyx mori</i> silkmoths (Mean $\pm$ SE)	40
Table 3: Sample running conditions for HPLC amino acid analysis of African wild and <i>Bombyx mori</i> silk fibroins .....	54
Table 4: Percentage composition of major amino acids in the African wild and <i>Bombyx mori</i> silk fibroins.....	56
Table 5: Various Amino Acid Ratios.....	58
Table 6: Percentage weight loss and moisture regain of African wild and <i>Bombyx mori</i> cocoon shells and degummed fibers (Mean $\pm$ SE) .....	64
Table 7: Percentage moisture regain of layers of <i>Epiphora bauhinae</i> and <i>Anaphe panda</i> cocoon shells (Mean $\pm$ S.E.).....	67
Table 8: Percentage solubility of cocoon shells of four African wild silkmoths and <i>Bombyx mori</i> (Mean $\pm$ SE) .....	77
Table 9: Percentage solubility of African wild and <i>Bombyx mori</i> degummed silk fibers (Mean $\pm$ SE).....	79
Table 10: Tensile properties of <i>Gonometa postica</i> , <i>Argema mimosae</i> and <i>Bombyx mori</i> cocoon shells (Mean $\pm$ SE).....	90
Table 11: Tensile properties of single African wild and <i>Bombyx mori</i> silk fibers (Mean $\pm$ SE) .....	94
Table 12: Cross sectional area of African wild and <i>Bombyx mori</i> silk fibers (brin) (Mean $\pm$ SE) .....	96
Table 13: Weight loss of African wild and <i>Bombyx mori</i> degummed silk fibers and cocoon shells after TG analysis (Mean $\pm$ SE) .....	99

**ABBREVIATIONS AND ACRONYMS**

ANOVA	Analysis of Variance
DNA	deoxyribonucleic Acid
FAO	United Nations Food and Agriculture Organization
FTIR	Fourier Transform Infrared Spectroscopy
GLM	Generalized Linear Model
H-chain	Heavy chain fibroin
HPLC	High Performance Liquid Chromatography
ICIPE	International Center of Insect Physiology and Ecology
L-chain	Light chain fibroin
LSD	Least Significant Difference
RH	Relative Humidity
rpm	rotations per minute
SEM	Scanning Electron Microscope
TGA	Thermogravimetric Analysis
UVB	Ultraviolet B
WHO	World Health Organization

SEM micrographs showed that *G. postica* and *A. panda* cocoons had thorny spines and hairs on their surface, while *A. mimosae* cocoons were highly perforated. The FTIR spectra peaks around 1312 and 712 $\text{cm}^{-1}$  for outer surfaces revealed the presence of calcium oxalate crystals on *G. postica* cocoons. Cocoon surfaces also showed great cross bindings, wrinkles and networking of twisting filaments in different shapes and forms conferring rough outer surfaces. Fiber surfaces were irregular with several fibrillar sub-structures running along the fiber axis in *A. mimosae* and *E. bauhiniae*. The cross sectional view of degummed fibers revealed elongated, rectangular, triangular, globular and wedge shaped fibers with variable number and size of voids. HPLC results showed that African silk fibroins were characterized by the presence of high proportions of the three amino acids, glycine, alanine, and serine. These amino acids represented 71-74 and 82% of the total amino acids present in wild and *Bombyx mori* silk fibroins, respectively. No significant difference ( $P < 0.05$ ) was observed among the moisture regain of the wild silk degummed fibers. However, there were significant differences ( $P > 0.05$ ) in weight loss and moisture regain among cocoons as well as shell layers. *E. bauhiniae* cocoons had the lowest weight loss and moisture regain of 23.2 and 5.6%, respectively while *G. postica* and *A. mimosae* had the highest weight loss and moisture regain, 56.8 and 9.1%, respectively. In both *A. panda* and *E. bauhiniae*, the outer cocoon layers had the lowest moisture regain and highest weight loss while the inner layer of *E. bauhiniae* and middle layer of *A. panda* lost the least weight. African wild silk fibers and cocoons also showed significant variability ( $P > 0.05$ ) in their dissolution behaviours. Degummed fibers were more readily soluble than the cocoon shells. *B. mori* had higher solubility than the wild silk cocoon shells (51.5%) and fibers (59.3%). Among the wild



species, *G. postica* cocoons and degummed fibers had the highest solubility (37.3 and 51.7%, respectively). LiBr was the most effective dissolving agent for both the cocoons and fibers (41.2 and 84.5%, respectively).

The tensile test measurements showed that *G. postica* and *A. mimosae* cocoons had lower breaking stress and breaking energy and higher breaking strain than *B. mori*. *Gonometa postica* fibers had the highest breaking strain (41.3%), while *E. bauhiniae* had the lowest breaking stress (237MPa). Wild silk fibers had breaking energy ranging between 34.5-76.4J/cm<sup>3</sup>. The TGA curves showed *A. mimomsae* fibers and cocoons had higher temperature for water loss (113 and 154°C, respectively). *G. postica* cocoons underwent multistep decomposition between 296-413, 483-506, and 710-730°C. *B. mori* had the highest total weight loss for degummed fibers (93.4%), while *E. bauhiniae* cocoons lost the highest total weight (97.2%). The overall results demonstrated the extensive variability present in structure, composition and properties among silks of the four African wild silkmoths. This could be associated with the selection pressure for environmental adaptation experienced by each species and the difference in molecular organization and composition of silk spun by each species. The physical structure and chemical composition of the cocoon shells and fibers have contributed towards the variations observed in the properties and these features have commercial and industrial implications. Hence, the value of silks when compared across taxa should be based on suitability of the fiber properties for specific application as well as potential silk products.

## CHAPTER ONE

### GENERAL INTRODUCTION

#### 1.1. Background information

Silks are fibrous proteins containing repetitive sequences of amino acids that are stored as a liquid but configure into solid filaments when spun upon secretion (Craig, 1997). Silks, from domesticated and wild silkworms and spiders, represent a unique and important class of polymeric composite materials in nature providing a wide range of evolutionary and ecological functions with an optimum microstructure and properties. Owing to its high qualities of strength, elasticity, softness, absorbency and affinity for dyes, silk has been used for over 5000 years and is still considered a unique textile material in the world (Li *et al.*, 2006). Silk, specifically from *Bombyx mori* L., is a premium priced textile commodity, although its sheer volume is less than 1 percent of the market for natural textile fibers. In addition to applications in textile, silk fibers have gained a great deal of attention because of their potential use as multifunctional materials in various fields, such as biotechnological, biomedical, tissue engineering, cosmetics, ink additives, resin composites and paints (Wang *et al.*, 2007; Kim *et al.*, 2008; Fang *et al.*, 2009; Nagai *et al.*, 2009). Many indigenous wild silkmoth species around the world have also been utilized locally and regionally for many years.

Wild silkmoths, sometimes referred to as non-mulberry silkmoths, generally defined as those that are not reared in captivity but present in the wild on their natural food plants. Craig

(2008) described “wild” silk as any type of silk other than that spun by *B. mori*, and it is produced all over the world by different species of silkmoths across wide range of ecologies. African wild silkmoths are known to be found distributed in most regions of Africa and occur mainly in three major families, Saturniidae (*Ephiphora* and *Argema* species), Lasiocampidae (*Gonometa* species) and Thaumetopoeidae (*Anaphe*, *Epanaphe* and *Hyposoides* species) with significant economic importance due to their exceptional quality fibers and aesthetic values (Kioko, 1998; Delport, 2006). The potential of these African indigenous species for wild silk production has been documented in Nigeria (Ashiru, 1988), Botswana (Hartland-rowe, 1992), Zimbabwe (Chikwenhere, 1992), Uganda (Gowdey, 1953), South Africa (Veldtman, 2005), Kenya (Raina, 2004), and Madagascar (Peigler, 1993; Razafimanantsoa *et al.*, 2006) among others. With the rich diversity of wild silkmoths recorded in Africa, wild silk farming has the potential to provide economic incentives for communities (Raina *et al.*, 2009). For example, Mbahin (2008) reported processing of *Anaphe panda* silk cocoons increased the net income of farmers twenty four times. Wild Lepidoptera silks also provide a tool for sustainable development and conservation of biodiversity (Akai, 2000; Thangavelu, 2002). Wild silks have advantage over mulberry silk in that they generally come in natural colours and are not only user friendly but also healthy owing to their porous texture and thermal properties (Arunkumar *et al.*, 2006). However, despite rich biodiversity and suitable environmental, social and economic conditions, silks from the African wild silkmoths have largely escaped the notice of the modern commercial and scientific world until recently.

Silk cocoon shells from silkmoths are non-woven structures and exhibit extensive variation in composition, structure, and properties, which impose direct influence on their adaptive functions. The urge to characterize and understand silks has been driven by variability in their exceptionally useful properties such as lightweight, high modulus, high strength, high elongation and energy to break and thermal stability depending on their origin (Kaplan *et al.*, 1991; Amiraliyan *et al.*, 2009). These properties, however, are influenced by the individual silk fiber components, hierarchical structure, spinning conditions and the degumming process (Chen *et al.*, 2001; Shao and Vollrath, 2002; Pe´rez-Rigueiro *et al.*, 2002; Zhang *et al.*, 2010a). The amino acid composition of silk produced by arthropods is also highly variable and is known to influence physical properties of the fibers (Lucas *et al.*, 1958). The protein composition, together with spinning speed and the carving of the fiber’s surfaces when it passes through the larval spinnerets, result in different biomechanical and surface properties of the silk fibers.

Ecological adaptations also play a significant role in effectively modifying the structure and properties of the silk fibers and construction of variable cocoons. Specifically, absorbed moisture and temperature are likely to determine the mechanical and physical properties of both the sericin ‘gum’ coating and the integral structural proteins (fibroin) of the silks (Fut *et al.*, 2009). The importance of cocoon shells in temperature regulation, water loss reduction from the pupae (Rosner and Fhrer, 1996) and acquisition of heat (Danks, 2004) has been reported. The thermal tolerance of organisms also plays significant role as performance in nature mainly depends on native adaptability to varied environmental conditions (Manjunatha

*et al.*, 2010). Thus, proper understanding of such natural polymer materials is an indispensable step toward clarifying their structure- property- function relationships.

## **1.2. Statement of the problem**

Silk cocoon characteristics of many silk producing insects vary widely in size, structure, properties, as well as in other features such as orientation, attachment to the substrate and amino acid composition of the individual components. In some species, these properties also vary with season and location. Most of the research works in this regard has been focused on spiders and mulberry silkworms in an attempt to comprehend and improve their properties, and hence broaden their application. So far, there is little comprehensive information available on the diversity of different structures and properties of the silks produced by African wild silkmoths. Only data about their biology, host plant distribution and ecology is available. Hence, detailed study of their fiber and cocoon shell structures and properties is required to gain a complete view of their nature and design their wider application.

Although the African wild silks have many important advantages over the Asiatic wild silks, it has not also been possible hitherto to introduce it in substantial quantity to the textile or any other industry. One possible reason for this might be limited data on their properties and the underlying rationale for the variations, if any. There has also been limited instructive study on the structure and properties of the silk fibers that are grown and produced in a wide range of environmental conditions to establish whether the correlations have practical validity. As the

micro and macrostructure of cocoon shells and fibers affect properties of the silk such as strength, stiffness and resilience, the relation between such mechanical properties and the protein components has not yet been established for African wild silk fibers.

### **1.3. Justification**

With the current increased quest for development of excellent biomaterials and other biological organic products, silk appeared as one of the best candidates. The demand for silk is constantly increasing in the world market and this provides excellent opportunities for any producer country to diversify and optimize any source of production. The ever growing evidence on the existence of diverse properties of silks from various silk producing arthropods instigated the search for new silk sources and design ways to exploit them effectively in the desired fields of application. There is also an urgent need to accumulate information on silk structure and properties in relation to product requirements. The African wild silkmoths are among such insects known to produce silk of economic importance and with enormous potential to be exploited. Therefore, understanding of the different properties of these silks (and silkworms and host plants) allows innovative conservation and poverty alleviation programs thereof to better leverage their success.

A complete comprehension of the diversity of silk fibers from African wild silkmoths and their structure and properties is also required to develop management plans for the conservation and sustainable utilization. This comes about by disseminating information to

the many potential users, many of whom do not as yet even know the importance of the silk, especially the African wild silks. This is also a key factor for the successful application of silk fibers in various fields and helps in selection of good quality cocoons for silkworm breeding and processing programmes. This information will also be useful to select species of wild silkmoths that could have an optimum economic and conservation effect with fibers that exhibit tailored combinations of properties under specified environments. The knowledge on the structures and properties of cocoon shells and fibers will give confirmation and develop quality standards that could be of interest for the design and tailoring of advanced silk materials. This will give silk producers, processors and traders additional confidence to effectively compete in the special silk markets. The study is also important to highlight the potential of Africa to introduce completely new forms of wild silk fibers to the world and exploration of new opportunities of how they can be utilized in the future. More importantly, this study serves as a comprehensive academic and research reference regarding silks produced by African wild silkmoths.

#### **1.4. Hypotheses**

1. The surface structure and cross sectional shape and size of the African wild silkmoths' cocoon shells and fibers do not show variability.
2. African wild silkmoths produce silk cocoon shells and fibers that do not exhibit variability with regard to their amino acid composition, solubility, weight loss and moisture regain properties.

3. There is no variation in mechanical (tensile) and thermal degradation properties of degummed silk fibers and cocoon shells from the African wild silkmths.

## 1.5. Objectives

### 1.5.1. General objective

To determine the extent of variability in structure, composition and properties of African wild silk cocoon shells and fibers from three major Lepidopteran (*Saturniidae*, *Lasiocampidae* and *Thaumetopoeidae*) silkmths.

### 1.5.2. Specific objectives

1. To study the surface structures and cross sectional properties of cocoon shells and degummed fibers from African wild silkmths
2. To determine the amino acid composition of fibroins from African wild silk fibers
3. To determine the sericin content and moisture regain properties of African wild silk cocoon shells, degummed fibers and cocoon shell layers
4. To study the dissolution properties of African wild silk cocoon shells and degummed fibers in different solvent systems
5. To determine the tensile properties (stress-strain responses) and thermal degradation behaviour of African wild silk cocoon shells and degummed fibers



## CHAPTER TWO

### LITERATURE REVIEW

#### 2.1. Seri-biodiversity

Seri-biodiversity refers to the variability in sericigenous (silk producing) insects and their host plants, which are economically and ecologically important biodiversity and largely, forest based (Srivastava and Thangavelu, 2005). The word silk is most often associated with the filaments produced by the domesticated silkworm *Bombyx mori*, but the fact is, a number of classical animals such as lepidoptera, hymenoptera, diptera, neuroptera, acarids and araneids have evolved to produce a variety of silks with different properties and for varying purposes (Craig, 1997; Hardy and Scheibel, 2009; Vollrath and Porter, 2006). The most important functions of silk include web construction, shelter building, leaf tying, construction of pupal cocoons, and as a safety line when dislodged from a substrate (Common, 1990).

Craig (2008) described “wild” silk as any type of silk other than that spun by domesticated silkworm, *B. mori* and it is produced all over the world by different species of silkmoths across wide range of ecologies. Across the arthropods, silk displays a diversity of material properties and chemical constituents and is produced from glands with different evolutionary origins (Craig, 1997). There are several domesticated and wild sericigenous insects and their host plants, which are abundant in different regions and parts of the world. However, only a few types of insects are commercially exploited and there remains a great scope for producing novel silk from other lesser known species (Mbahin, 2008).

### 2.1.1 Silkworms

In total, there must be well over 200,000 different silks with either major or minor sequence differences (Craig, 1997). Though accurate data are not available on the silkworm germplasm in different countries of the world, approximate information indicate that there are 4310 silkworm germplasm accessions available in different countries (FAO, 2003). There are around 3000 genotypes of *B. mori* at the global level, which includes mutants, parthenoclones, polyploids and geographical races (Nagaraju *et al.*, 2001).

There are 400-500 species of silk-producing moths in the world, but only nine species such as *Bombyx mori*, *Philosomia ricini*, *Antheraea mylitta* and *Antheraea assama* are commercially cultivated (Dingle *et al.*, 2005). Jolly *et al.* (1975) reported about 80 wild silk species occurring in Asia and Africa to produce silk of economic value. In Kenya, Uganda and Tanzania, 58 wild silk moth species were found to occur in Saturniidae (19 species in six Genera), Lasiocampidae (33 species in 17 Genera) and Thaumetopoeidae (six species in one genus) Families (Kioko, 1998). Nassig *et al.* (1996) reported that the Family Saturniidae comprises of about 1200-1500 species all over the world making it the largest Family of Bombycoidea containing about 1861 species in 162 Genera and 9 subfamilies (Lemaire and Minet, 1998). They include some of the largest and most spectacular species of all Lepidoptera which are univoltine to multivoltine depending upon the climatic conditions and are distributed in both temperate and tropical region (Regier *et al.*, 2008). Kakati and Chutia (2009) recorded fourteen species of sericigenous insects belonging to eight Genera from the

state of Nagaland, India, comprising species of *Antheraea*, *Actias*, *Samia* and *Loepa*. Silkworms produce cocoon shells from silk-protein-based fibers as a means of protection during their metamorphosis into moths. The cocoon is firm to resist mechanical damage, durable to withstand harsh weather conditions, non-palatable to resist attacks by animals, and immune to microbial degradation.

### 2.1.2. Silk from spiders

Currently, 40,700 spider species belonging to 3,733 Genera and 109 Families (Platnick, 2009) are known and more than 40,000 species use dragline silk for a variety of functions such as lifelines and the frames of webs (Blackledge *et al.*, 2009) and further, more than 130 different shapes of spider webs are known (Römer and Scheibel, 2008). Among the most studied webs are the so-called orb webs which consist of several different types of silk (Vollrath, 2000). Orb-weaving spiders (Araneidae) such as *Nephila clavipes* can produce up to seven different types of silk that originate from different abdominal glands (Lewis, 2006) to capture prey, protect their offspring/prey and as lifelines to escape from predators (Römer and Scheibel, 2008; Hardy and Scheibel, 2009). A number of taxonomically diverse species of araneoid spiders adorn their orb-webs with conspicuous silk structures, called decorations or stabilimenta. The function of these decorations remains controversial and several explanations have been suggested including stabilizing and strengthening the web, hiding and concealing the spider from predators, preventing web damage by larger animals, such as birds, increasing foraging success and providing a sunshield (Herberstein *et al.*, 2000).

### 2.1.3. Other silk producing arthropods

The ability to produce silk proteins has evolved multiple times in the arthropods. The fibrous proteins, constituting the silk, are produced in different glands (colleterial, salivary, dermal glands, and Malpighian tubules) in both adult and larvae (Rudall and Kenchington, 1971). Weijers *et al.* (2008) reported the green lacewing (*Mallada signata*, Neuroptera) produces two distinct classes of silk, the larval lacewing cocoon silk and the adult lacewing egg-stalk silk. Caddis flies, *Limnephilus decipiens*, use silk rather sparsely for stitching portable larval cases from the pieces of plants, sand, or other foreign materials and larvae of *Hydropsyche angustipennis* produce large amounts of silk to spin food-collecting nets and retreat tunnels (Yonemura *et al.*, 2009). From an early larval stage, the caterpillars of *Galleria mellonella* (Pyralidae), which develop in bee colonies, spin silky tubes that protect them against the detection and killing by the bees. Larvae of the Mediterranean flour moth, *Ephestia kuehniella*, which typically attack ground cereal products, spend most of their life in silk tubes that probably provide some protection against parasitoids and reduce water loss (Fedic *et al.*, 2003). Larvae of Siphonaptera (fleas) produce silk from the labial glands to construct nests, pupation cases and individual and group cocoons (Sehna and Sutherland, 2008). The glowworm (*Arachnocampa luminosa*: Mycetophilidae) larvae spin silken nests on the roof of caves or overhangs and suspend silken snares from this nest to trap prey. Mayflies (Ephemeroptera) attach themselves to surfaces using suckers, claws and small silk filaments (Cave, 1998). *Theriodopteryx ephemeraeformis* (bagworms) has been reported to produce remarkably different ultrafine silk fibers (Reddy and Yang, 2010a).

Cocoon silks produced from the labial glands of Hymenoptera (sawflies, ants and bees) has also been reported (Sehnal and Sutherland, 2008). The larvae of social wasps and hornets (Hymenoptera:Vespinae) also spin a silk weave around their body before metamorphosing to a pupal stage (Spradbery, 1973). *Tetranychus urticae* is a ubiquitous phytophagous mite with abundant silk production continuously while walking for protection against biotic and abiotic agents and as sex pheromone (Clotuche *et al.*, 2009). The silk gland of last instar *Diatraea saccharalis* produces large amount of silk to protect the insect (Victoriano *et al.*, 2007). Weaver ants, *Oecophylla*, use silk from larvae approaching metamorphosis to bind the leaves of their nest together and Psocoptera have two labial glands, one pair produces saliva and the other, silk (Chapman, 1998). Edgerly and Rooks (2004) documented the diversity of *Antipaluria urichi* (Embiidina :Clothodidae) spinning behaviour and use of silk, implications for maternal care, short and long term costs of spinning, and how the variable reliance on silk as a building material relates to colonial behaviour. In Neuroptera and few Coleoptera, a secretion from the malpighian tubules flows into the hindgut and is extruded from the anus to spin the cocoon (Rudall and Kenchington, 1971). Hard cocoons consisting of particles of earth, dung fibers or any other suitable material cemented together by a liquid that dries to a smooth, glistening, translucent substance on the inside of the cocoon were made by all species of Musciidae other than *Passeromyia* and *Philornis*, that form white froth, thick, soft coating around the puparium, usually without objects deliberately cemented into it (Ferrari, 1980). Scorpions, mygalomorphs and ctenizids use silk to line burrows and construct trip-lines (Vollrath and Selden, 2007).

Unusual silk occur in the cocoon of Chrysopid larvae, which are composed of a cuticulin like materials and of *Ptinus tactus* larvae which are formed from an unbroken chitaneous thread of peritrophic membrane extruded from the anus (Richards and Davies, 1977). Other filamentous proteins, such as the widely studied byssus of molluscus, have a silk like structure, but are not included in the definition of silk (Gellynck, 2006). Another silk or silk like filament is the biopolymer composed of at least ten proteins secreted by the salivary glands of the bloodworm *Chironomous* (Case and Wieslander, 1992). Male myriapoda secrete fibrous proteins from their accessory glands to produce sperm webs, sperm stalks, and mating threads while the female Diplopoda and Symphyla use them for molting, egg cocoons, defence and communication (Craig, 2003).

## 2.2. Composition of silk

The cocoons of mulberry and non-mulberry silkworms contain two major proteins, a double strand of fibroin, which is held together by a gummy substance, sericin. Silk also contains several low molecular weight polypeptides, waxes and fats. The silk fiber has a triangular cross section and composed of two protein mono filaments (known as brins) lie with the flat sides of the triangles together, encircled by a sericin coating (Altman *et al.*, 2003). The brins are fibroin filaments made up of bundles of nano-fibrils, approximately 5nm in diameter, with a bundle diameter of around 100nm (Poza *et al.*, 2002). The fiber is smooth and transparent and has a rod-like shape, occasional swelling or irregularities along its length and with a diameter of 9–11  $\mu\text{m}$  (Li *et al.*, 2006).

### 2.2.1 Fibroin

Fibroin accounts for about 70-80% of the raw silk thread depending on the silkworm origin. The fibroin consist of three proteins: heavy chain fibroin (H-fib), light chain fibroin (L-fib) and P<sub>25</sub> (fibrohexamerin protein) (Kojima *et al.*, 2007). *B. mori* H-fib is a large protein (~390 kDa) and L-fib is lighter (25-30kDa) (Inoue *et al.*, 2000). The H- chain consists of three domains: an N-terminal domain (contributing to the solubility of the H-Chain), a repeated region (contributing to the physical properties of fibroin fiber) and a C-terminal domain (containing cysteine residues that form intra- and inter-molecular disulfide bonds). P<sub>25</sub> is a glycoprotein containing asparagin-linked oligosaccharide chains and forms a compact structure due to intra-molecular disulfide linkages but associates with the H-L complex by non-covalent interactions (Tanaka *et al.*, 1999). Its central role is maintaining the structure of elementary unit. However, these compositions might not always exist in all kinds of silk fibers. For example, silks of caddis flies contain H-fibroin and L-fibroin but not P<sub>25</sub> component (Yonemura *et al.*, 2009) while the specialized moth Family Saturniidae has lost both L-fibroin and P<sub>25</sub> (Tanaka and Mizuno, 2001). The composition of amino acid residues in the fibroin is 45.9% Glycine, 30.3% Alanine, 12.1% sericin, 5.3% Tyrosine, 1.8 % Valine, and only 4.7% of the other amino acid residues (Zhou *et al.*, 2000). On the other hand, the L-chain is non-fibrous and contains relatively high amounts of leucine, isoleucine, valine, and acidic amino acids (Shimnra, 1983). The major constituent of fibroin repetitive region is a hexapeptide (Gly-Ala-Gly-Ala-Gly-Ser)<sub>n</sub> in *B. mori* while in wild silk and *Galleria*

*mellonella* the repetitive region is poly-alanine and has higher amino acids with long side chains than *B. mori* silk (Fedic<sup>˘</sup> *et al.*, 2003).

### 2.2.2. Sericin

Sericin is sticky protein, which glues together fibroin threads and constitutes about 25–30% of silk protein and 20 – 30% of the cocoon weight (Zhang, 2002). The greatest sericin content is present in the outer layer of cocoon whereas the least sericin proportion is present in the innermost layer (Mondal *et al.*, 2007a). Sericin is a mixture of proteins with a large number of amino acids containing hydroxyl groups and is therefore more soluble in water. It majorly contains serine (32%) and large proportion of several polar amino acids that confers it with high hydrophilicity and adhesion (Gamo *et al.*, 1977; Padamawar and Pawar, 2004). The sericin amino acids can be categorized into three types: neutral (glycine, alanine, leucine, isoleucine, proline phenylalanine, tryptphan, cystine, valine, serine, theonine and tyrosine), alkaline (arginine, histidine and lysine) and acidic (Methionine, aspartic acid, and glutamic acid) (Datta and Nanavaty, 2007). Komatsu (1975) and Robson (1985) reported sericin might be separated into sericin I, II, III and IV depending on their hot water solubility. Sericin I is more soluble than the others and sericin IV being harder to dissolve. The wild silk sericin is relatively insoluble compared to *B. mori*, mainly due to chemical interaction between silk sericin and inorganic minor components or tannins contained originally in wild silk (Mondal *et al.*, 2007a).



### 2.2.3. Other components of silk

Silk also contains several low molecular weight polypeptides and a small percentage of waxes and fats (~1.5%), carotenoids pigments and mineral components (~2%), ash (0.3- 2.0%) and small amounts of polysaccharides which occur exclusively in the sericin layer (Voegeli *et al.*, 1993; Aruga, 1994; Schoeser, 2007). Several proteins that are smaller than the main fibroin and sericin components appear to serve defensive anti-bacterial and anti-fungal roles (Akai, 1977). Green cocoons are already known to contain a compound that is a typical polyphenolic substance flavonol, with clear antioxidant and antibacterial activities (Mase *et al.*, 2008).

### 2.2.4. Amino acid composition

Silks are fibrous proteins made up of repetitive sequence of amino acids. These amino acids are stored in the animal as a liquid and configure into fibers when sheared at secretion (Craig, 2003). Amino acid composition of mulberry and non-mulberry silk varies and is used to establish the first classification of silks (Lucas *et al.*, 1955). The specific ratios of amino acids are dependent on rearing conditions, processing, use, and age (Miller and Reagan, 1989). Glycine, alanine, and serine form the major components of mulberry and non-mulberry silk although large differences have been found in the relative frequency of each amino acid (Dhavalikar, 1962; Pe´rez-Rigueiro *et al.*, 2000). The composition of these three amino acids was the highest in Eri silk (84.26%) followed by mulberry (82.8%), Tasar (72.06%) and

Muga (67.77%). Nadiger *et al.* (1985), however, reported higher percentage (91%) for mulberry silk than other wild silks (77 - 82%). In General, higher relative content of alanine than glycine was reported in wild silkworm silk than *B. mori* (Gary and Gary, 2008).

Alanine and glycine are dominant in cocoon shell of *Rondotia menciata* and *B. mandarina*, (Ito *et al.*, 1992). Most of the silk proteins of ants, bees and wasps have few glycine residues and high content of acidic residues (Rudall, 1962). In ichneumonoids, serine, alanine and glycine can comprise up to 80% of the amino acid residues (Craig and Riekel, 2002). *Pycnopsyche guttifer* (Walk.) silk have dominantly glycine, serine and Arginine (Engster, 1976). These results show that the amino acid composition the cocoon is species specific. A summary of the amino acid composition of various silks is presented in Table 1.

Table 1: Percentage amino acid composition of silks from selected arthropods

Amino Acids	Species						
	<i>B. mori</i>	<i>R. Menciaana</i>	<i>B. mandarina</i>	<i>Nephila clavipes</i> (residue/100 total residue)	<i>Argiope aurantia</i> (residue/100 total residue)	<i>Anaphe</i>	<i>S.c. ricini</i>
Glycine	42.9-45.5	41.15	41.88	37.1	34.7	32.3	33.2
Alanine	30-30.9	37.17	37.48	21.1	22.2	59.1	48.4
Serine	10.7-12.2	7.68	9.71	4.5	5.1	2.4	5.5
Tyrosine	4.25-4.8	2.5	3.95	2.9	3.8	0.8	4.5
Valine	2.16-2.5	1.05	1.80	1.8	1.5	0.4	0.4
Aspartic acid	1.43-1.9	1.92	1.18	2.5	1.6	1.7	2.7
Glutamic acid	1.07-1.7	3.48	1.03	9.2	1.6	0.9	0.7
Threonine	0.83-0.9	0.68	0.70	1.7	0.8	0.3	0.5
Lysine	0.36-0.4	0.72	0.24	0.5	0.5	0.1	0.2
Phenylalanine	0.61-0.7	0.31	0.61			0.1	0.2
Isoleucine	0.54-0.6	0.56	0.39	0.9	0.8	0.2	0.4
Arginine	0.46-0.5	1.98	0.3	7.6	2.9	-	1.7
Leucine	0.41-0.6	0.60	0.33	3.8	4.2	0.6	0.3
Proline	0.36-0.5	0.13	0.12	4.3	6.4	0.6	0.4
Histidine	0.20	0.06	0.19			0.5	1.0
Methionine	0.07-0.1			0.4	0.3	0.02	0.01
Cystine	0.03-0.14			0.1	0.3	-	0.01
Tryptophan							0.3

Data from; Lombardi and Kaplan, 1990; Ito *et al.*, 1992; and Tanaka *et al.*, 2008

## 2.3. Properties of silk

### 2.3.1. Tensile properties

The tensile strength of a material is the maximum amount of tensile stress that it can be subjected to before failure. Tensile strength is measured in units of force per unit area. It has an important application in engineering, especially in the fields of material science, mechanical engineering and structural engineering. High tensile strength is the major mechanical requirement imposed on the cocoon silk. *Bombyx mori* cocoon has a tensile strength of about 0.5GPa, with a breaking elongation of 15% and a breaking energy (toughness) of  $6 \times 10^4$  J/kg (Shao and Vollrath, 2002; Pérez-rigueiro *et al.*, 1998). Michalak *et al.* (2005) showed that the specific strength of fibers produced by caddis-flies is  $5.7 \times 10^9$  N/m<sup>2</sup>. Typical *Nephila* spider dragline silk has strength of 1.3GPa, with an elongation of 40% and a toughness of  $6 \times 10^4$  J/kg (Madsen *et al.*, 1999; Vollrath *et al.*, 2001). Tussah silk fiber has a relatively high extensibility as compared to *B. mori* silk fiber and other natural fibers (Cheung, 2009). These mechanical measures show considerable inter- and even intra-individual variability. For example, the tensile properties of silk collected from the spider web shows an intrinsic variability, even among fibers from a single web (Work, 1976). The large variability of the tensile properties of spider silk was interpreted in biological terms as a contribution to the survival ability of the spider (Madsen *et al.*, 1999).

The mechanical properties of silk fibers appear to be determined by the amino acid sequence of the heavy-fibroin, which is for the most part composed from repeats (Fedič *et al.*, 2003)

as well as the conditions under which the protein is produced (Kerkam *et al.*, 1991; Holland *et al.*, 2006). The extraordinary toughness of silk is assumed to be encompassed by the strong and stiff crystalline units, taking up the mechanical load in stretched as stiffness attracts force and thereby protects against failure (Xio *et al.*, 2009), while the interspersed “amorphous” regions confer the elasticity of the silk (Fedić *et al.*, 2003). Shao and Vollrath (2002) indicated the mechanical properties of *Bombyx* silk, like those of spider silk, depend crucially on spinning conditions.

### **2.3.2. Solubility and thermal properties**

The solubility of silk fibroin in certain solvents has been studied in recent years and several different solvent systems including Lithium bromide (Alessandrino *et al.*, 2008), N-methylmorpholine-N-oxide (NMMO) hydrate (Plaza *et al.*, 2008), Phosphoric acid/formic acid mixture (Ki *et al.*, 2007a), Calcium nitrate (Kweon *et al.* 2001), and CaCl<sub>2</sub> (Miyaguchi and Hu, 2005) have been recommended. These solvents can be classified into two as acidic solvents (Formic acid) and high ionic-strength aqueous salt solutions. Acidic solvents tend to be harsh and have poor solution stability, while basic solvents make removal of the inorganic salts from the solutions difficult (Wang *et al.*, 2006). The spider silk protein is partially soluble in mineral acids and alkaline hydroxides and completely soluble in concentrated solutions of Lithium bromide, Lithium thiocyanate or Calcium chloride, and ethyl alcohol (Saravanan, 2006).

Thermal decomposition of *B. mori* silk occurs above 250°C and the fibers are thermally stable up to 230°C (Kaplan, 1998). Prasong *et al.* (2009) found thermal decomposition of *B. mori* silk occurs at 350°C and 360°C for silk with and without sericin, respectively, while Eri silk underwent three thermal decomposition stages at 200-300°C, 300-350°C and 350-400°C however, the silk did not completely decomposed even at 1000°C. Zhang *et al.* (2002) reported 9% and 8.2% initial weight loss from cocoon shell and silk fiber, respectively attributed to the evaporation of water 105°C. They also reported only 1% and 0.9% of the original cocoon shell and silk fiber weight remains as ash after heat treatment at 550°C. Dragline silk from the spider, *N. clavipes* has a thermal stability to about 230°C (Cunniff *et al.*, 1994).

## 2.4. Applications of silk

### 2.4.1. Dietary and medicinal applications

*B. mori* has high protein content, reasonable nutrient compositions and ample contents, a short lifespan, easy breeding method, small growth room, and little odour and waste water produced (Yang *et al.*, 2009). The proximate compositions of silkworm pupae is in the range of 12 to 16% total protein, 11 to 20% total fat, 1.2 to 1.8% carbohydrates, 65 to 70% moisture and 0.8 to 1.4% ash which can be easily digested and absorbed by human body, promote the physiological functions of the gastrointestinal tract and plays an excellent role in lowering blood-glucose levels (Mishira *et al.*, 2003). *B. mori* pupae is very rich in protein, oil, carbohydrate and minerals and can be utilized as a high potential raw material for various industries including pharmaceuticals, paints, varnishes, soaps, candles, bio-diesel and plastic

industries (Trivedy *et al.*, 2008). The protein of silkworm pupae is a new available source of high quality protein that contains all the amino acids needed by the human body with appropriate proportions in line with FAO/WHO standards (Xia and Zhao, 2003; Zhou and Han, 2006). More than 30% of pupae oil is linolenic acid, which is the raw material for human docosahexaenoic acid (DHA) exerting an important effect on human intellect and memory improvement, sight-protection and is a precaution chemical against hyper-lipoidemia (Lu *et al.*, 1998). In fact, the protein of pupae is better than the protein of soybean, fish or beef (Trivedy *et al.*, 2008). Sericin contains amino acids that can be easily absorbed by human body and over 17% of which are eight kinds of essential amino acids higher than that found in common food (Zhang *et al.*, 2000; Yang *et al.*, 2009). Intake of sericin containing food relieves constipation, suppresses development of bowel cancer and accelerates the absorption of minerals (Padamawar and Pawar, 2004).

#### **2.4.2. Cosmetic application**

The silk fibroin peptides are used in cosmetics due to their glossy, flexible, elastic coating power, easy spreading and adhesion characters (Kumaresan *et al.*, 2007). The extracts of silk protein like hydrolyzed silk, silk amino acids, silk powder and raw silk are used in soap making, personal care and cosmetic products (Gulrajani, 2006). Powdered silk fibroin is considered to be effective as an additive for cosmetic and pharmaceutical preparations because of its moderate moisture absorption and retention properties and its high affinity for the human skin (Takeshita *et al.*, 2000). Sericin alone or in combination with silk fibroin has been used in skin, hair and nail cosmetics. Sericin when used in the form of lotion, cream and

ointment shows increased skin elasticity, anti-wrinkle, and anti-aging effects (Li *et al.*, 2009.). Nail cosmetics, containing 0.02 - 20% sericin are reported to prevent nail from chapping, brittleness, and imparting the inherent gloss to nails (Yamada *et al.*, 2001). Creams containing 0.001- 30% (w/w) of sericin improves cleansing properties with less skin irritation (Sakamoto and Yamakishi, 2000). Sweat and sebum absorbing type of cosmetics containing cellulose impregnated with fibroin dispersion and aqueous sericin solution are also reported (Miyashita, 1999). Chinese oak silkworm, *Antheraea pernyi*, is commercially cultivated mainly for silk production and presently it is mostly used as a source of insect food (larva, pupa, and moth) and for cosmetics (Li *et al.*, 2009).

### **2.4.3. Applications in pharmaceuticals, biomaterials and biomedical materials**

#### **2.4.3.1. Applications of fibroin**

Among the natural biodegradable polymers like collagen, gelatine and chitosan, silk fibroin provides an important set of material options for biomaterials and scaffolds in biomedical applications because of its high tensile strength, controllable biodegradability, haemostatic properties, non-cytotoxicity, low antigenicity and non inflammatory characteristics (Stitzel *et al.*, 2006). This protein is biocompatible, degrades slowly in the body, and is readily modified into a variety of formats and Generates mechanically robust materials (Altman *et al.*, 2003). Fibroin has been used particularly as a suture material in tendon repairs for many years (Lovett *et al.*, 2007) as it does not cause inflammatory reactions and absorbed after wounds heal (Reddy, 2009). Fibroin is also used to produce vascular grafts (Sakabe *et al.*, 1989),



membrane frames that allowed oxygen flow for contact lens (Minoura *et al.*, 1990) and artificial skin for use in healing fire burned wound as fibroin had high evaporation rate (Liu *et al.*, 2010). Moreover, fibroin is appropriate for producing artificial ligament tissues as fibroin absorbs calcium ions in a great deal and is very flexible (Fang *et al.*, 2009). Fibroin also helps drug delivery process which could control drug release (Tsukada *et al.*, 1994) and regularly used as healing wound pad as it allows cell adhesion and cell growth (Min *et al.*, 2004).

In order to function as a potential biomaterial, biocompatibility is obviously an important prerequisite, and *in vivo* studies have shown that both *B. mori* and spider silk are biodegradable and evoke a comparable defence reaction as materials routinely used in surgery (Vollrath *et al.*, 2002; Gellynck *et al.*, 2008). Spider silk have good clotting properties due to the fine size of its threads and have anti-bactericidal properties (Vollrath and Knight, 2001). MacIntosh *et al.* (2006) demonstrated *Nephila edulis* egg case silks support the attachment, proliferation and re-differentiation of bovine articular chondrocytes *in vitro*. Kim *et al.* (2008) showed aqueous-derived porous silk fibroin scaffolds could be applied in bone tissue engineering. The hexapeptides derived from fibroin not only enhance insulin-stimulated glucose uptake but also block the development of insulin resistance in cells exposed to chronic insulin (Kim *et al.*, 2009). The silk fibroin peptides are also used in the biomedical field with a novel bio-mimetic design of silk fibroin-nerve guidance conduit (SF-NGC) used for peripheral nerve reGeneration (Reddy, 2009). Fibroin proteins from *Antheraea mylitta* and *B. mori* are immunologically inert and invoke minimal immune response (Acharya *et al.*, 2008). The fibroin powder is known for wound dressing by

maintaining a moist environment and absorbing excess exudates from the wound (Teramoto *et al.*, 2008). The silk fibroin could also be applied as an alternative material for removing/filtration of particulate matters in indoor air (Triped *et al.*, 2009).

#### **2.4.3.2. Applications of sericin**

Sericin solutions has the potential to promote wound healing and wound-size reduction in rat eyes, probably as a result of increased cell movement and proliferation (Nagai *et al.*, 2009). Sericin has also been identified as a potent antioxidant and photo-protective agent against ultraviolet B (UVB) irradiation in mouse skin model (Dash *et al.*, 2008). Sericin enhances the attachment and growth of fibroblasts (Tsubouchi *et al.*, 2005). Terada *et al.* (2002) found growth promotion in several human cell lines and mouse hybridomas when sericin was added to the culture media. Tsubouchi *et al.* (2002) reported wounds covered with sericin powder exhibited accelerated wound healing in dogs. Sericin was recommended as vehicle for DNA delivery in the gene therapy (Yanagihara *et al.*, 2006) and as insulin conjugate that would extend the hormone half-life in treated patients (Zhang *et al.*, 2006). The other proven applications include hernia repair, tissue wall reconstruction and organ support as bladder slings (Sehna and Sutherland, 2008), scaffolds for tissue engineering (MacIntosh *et al.*, 2006) and as controlled release drug delivery vehicles (Wang *et al.*, 2007; Hardy and Scheibel, 2009).

## CHAPTER THREE

### GENERAL MATERIALS AND METHODS

#### 3.1. Silkmoths and cocoon shells

Cocoon shells of the four African wild silk species were collected from four different ecosystems in Kenya namely; the coastal forest of Arabuko Sokoke (*A. mimosae* Biosduval), the semi-arid Mwingi district acacia forest (*G. postica* Walker), the arid and semi-arid West Pokot region (*E. bauhiniae* Guer) and the tropical rain forest of Kakamega (*A. panda* Biosduval) (Fig. 1a-d). *B. mori* cocoons (race ICIPE II) were obtained from the Commercial Insect Program of International Centre of Insect Physiology and Ecology (ICIPE) (Fig 1e).

#### 3.2. Cleaning of cocoon shells

*B. mori* cocoon shells were harvested seven days after the completion of spinning, and left in the sun for two days to kill the pupae. Wild silk cocoon shells were collected after the adult moth had emerged. All the cocoon shells were cut open by a sharp razor blade and dead pupae and/or remaining debris of the pupae were removed. The inside and surface of the cocoons were scrubbed to remove any impurities and other foreign materials such as leaves and branches. Stained and deformed cocoons shells were rejected.

### 3.3. Degumming of cocoon shells

Degumming (process of removing the gum (sericin) component of silk fibers usually through boiling with alkaline chemicals) solution was prepared by adding 10g  $\text{Na}_2\text{CO}_3$  (commonly known as Magadi soda) in a beaker with 1500ml of deionized water and stirred with a magnetic stirrer for 10 minutes at room temperature. Then the volume was then adjusted by adding distilled water to 2000ml in a volumetric flask. Cleaned cocoons were enclosed in wire mesh cages with a volume of  $717\text{cm}^3$  and boiled with the degumming solution for one hour for *B. mori*, 1.5 hours for *G. postica*, 3 hours for *A. mimosa* and *E. bauhiniae* and 5 hours for *A. panda*. Boiled cocoons were soaked in liquid detergent solution of 50ml/L of distilled water for 3 minutes and washed with hot and cold distilled water twice. Excess water was removed by filter paper.

### 3.4. Chemicals

All reagents used were of analytical grade. Deionized water (made by Elix Milipore Darmstadt®) was used throughout the experiment.

### 3.5. Data analysis

All percentage data were subjected to appropriate transformation procedures to stabilize the variance before the final statistical analysis. Means were analyzed using one-way and two-

way analysis of variance (ANOVA) with PROC ANOVA procedure (SAS Institute, 2010).

Least Significance Difference (LSD) tests ( $\alpha=0.05$ ) were used to separate means.



(a) *Argema mimosae*



(b) *Gonometa postica*



(c) *Epiphora bauhiniae*



(d) *Anaphe panda*



(e) *Bombyx mori*

Figure 1: Cocoon shells of the four African wild and *Bombyx mori* silkmoths

## CHAPTER FOUR

# MICROSTRUCTURES OF COCOON SHELLS AND DEGUMMED FIBERS

### 4.1. INTRODUCTION

Silk, from both domesticated and wild silkworms and spiders, represents a unique and important class of polymeric composite materials in nature providing a wide range of evolutionary and ecological functions with optimum microstructures and properties (Zhao *et al.*, 2005; Cheung *et al.*, 2008). Larvae of silkmths shoot out silk threads and form cocoon shells to enwrap themselves completely prior to metamorphosis. These cocoon shells are non-woven structures majorly composed of two proteins, fibroin and sericin. They exhibit remarkable variation in structure, property and composition which imposes direct influence on their adaptive functions. The functional significance of these proteinaceous structures includes crypsis, provision of barricade from predators, pathogens and parasitoids and assisting the pupae to complete their metamorphosis by improving thermal and/or moisture conditions (Lyon and Cartar, 1996). The multitude of variations in diet, breed and climate resulted in considerable diversity in the type and properties of the cocoons and fibers produced by silk producing insects of different origins and within the same species. Thus, species- specific fiber mechanical, chemical and physical properties reflect the ecology and behaviour of cocoon-spinning insects (Danks, 2004; Reddy and Yang, 2010a) and can

significantly influence the quality, quantity and efficiency of the reeling process in commercial varieties (Vasumathi *et al.*, 2004).

Studies have shown the existence of macro- and microscopic level structure and property variations among cocoon shells and fibers from mulberry and wild silkworms. Narumi *et al.* (1993) revealed the presence of a large number of voids in the cross sections of wild silk fibers in contrast to mulberry silk. The silk fibers from the wild silkmoths have many longitudinal striations on their surface and are porous which make them lighter than mulberry silk (Sen and Babu, 2004a). Wild silk fibers also consist of flattened, ribbon-like filaments of much greater diameter than mulberry silk (Das, 1992). Although the potential of African wild silkmoths for production of large cocoons with economic importance has been documented. However, the microscopic structures and properties of these fibers and cocoon shells have not yet been studied in detail. Comprehensive studies of such structures will lead to better understanding of the cocoon spinning behaviours of the silkworms and how silk fibers are arranged in the cocoon shells to suit their designed purposes. This information would be of immense value in the prudent evaluation of the potential of the African wild silk fibers and cocoon shells for commercial application and further investigation on the structure-property-function relations.



## **4.2. MATERIALS AND METHODS**

### **4.2.1. Surface and cross sectional study of cocoon shells**

Cocoon shell discs (5mm diameter) were pressed out of the middle section of the cocoons with a sharp hole-punch for external and internal cocoon surface studies. Cocoon shells were also cut into slices by using a sharp blade for cross sectional observation. Spines and hairs from *G. postica* and *A. panda* cocoons were collected using forceps. All samples were separately mounted onto copper stubs using double sided sticking tape and were then sputter-coated with gold for three minutes to minimise charging under the electron beam. The samples were then studied with SEM ((Jeol Neoscope, JCM-5000 (Nikon<sup>®</sup>, UK)) under an accelerating voltage of 10kV with a beam current of 0.1nA. Ten cocoons were pressed out five times at random locations with a sharp hole-punch and the thicknesses of the discs were measured using a digital micrometer (Mitutoyo, IP 65).

### **4.2.2. Longitudinal and cross-sectional study of degummed fibers**

Degummed fibers were placed in 70% ethanol for three days to remove remnant sericin and fatty materials and were then dried at room temperature. Longitudinal and cross sections were prepared by cutting fibers mounted in plastic tubes using a new razor blade. The slices were mounted onto copper stubs using double-sided sticking tape and were coated with gold on their cut surface to be observed by SEM.

#### 4.2.3. Fourier Transform Infrared Spectroscopy (FTIR) study

Three cocoon discs of each species were sampled three times on each side (inside and outside of the disc) and all the spectra were averaged. Spectra were acquired at  $4\text{cm}^{-1}$  resolution from  $7000$  to  $400\text{cm}^{-1}$  and average of 64 scans. All spectral operations were performed using OMNIC version 7.3 (Thermo Scientific, Madison, WI).

## 4.3. RESULTS

### 4.3.1. Surface and cross sections of cocoon shells

Being a typical protective structure, surfaces of cocoon shells exhibited extensive variation to meet the specific needs of a given species. *A. panda* and *G. postica* cocoon shells had dense white and brown hairs and spines, respectively embedded from the body of the larvae during spinning (Fig. 2a-c). The average diameter of *A. panda* hairs was 34 $\mu$ m and had thorny spines (6-8 $\mu$ m in diameter) arranged alternatively over the surface. *Gonometa* cocoons had short white hairs interwoven throughout the cocoon layers while the brown needles like spines with sharp buds on their surface were found attached to the outer cocoon surface (Fig 2b). The sharpness of the buds decreased towards the base of the spines (Fig. 2c).

*E. bauhiniae* cocoon shells had strong peduncle to attach on the twig of a plant. It was composed of highly cross-linked fibers embedded with mass of sericin gum (Fig. 3a and b). In the rest of the species, cocoons were sessile and directly attached along their full length to twigs and forked branches. The attachment surfaces for *A. mimosae* and *G. postica* were smooth and plastered with massive amount of gum (Fig. 4a and b). Unlike the other cocoon surfaces, the crystals in *G. postica* were found covered with the gum material at the attachment surface.

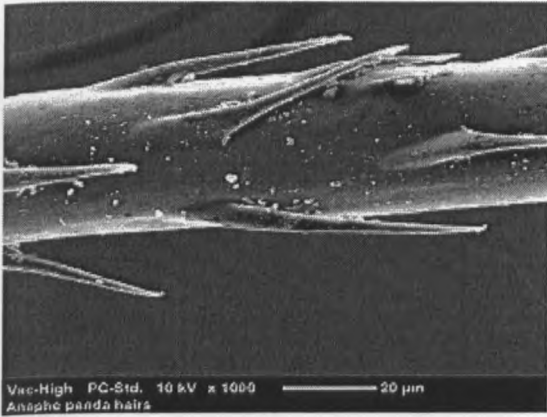
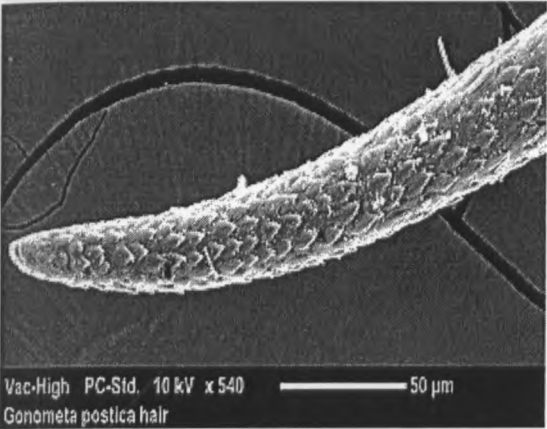
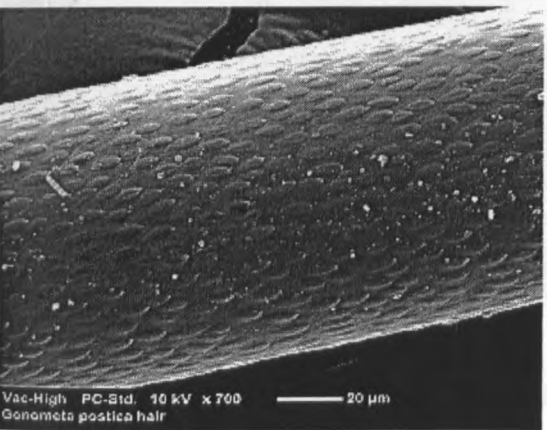
(a) *Anaphe panda* cocoon hair(b) *Gonometa postica* spines (tip)(c) *Gonometa postica* spines (base)

Figure 2: SEM micrographs of hairs and spines from the surfaces of *Anaphe panda* and *Gonometa postica* cocoon shells

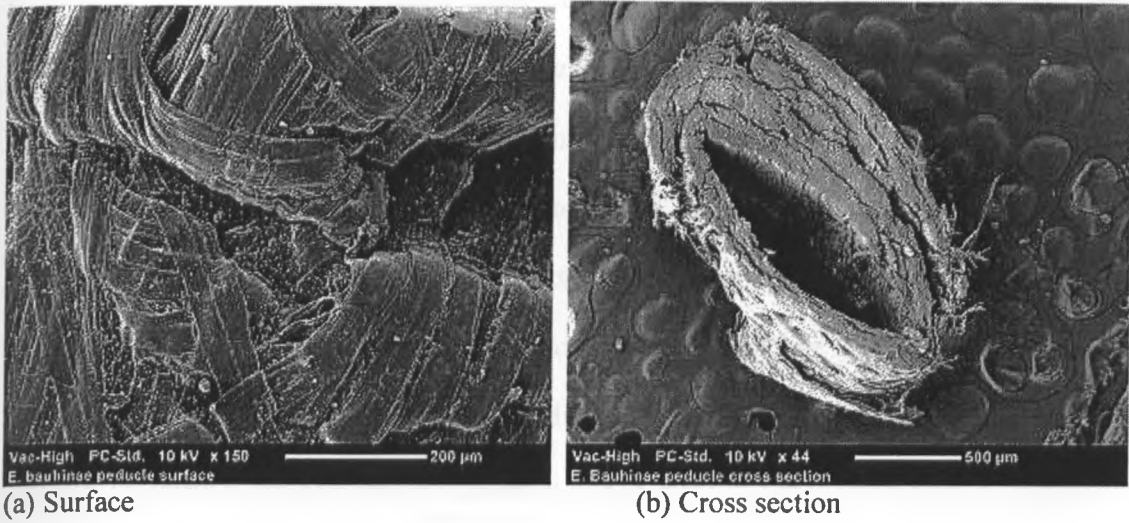


Figure 3: SEM micrographs of surface (a) and cross section (b) of *Epiphora bauhiniae* cocoon peduncle

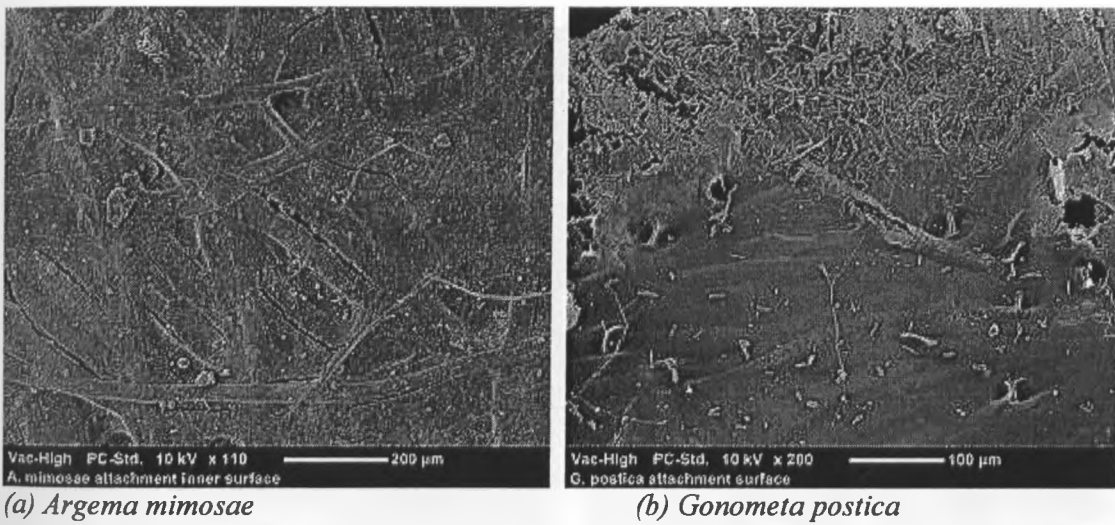


Figure 4: SEM micrographs of attachment surfaces of cocoon shells of *Argema mimosae* and *Gonometa postica*

*G. postica* and *E. bauhiniae* cocoon shells were covered with whitish rectangular and cubic shaped granular crystalline materials, respectively throughout the surface except areas of fiber intrusion and attachment surfaces for the former (Fig. 5a and b). FTIR spectra for the outer cocoon shell surface of *G. postica* showed the peaks at  $1312\text{cm}^{-1}$  and  $777\text{cm}^{-1}$  were attributed to Calcium Oxalate crystal monohydrate (Siga) (Fig. 6i). However, the FTIR spectra could not clearly identify *E. bauhiniae* crystals as calcium oxalate, which might be due to their smaller size and quantity or difference in the chemical composition of the crystals. *G. postica* cocoons had prominently higher level of the crystals than *E. bauhiniae*. *G. postica* had 110-130 $\mu\text{m}$  thick calcium oxalate crystal layer deposit. The inner surfaces of all the cocoon shells had no calcium oxalate crystal layers (Fig. 6ii).



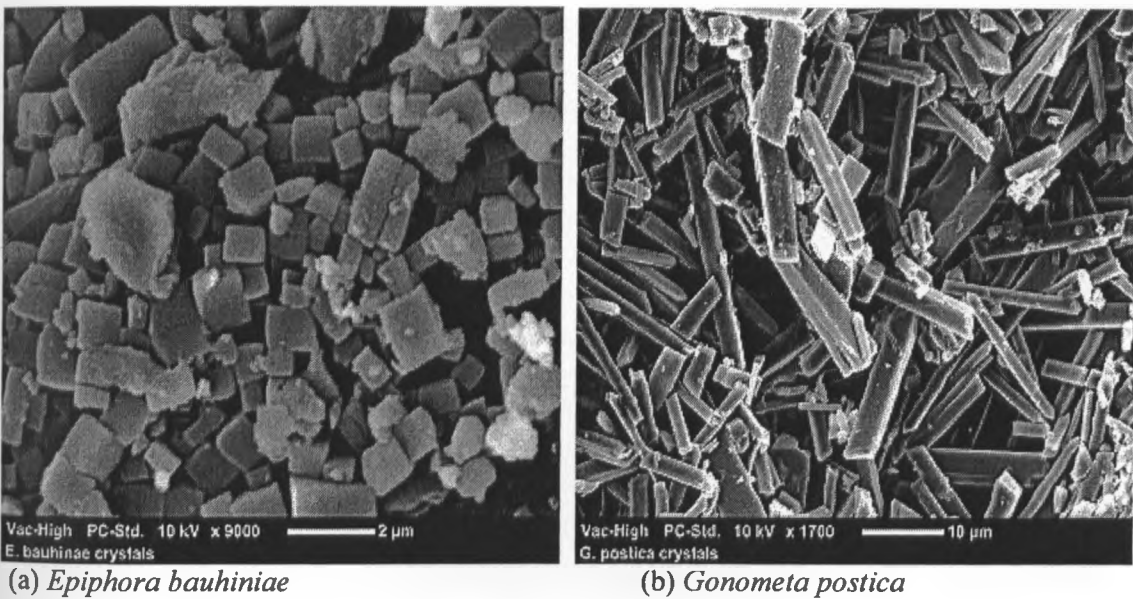


Figure 5: SEM micrographs of cocoon shell crystals of *Epiphora bauhiniae* and *Gonometa postica*

## (i) Outer surface

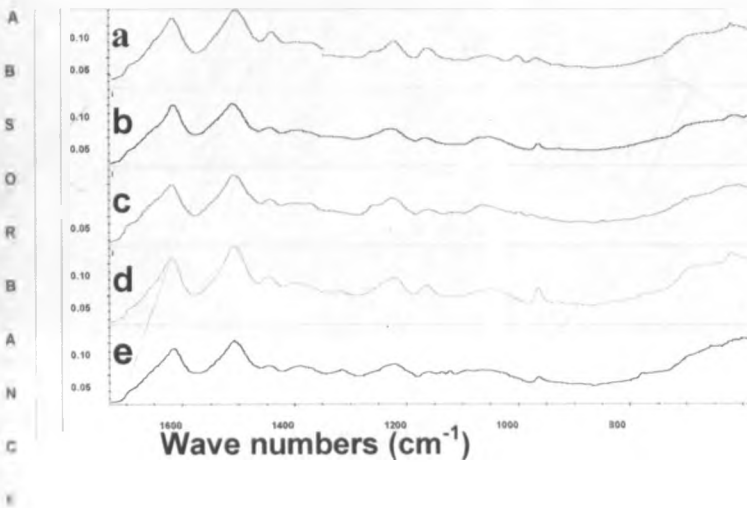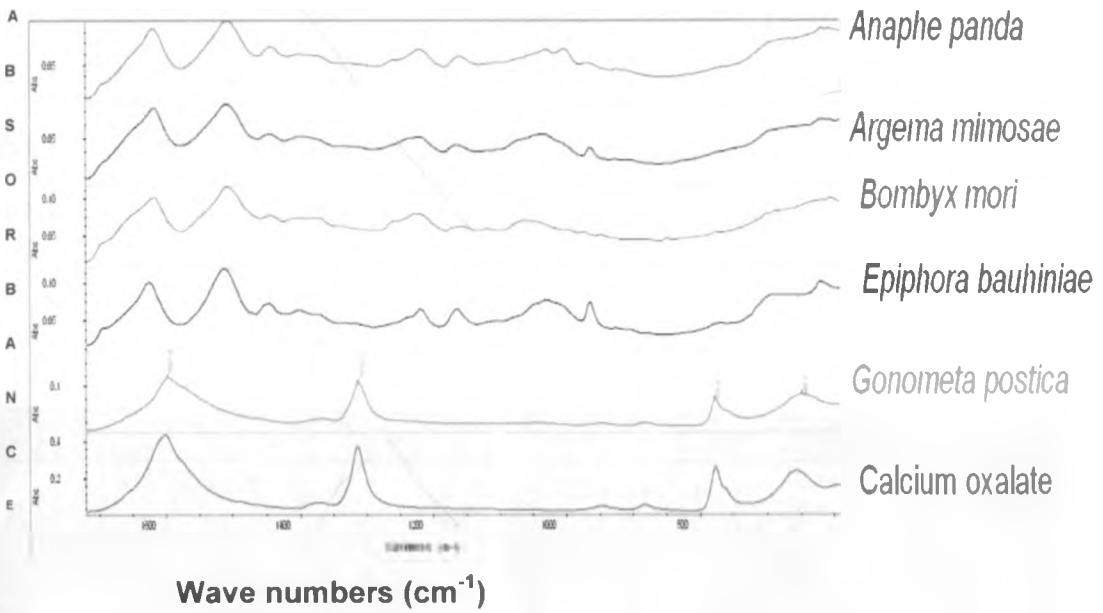

## (ii) Inner surface

Figure 6: FTIR spectroscopy of outer (i) and inner (ii) cocoon shell surfaces of (a) *Anaphe panda*, (b) *Argema mimosae*, (c) *Bombyx mori*, (d) *Epiphora bauhiniae*, (e) *Gonometa postica*, (f) Calcium oxalate hydrate

Unlike others, *A. mimosae* cocoons had considerable amount of holes formed as a ring like pattern (Fig. 7a and b). The width of the holes ranged between 448–512 $\mu\text{m}$ . However, the number, size, distribution and structure of the holes varied considerably with the position on the cocoon, the highest number being found at the emerging tips and near the attachment areas while larger holes were located at the middle section of the cocoons.

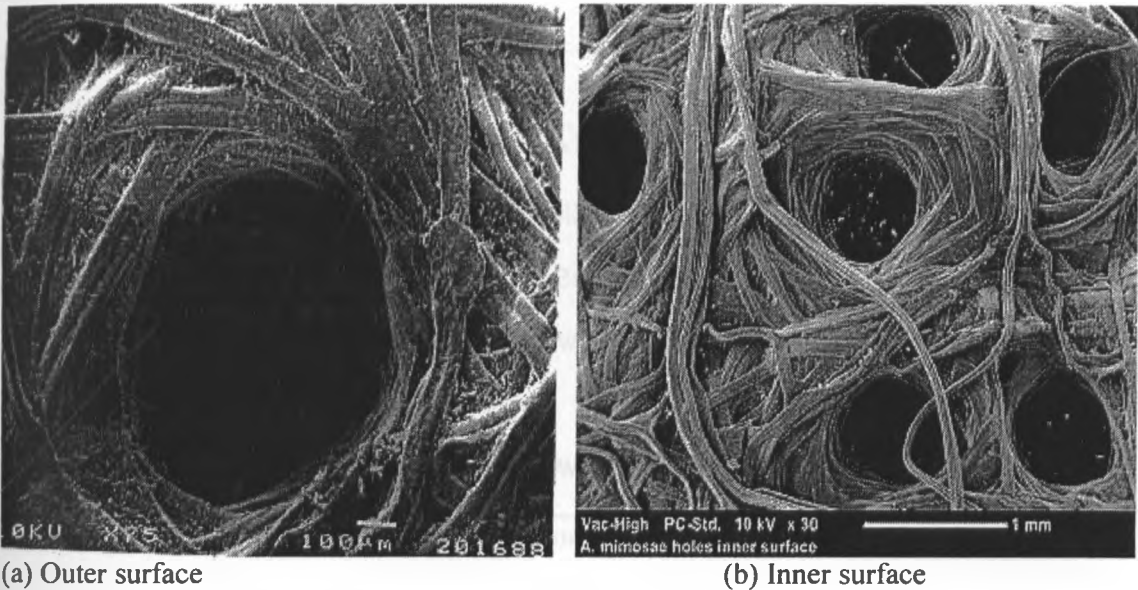


Figure 7: SEM micrographs of outer (a) and inner (b) surfaces of hole/perforations of *Argema mimosae* cocoon shells



The cocoon shells also showed variation in thickness and color. *G. postica* and *A. mimosae* had the largest and smallest cocoon shell thickness of 0.536 and 0.234mm, respectively (Table 2). Color of the cocoon shells also ranged from whitish grey to silver.

Table 2: Cocoon shells thickness of African wild and *Bombyx mori* silkmoths (Mean  $\pm$ SE)

Species	Thickness of cocoon shell (mm)	Cocoon colour	Host plant
<i>Bombyx mori</i>	0.409 $\pm$ 0.02 <sup>b</sup>	white	Mulberry plant ( <i>Morus alba</i> )
<i>Argema mimosae</i>	0.234 $\pm$ 0.01 <sup>d</sup>	silver	<i>Sclerocarya birrea</i>
<i>Anaphe panda</i>	0.408 $\pm$ 0.018 <sup>b</sup>	Brown/grey	<i>Bridelia micranth</i>
<i>Epiphora bauhiniae</i>	0.319 $\pm$ 0.08 <sup>c</sup>	White grey	<i>Zizyphus mucronata</i> , <i>Z. Mauritania</i>
<i>Gonometa postica</i>	0.536 $\pm$ 0.08 <sup>a</sup>	Whitish brown	Acacia species

Means followed by the same letter in a column are not statistically significant ( $P < 0.05$ ) using the least significant difference test (LSD)

African wild silkmoth cocoon shells were intact with highly cross-linked fibers and the space among the fiber strands and layers were smaller than *B. mori* cocoon shells granting better rigidity and compactness (Fig. 8a-e). The surface of the cocoons had fibers held together in

pairs by sericin gum, other secretions and impurities. The arrangement of the fibers in all the cocoon shells missed uniformity throughout the surface and showed great cross bindings, wrinkles and networking of twisting filaments in different shapes and forms. Such random twisting and bending of fibers imparted rough outer surface and rigidity for the cocoon shells. Fibers of *B. mori* and outer layer of *A. panda* cocoon shells appeared flossy and irregularly arranged. *G. postica*, *A. mimosae* and *E. bauhiniae* had smooth and uniformly plastered inner walls and the fibers were tightly bound together by the sericin gum making them appear more solid and intact (Fig. 8f-j).

All the cocoon shells were multilayered structures of fibers packaged in different fashion (Fig. 8k-o). However, depending on their cross sectional layers the cocoon shells were divided into two groups; single and double layered cocoons. The first group composed of *A. mimosae*, *G. postica* and *B. mori*, had single compact cocoon layer, while the second group composed of *E. bauhiniae* and *A. panda* had two hard layers (outer and inner most layers) joined by a middle flossy layer of silk fibers. Cocoon shells could also be divided in two groups depending on the presence of exit holes. *B. mori* and *G. postica* had closed cocoons while, *A. panda*, *E. bauhiniae* and *A. mimosae* had cocoon openings for the emerging adults left by the spinning larvae. The fiber layers of *B. mori* were arranged in more or less orderly but slack manner with wide space. Fibers of *A. mimosae* and *G. postica* were deeply encrusted and were slightly visible making the cocoons more compact and rigid. However, the thin outer layer of *A. panda* and *E. bauhiniae* were composed of loosely packed and visible fibers.

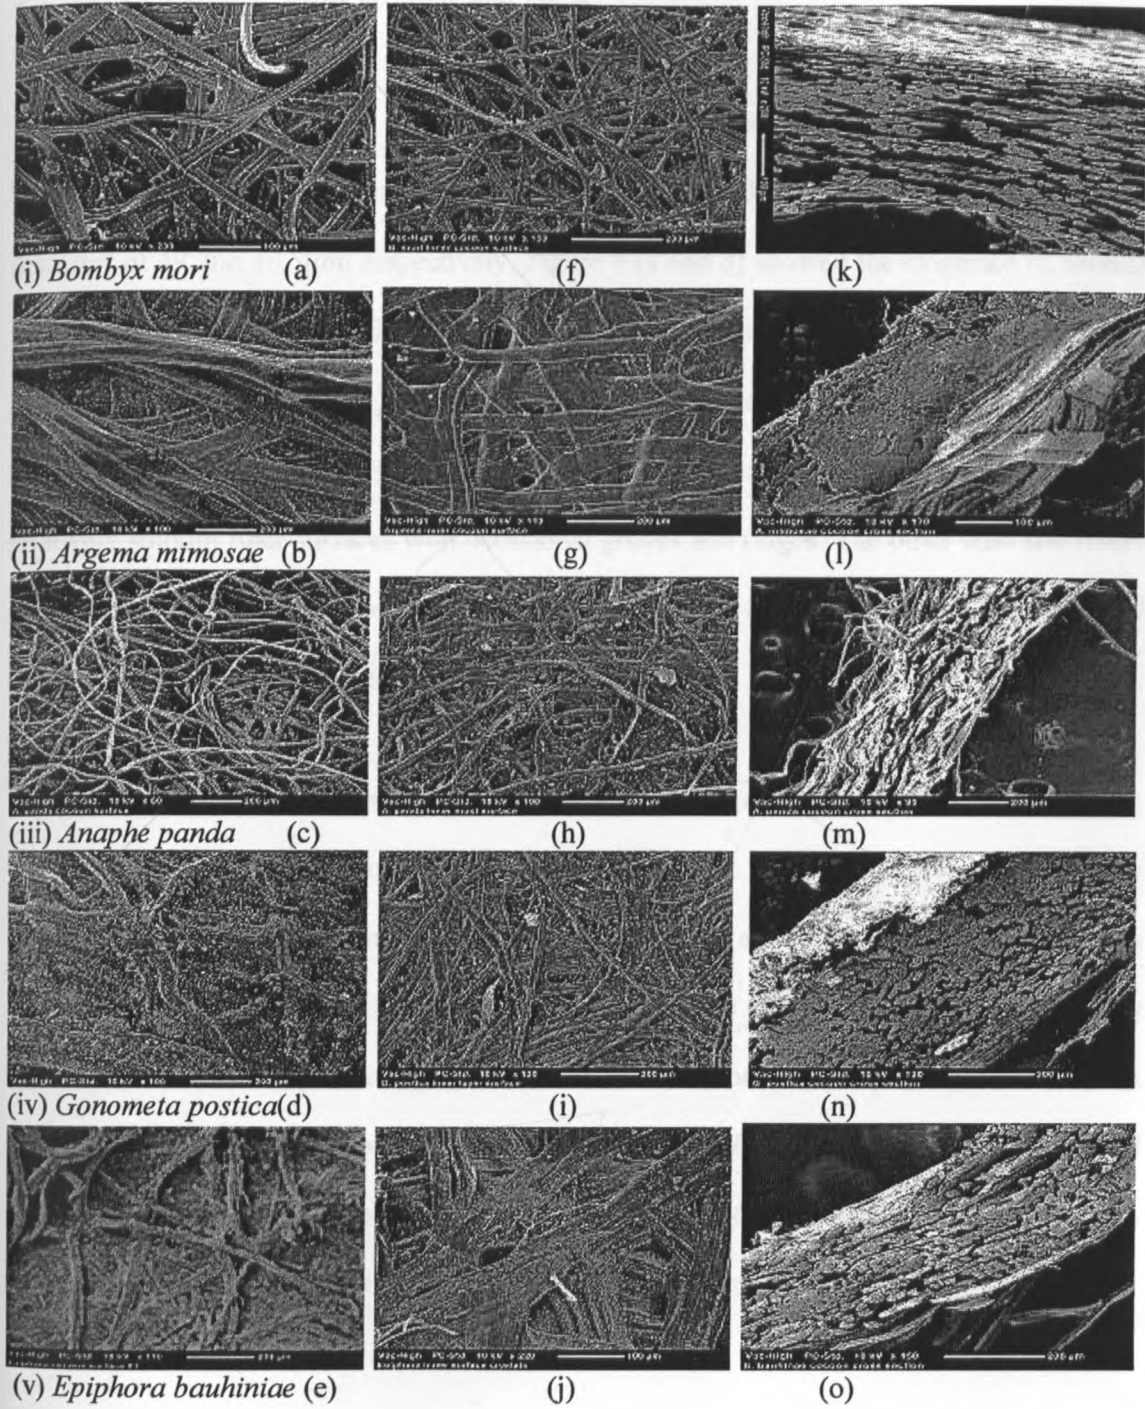


Figure 8: SEM micrographs of the outer (a-e), inner (f-j) surfaces and cross sections (k-o) of cocoon shells of African wild and *Bombyx mori*

#### 4.3.2. Fiber surfaces, cross sections and voids

After degumming, the bave were separated into individual brins and compact cocoons became flosses of fibers. *A. mimosae* and *B. mori* had the thickest and smallest brin with a diameter of 49 and 10.5 $\mu$ m, respectively. Figure 9 (a and d) showed the existence of several longitudinal striations and fibrillar structures in *A. mimosae* and *E. bauhiniae* fibers, respectively. The fibers of *A. panda* were unique from other species with their bamboo-like appearance with jointed nods at intervals (Fig. 9b). *G. postica* and *B. mori* fibers had relatively smooth fiber surfaces with occasional groves and ridges. The other wild silk fibers formed ribbon like twisting with uneven width along the fiber and their surfaces showed many irregularities such as fissure.

The silk fibers also showed tremendous variabilities, even between fibers of the same species, in shape and size of their cross sections. *A. mimosae* and *E. bauhiniae* fibers had mostly flattened, elongated and rectangular cross sections (Fig. 9 f and i), while fibers of *G. postica* and *B. mori* had globular and triangular cross sections. The silk filaments spun by *A. panda* had mostly crescent-shaped, triangular or round cross-sections. The fibers also showed great variability in the shape, size and number of voids present. *B. mori* silk fibers had fewer and smaller voids compared to the wild silk fibers. Some voids of *G. postica*, *A. mimosae* and *E. bauhiniae* were large enough to reveal the microfibrillar structures (Fig. 9k-o).

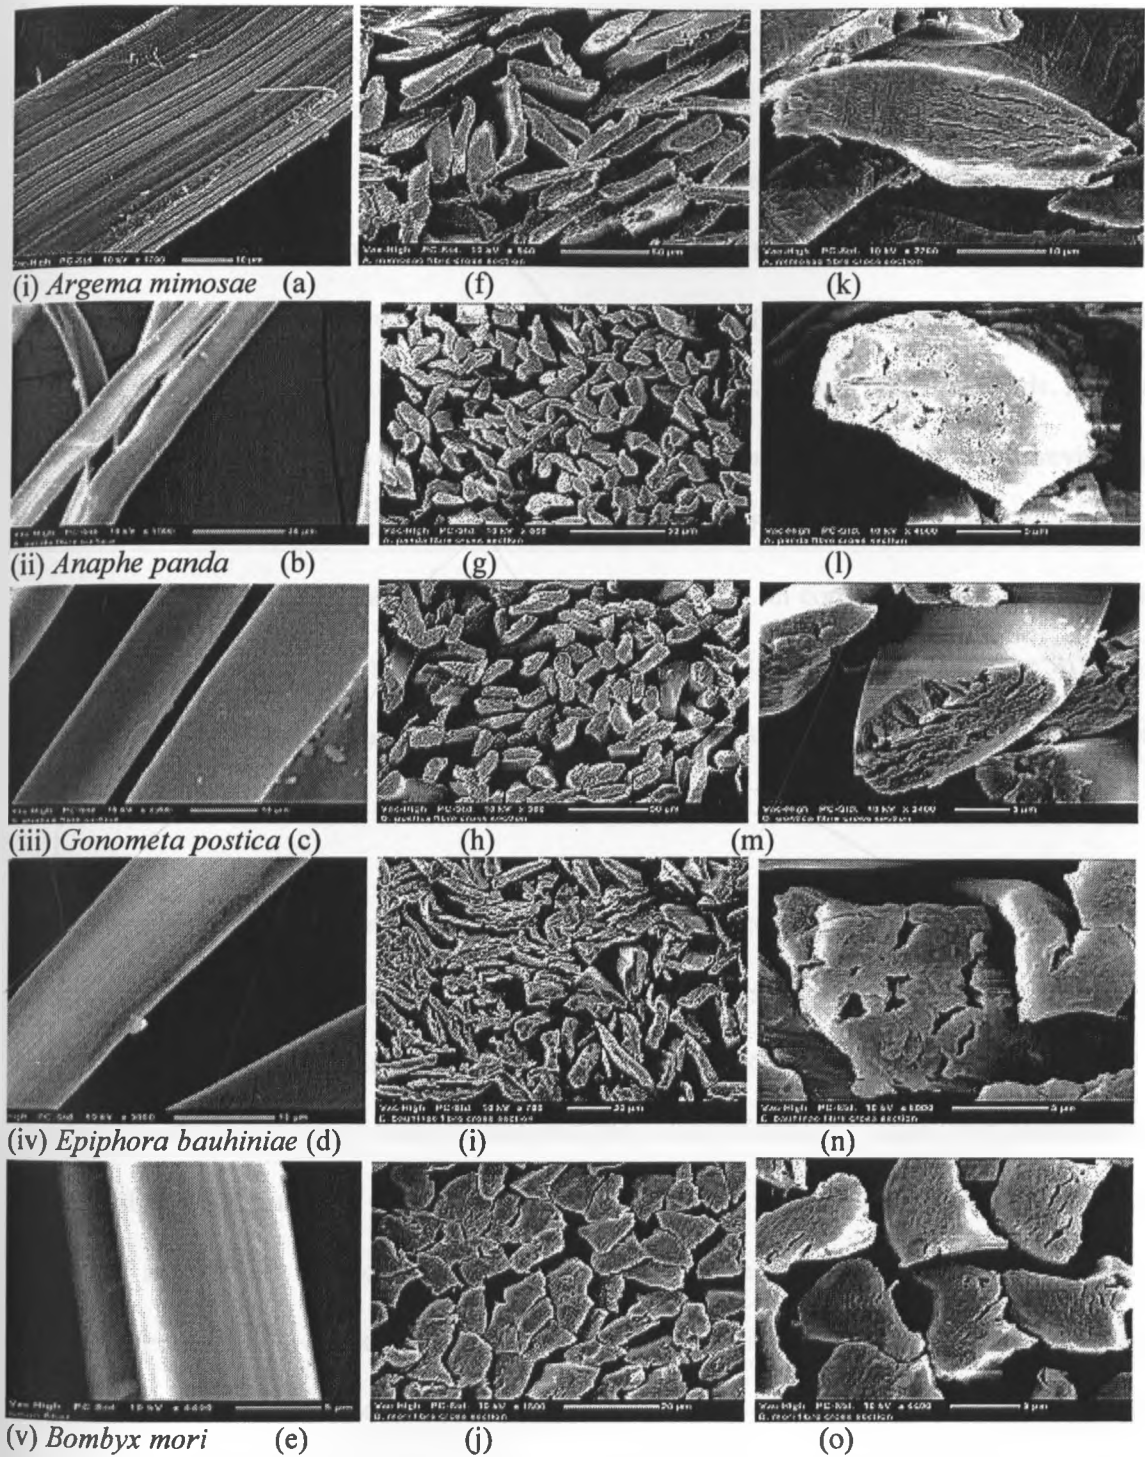


Figure 9: SEM micrographs of the surface (a-e), cross section (f-j) and macrovoids (k-o) of African wild and *Bombyx mori* silk fibers

#### 4.4. DISCUSSION

From the cocoon macro and microstructures, it is evident that silkworms larvae of each species ensure the pupae are well protected from natural enemies and environmental calamities by spinning hard and compact cocoon shells, which fits into their respective ecology. The needle-like spines and hairs in *G. postica* and *A. panda* are important structures for protecting the larvae and cocoons against natural enemies such as predating birds. Peigler (2004) also reported that the Genera *Gonometa* and *Borocera* embed what were previously protective body spines of the larvae in the cocoon surface hence protecting the developing chrysalis. These spines and hairs can sometimes be irritating on contact and along with other cocoon chemicals and dusts might be reasons for eye and skin irritations that make working with the cocoons of *Anaphe* and *Gonometa* uncomfortable, and causing workers' allergies in some cases.

The surface and interstices between fibers and layers of the cocoon shell of *G. postica* and *E. bauhiniae* cocoons are also packed with calcium oxalate crystals, defecated during spinning, which confer lower risk of bird attack and hardening of the cocoon shells (Veldtman, 2005). The functional adaptations of these crystals and the colour of cocoons range from camouflage to heat absorption or light transmission (Peigler, 1993). Thus, the crystals are perfect ecological adaptations for the arid and semi-arid environments where these two species are found. Other wild silk cocoons, such as *A. assama*, also showed the presence of calcium oxalate crystal deposits on their surface (Freddi *et al.*, 1994). The difference in size and shape of crystals suggests the role they might have on influencing the texture of the cocoon surface.

However, the extensive infiltration of these crystals between the silk fibers makes *Gonometa*, and apparently other wild silk cocoon shells, extremely hard and difficult to reel (Akai and Nagashima, 2003; Gheysens *et al.*, 2011).

The larvae of the wild silkmoths also utilised different mechanisms to ensure firm and secure attachment of the cocoons to a substrate before pupating. This helps the cocoons to avoid falling over to the ground and being taken away by wind and water, and to prevent attack from predators like birds. The silken petiole (peduncle) of *E. bauhiniae* varied in fiber arrangement and compactness from the cocoon shells indicating that there might also be a difference in the chemical composition. Such variations have been reported in *A. mylitta*, where the peduncle sericin has higher molecular weight and slight difference in amino acid composition than the cocoon shells (Dash *et al.*, 2006). The other wild silk cocoons were sessile; however, they have high sericin gum at the attachment surface, which confers strong binding to the attachment substrates. The cocoon shell holes of *A. mimosae* have adaptive significance by allowing fresh air exchange with inner cocoon atmosphere where the pupae reside. These holes provide great ecological adjustment mechanism against the humid and hot coastal rain forest climate (Arabuko Sokoke) for *A. mimosae*. Reddy and Yang (2010b) also reported *Copaxa multifenestrata* (Saturniidae) have perforated construction with considerable amounts of holes on the surface of the cocoons.

Wild silk cocoon shells exhibited cross-bindings and junction of filaments forming an intricate network and irregularly shaped structures with more cementing gum between the

filaments. Such structures of cocoon shells have also been reported in *A. mylitta* (Shamitha and Rao, 2006). *B. mori* shells are more loosely arranged and less compact than their wild counterparts. Such loose arrangement together with comparatively uncomplicated sericin removal procedure might be an added advantage to its success as a major textile fiber by allowing easy reeling with minimum breaking percentage. The wrinkles on outer cocoon surfaces might have been formed due to non-uniform shrinking during drying (Zhao *et al.*, 2005). The multilayered and porous structure of the cocoon shells serves as a mechanical barrier and offers a better energy absorbing property due to the wave impedance matching of different plies (Tsai and Prakash, 2005). The dimension of the fiber spaces (compactness) varied with the species mainly due to the spinning behaviour and amount of silk materials (sericin and fibroin) available to construct the cocoons. These porous structures can also be viewed as a trade-off between optimising the use of a limited amount of silk materials from the silk gland and construction of efficiently large cocoon structures, which can withstand possible attacks from the outside. Tagawa and Sato (2009) also emphasised the balance between economy and robustness of cocoons is important for cocoon-spinning insects.

The variability in fiber size, surface and cross sectional structures might be due to wide variation in cocoon size (Komatsu, 1980). Mbahin (2008) and Nel (2007) reported the size of *A. panda* and *G. postica* silk fiber is about 20 and 15-25 $\mu\text{m}$ , respectively. The cross sectional view of the brins appeared largely as elongated rectangular, wedge-shaped, triangular, or globular in wild silk fibers. This is in agreement with reports for other wild silk species (Buschle-Diller, 2010; Zhang *et al.*, 2010b). Freddi *et al.* (1993) reported that silk threads



spun by *G. rufobrunnae* are variable in cross-sectional dimension and can be round, triangular or even flat and ribbon like. Fibers of *A. mimosae* and *E. bauhiniae* exhibited a distinctly flattened surface with longitudinal micro fibrils similar to *A. assama* silk fibers (Freddi *et al.*, 1994). Thus, it can be concluded that these fibers are made up of bundles of microfibrils oriented along the fiber axis. The larval body movement, speed of spinning, body twisting and bending during the cocoon forming process and elasticity of the fibers when emerging from the spinnerets might force the fibers to acquire different shapes and sizes. The cross-markings and twisting of the wild silk fibers might also be caused by the overlapping of one fiber on the other before the substance of the fiber has completely hardened, in consequence of which such areas are flattened out. The resulting cross sectional size and shape of fibers have been reported to have a direct relationship with the yarn's lustre, friction and mechanical properties (Narumi and Kobayashi, 1995).

The cocoon filaments of various wild silkmoth species were also found to have voids that were absent in *B. mori* silk fibers (Narumi *et al.*, 1993; Lin *et al.*, 1993). However, in this study, voids were observed in *B. mori* fibers. Narumi *et al.* (1992) and Mondal *et al.* (2007b) also reported the rare voids in cocoon filaments of *B. mori* and *B. mandarina*. Silk fibers are also known to have micro-voids (8–11nm) which differ in their number, size and distribution between species with larger volume fraction and number in *B. mori* than tussah silk (Kawahara and Shioya, 1999). Akai *et al.* (1991) revealed that the voids in *Antherea* originate from the droplets in liquid silk material present in the posterior silk gland and stretched out with the protein masses during spinning. Akai and Nagashima (1999) noted voids in *A. panda*

fibers are traces of the rhythmical movement of liquid silk, which reflects the spinning behaviour and speed. African wild silk fibers have larger and numerous voids which could be an advantage for chemical modifications as these voids play a significant role in the penetration of water and other chemicals to the fiber resulting in marked increase in cross section.

## CHAPTER FIVE

### AMINO ACID COMPOSITION OF SILK FIBERS

#### 5.1. INTRODUCTION

Silk represent a Family of high-quality animal fibers composed of amino acids which vary significantly in relative composition, structure, and functional properties (Prasong *et al.*, 2009). It is majorly composed of two proteins; fibroin and sericin, together with small quantities of other proteins, waxes, fats, salts, and ash (Schoeser, 2007). Although both fibroin and sericin consist of proteins, they strongly differ in the related building blocks (amino acids). Fibroin is a single protein with roughly 76% of its amino acids having non-polar side chains, the main ones being glycine (43.7%) and alanine (28.8%). On the other hand, sericin is a mixture of proteins and contains a large number of amino acids with hydroxyl groups (Arami *et al.*, 2007). The main amino acids are serine (33.4%), aspartic acid (16.7%), glycine (13.5%), and threonine (9.7%) (Chopra and Gulrajani, 1994). The amino acid sequences of these major silk proteins have been determined for a number of silk types and species, revealing extensive variation. This variation in sequence is hypothesized to confer different material properties in different silks (Swanson *et al.*, 2006).

Common to insect silks are high levels of glycine, alanine, and serine. Together, these three small amino acids take up to about 80 to 85% of the total amino acids in *B. mori* and *A. pernyi* silks. Such a high concentration of these amino acids having small and simple side

groups in silk fibroins permits the arrangement of polypeptide molecules into an orderly and crystalline manner and is responsible for the desirable mechanical, physical and chemical properties of the silk fibers (Kaplan *et al.*, 1994). Glycine and alanine represent 50% of the total number of amino acids in silk, although large differences have been found in the relative frequency of each amino acid (Pérez-Rigueiro *et al.*, 2001).

Except for few dominant amino acid residues, wide variations in composition have been observed in silks of different origin (Prasong *et al.*, 2009). Such variation can further be influenced by the dietary intake of the insect and the environmental conditions during the spinning process (Shao and Vollrath, 2002). Warwicker (1960) showed that silks produced by over 70 species in the classes Insecta and Arachnida have similar crystalline structure, basic chain axis and hydrogen bonding dimensions, while differences arise in the inter-sheet spacing due to the different amino acid compositions and sequences of the fibroins. Some investigators have proposed that the diverse amino acid composition of silks may be the result of relaxed selection on proteins used outside of a cellular environment (Lucas and Rudall, 1968). It has also been argued that amino acid composition of silks evolved in response to selection for specific functional properties such as prey capture, egg and pupae protection (Craig, 1997; Gosline *et al.*, 1984). Based on such structural considerations, attempts have been made to relate the chemical constitution of silk fibers to their outstanding mechanical, physical and chemical properties. Lucas *et al.* (1955) showed that the amino acid composition of mulberry and non-mulberry silk varieties is different and influenced the physical properties. However, there is insufficient information to make a definitive

correlation between chemical composition and structural properties for the African wild silk fibers. Thus, the composition and properties of these silk fibers in terms of basic amino acids is still uncertain.

## **5.2. MATERIALS AND METHODS**

### **5.2.1. Sample preparation**

About 100g of cocoons were cut in pieces and gently washed in 100ml of warm water at 65°C for three minutes. To eliminate the pigments and inorganic compounds, the pieces were immersed into 70% methanol at 25°C for ten days. There after cocoons were degummed with standard procedure for each species and rinsed by warm deionized water repeatedly in order to remove remnant sericin.

### **5.2.2. Hydrolysis of silk**

Approximately 1mg of silk was lyophilized and crushed using liquid nitrogen, dried in an oven to remove moisture at 105°C before acid hydrolysis. Hydrochloric acid (6N) (2ml) containing 1% of phenol was added to the dry silk in a vial, sealed under nitrogen and heated in an oven at 110°C for 24 hours. The hydrolysate was then centrifuged at 13000 g for five minutes and filtered through glass wool. The supernatant was diluted 20 times with 50% methanol before analysis.

### 5.2.3. Amino acid analysis

Multiple analyses were carried out on HPLC (Prominence LGE-UV Low Pressure Gradient HPLC system-Shimadzu, Japan: Column Gemini C4, Length 250mm, ID 4.6mm, Run time 25minutes) under the following gradient system (Table 3). The resulting peaks were identified by running authentic standards of the amino acid.

Table 3: Sample running conditions for HPLC amino acid analysis of African wild and *Bombyx mori* silk fibroins

Time(min)	Module	action	value	Solvent
0.01	Pumps	B.Conc	5	Solvent A: dH <sub>2</sub> O (5% HCOOH), Solvent B: Methanol
3	Pumps	B.Conc	10	
13	Pumps	B.Conc	30	
25	Controller	Stop		

### 5.3. RESULTS AND DISCUSSION

The percentage composition of the major amino acids in the wild and *B. mori* silk fibroins was presented in Table 4. The results showed that there were variations in quantities of the amino acids present in the fibroins, although all the fibroins examined so far were Generally characterized by the presence of high proportions of the three simple amino acids, glycine, alanine, and serine. The three amino acids represented about 71-74 and 82% of the total amino acids present in wild and *B. mori* silk fibroins, respectively. In all the wild species, alanine was the dominant amino acid (34-36%) followed by glycine and serine. However, in *B. mori*, glycine was predominant (43%). Other amino acids including glutamic acid, asparatic acid, valine and methionine were also found to be incorporated in various amounts depending on the origin of the fibroin. Though the content of alanine was higher for the African wild fibroins compared to *B. mori*, it was lower than other non-mulberry silk fibroins particularly for Muga (44%) (Freddi *et al.*, 1994). However, the proportion reported here was comparable with eri, tasar and muga (34-36%) as reported in Sen and Babu (2004a). However, alanine content as high as 52-59% has been reported for the outer layer of *Anaphe reticulate* and the sum of alanine and glycine content accounted for more than 90% of the total amino acids (Perepelkin, 2007; Tanaka *et al.*, 2008). The composition of some of the amino acids such as tryptophan, cystine, asparagine, glutamine and isoleucine could not be included in this study because their analysis and degradation products were hampered by their instability in oxidative or strongly acidic media, deamination, slow cleavage and/or light.



Table 4: Percentage composition of major amino acids in the African wild and *Bombyx mori* silk fibroins

Amino acids	<i>Argema mimosae</i>	<i>Epiphora bauhiniae</i>	<i>Anaphe panda</i>	<i>Gonometa postica</i>	<i>Bombyx mori</i>
Aspartic acid	4.34	4.19	4.78	4.68	1.52
Glutamic acid	1.31	1.11	1.12	1.02	1.73
Serine	8.85	9.65	8.17	8.56	10.34
Glycine	27.84	27.64	29.62	29.51	43.45
Threonine	0.23	0.03	0.04	0.02	0.82
Alanine	34.72	34.52	36.53	36.43	28.04
valine	1.42	1.22	1.23	1.13	2.57
Methionine	0.28	0.25	0.26	0.16	0.11
leucine	0.68	0.48	0.49	0.39	0.75
lysine	0.19	0.12	0.13	0.03	0.25

Table 5 showed the ratios of different amino acids categorized into groups which have significant correlation with the properties of the fibroins. The ratio of bulky to non-bulky amino acids was higher for wild silk fibroins ranging from 0.10 to 0.12. Similarly, the ratio of hydrophilic to hydrophobic was also higher for all wild silks analysed (0.22-0.24) than *B. mori* (0.19). In General, the large portion of the *B. mori* fibroin was made up of simple amino acids such as glycine and alanine. The glycine/alanine ratio, therefore, was higher for *B. mori* (1.5) than wild fibroins (0.8). Freddi *et al.* (1993) reported *Gonometa rufobrunnae* silk fibroin contains a large amount of glycine and alanine, with glycine/alanine ratio of 1.5 similar to that of *B. mori* silk fibroin. However, all the wild silk fibroins in this study had similar glycine/alanine ratios. These two amino acids are known to form the major part of the crystalline structure of the fibroin and thus definitely lead to a different crystallographic arrangement. Simmons *et al.* (1996) reported that the tensile strength of silk is attributed to the crystalline regions, whereas elasticity is believed to reside in the amorphous domains.

No General correlation could be made between the biological classification of the wild silk moths and the amino acid composition of the fibroin they produce. Some fibroins from biologically unrelated species (*A. panda* and *G. postica*) have closely similar amino acid compositions. *A. mimosae* and *E. bauhine* (Saturniidae) exhibited fair similarity at least in the three major amino acids. Some authors argue that such diversity and evolution of silk is related to selection for specific purpose (Craig, 1997) which could also be true for the African wild silkmooths as they produce similar type of silks for common purpose during a limited period in their lives. The observed heterogeneity in composition might rely on the selective

protein expression and host plants used among the species. Craig *et al.* (1999) also suggested that differences in dietary energy versus dietary diversity may be important to silk expression in herbivores lepidopterans and the high alanine, serine and glycine composition of silks produced by the larvae might reflect their predictable and energy rich diet.

Table 5: Various Amino Acid Ratios

Ratio <sup>a</sup>	<i>Bombyx mori</i>	<i>Gonometa postica</i>	<i>Anaphe panda</i>	<i>Argema mimosae</i>	<i>Epiphora bauhiniae</i>
Hydrophilic/hydrophobic	0.19	0.21	0.20	0.23	0.22
Bulky/non-bulky side groups	0.08	0.10	0.11	0.11	0.11
Glycine/alanine	1.54	0.81	0.81	0.80	0.80

**\*Hydrophilic amino acids:** serine, threonine, aspartic acid, glutamic acid, tyrosine, arginine, lysine, histidine

**Hydrophobic amino acids:** glycine, alanine, cystine, proline, tryptophan, valine, isoleucine, phenylalanine, methionine, tryptophan, leucine

**Amino acids with bulky side groups:** aspartic acid; glutamic acid, tyrosine, phenylalanine, leucine, isoleucine, valine, arginine, cystine, methionine, lysine, tryptophan

**Amino acids with non-bulky side groups:** glycine, alanine, serine, threonine, proline, histidine

## CHAPTER SIX

# WEIGHT LOSS AND MOISTURE REGAIN OF COCOON SHELLS AND DEGUMMED FIBERS

### 6.1. INTRODUCTION

Silks are natural polymers, which have been gaining wide use in variety of applications such as degradable biomaterials, biomedical and functional bio-membrane materials and fibers besides their traditional use as a textile raw material (Zhang, 2002; Mondal *et al.*, 2007a, Wilaiwan *et al.*, 2010). The use of such silks can be justified both by the combination of mechanical properties, non-toxicity, biocompatibility and biodegradability depending on their origin and treatment.

Moisture regain is the percentage of moisture that a dry fiber will absorb from air under standard conditions of temperature and moisture (Hollen and Saddler, 1973). Specifically, absorbed moisture is likely to determine the mechanical and physical properties of both the sericin 'gum' coating and the integral structural proteins of the silks (Fut *et al.*, 2009). Some silks can indeed be hygroscopic with a moisture regain of 11% at 65% relative humidity (RH) and 27°C (Ranganathaian, 2003; Sonthisombat and Speakman, 2004) which is larger than many other commercial fibers and more in line with wool (Salamone, 1999). This interaction of moisture and fiber has technical as well as commercial consequences. For example, in *B. mori* silk, the absorption of water causes 1.6% fiber swelling in the longitudinal crosswise

(Schoeser, 2007). This apparently small degree of swelling can influence the rate of heat and moisture vapour transfer through the textile fiber (Fuzek, 1985). Moreover, the weight change resulting from moisture absorption can affect the commercial weight of the fibers as well as affecting properties such as dyeing, finishing and apparent comfort of the product (Salamone, 1999).

However, most silk contains not only the fiber matrix protein but in addition, have a coating of sericin or similar compounds. This sericin component of the composite silk fiber (typically of two fiber brins held together into the bave by the sericinaceous 'gum'), is usually expressed as weight loss and is an important additional factor affecting the quality of a silk (Vishuprasad, 2004). The weight loss from a raw silk filament depends on the water solubility and higher alkali sensitivity of the sericin as compared to the fibroin (Choundhury, 2006). Quantity and nature of sericin are fundamental characteristics in conferring distinctive traits to the cocoon (Sadv *et al.*, 1987). Sericin coating has important biological properties such as oxidation and UV resistance as well as anti-bacterial and moisture control (Mondal *et al.*, 2007b). However, the sericin coating also gives a callous and stiff feeling to the fiber and hides the rich luster and whiteness of the silk brins in addition to preventing the penetration of dye (Arami *et al.*, 2007). These necessitate its removal by process of boiling (degumming) to obtain an ideal fiber for the textile industry and any other specific applications. Because of these effects, understanding the amount of sericin present in silk bave as wells as their water absorption properties of fibers and cocoon shells has considerable technical and economic implications for a silk as a commercial proposition.

## 6.2. MATERIALS AND METHODS

### 6.2.1. Determination of weight loss from cocoon shells and cocoon shell layers

Cleaned cocoon shells (20g) of all the wild silkmoths and cocoon shell layers of *A. panda* and *E. bauhiniae* were used. These two species were selected because of the clear distinction in the physical structure of the three shell layers in their cocoons (double cocoons); a leathery outer envelope, a loose and flossy intermediate layer and thick walled and rigid inner layer. These layers were designated as outer, middle and inner, respectively and were separated manually. All cocoon shells and shell layers were degummed separately. Boiled cocoons and layers were soaked in liquid detergent solution of 50ml/L of distilled water for 3 minutes and washed with hot and cold distilled water twice. Excess water was removed by filter paper and cocoon filaments were dried for 24 hours in oven at 110°C. Dried fibers were weighed using sensitive balance and the quantity of sericin (gum) removed from the cocoon shells and shell layers, expressed in percentage, was obtained using following equation (Nakpathom *et al.*, 2009):

$$\text{Weight loss(\%)} = \frac{W_i - W_f}{W_i} \times 100$$

Where,  $W_i$  - mass of fibers before degumming (g) and

$W_f$  - mass of fibers after degumming (g)

### 6.2.2. Determination of moisture regain of cocoon shells, degummed fibers and cocoon shell layers

Moisture regain was determined by the oven drying procedure. Cocoon shells, shell layers and degummed fibers were placed in an oven at 110°C for 24 hours for uniform drying. Oven-dried samples (20g) were placed at laboratory bench for 72 hours at room conditions (23 ± 2°C and 71 ± 3% RH). Samples were then weighed using sensitive balance and the moisture regain percentage was obtained using the formula by (Nawaz *et al.*, 2002):

$$\text{MoistureRegain(\%)} = \frac{W_f - W_i}{W_i} \times 100$$

Where,  $W_i$  = weight of oven dried sample (g) and

$W_f$  = final weight of sample (g)

All the experiments were replicated four times. Percentage data was log transformed to bring the data to normal distribution. One-way ANOVA was used to analyze the moisture regain and weight loss of cocoons, layers and degummed fibers with PROC ANOVA procedure (SAS Institute, 2010). LSD test ( $\alpha=0.05$ ) was used to separate the means.

## 6.3. RESULTS

### 6.3.1. Weight loss and moisture regain of cocoon shells and degummed fibers

The effect of degumming of four African wild and *B. mori* silk cocoons shells on percentage weight loss and moisture regain was presented in Table 6. There was a highly significant difference ( $P > 0.05$ ) in weight loss between the cocoon shells. *G. postica* and *E. bauhiniae* cocoons had the highest and lowest weight losses (57 and 23%, respectively). *B. mori* and *A. mimosae* cocoons had comparable weight losses (29 and 31%, respectively) which were marginally higher than *A. panda* (26%). The SEM micrographs revealed that the fibers were covered with different quantities of sericin gum after the degumming treatment indicating that all the sericin layer was not removed from the fiber matrix (Fig. 10).

There were also significant differences ( $P > 0.05$ ) in the moisture regain percentage between cocoon shells and degummed fibers. *A. mimosae* and *E. bauhiniae* cocoon shells had the highest and lowest moisture regain percentages (9 and 5.6%, respectively). *B. mori* and *A. panda* cocoons gained marginally higher (statistically non-significant ( $P < 0.05$ ) moisture (7.9 and 8.0%, respectively) than *G. postica* cocoon shells (7.1%) (Table 6). In contrast to the cocoon shells, the moisture regain of degummed wild silk fibers was not significantly different among species with *E. bauhiniae*, *G. postica* and *A. panda* gaining 10, 9.9 and 9.9%, respectively. However, *B. mori* had the lowest value (8.5%) which was significantly different ( $P > 0.05$ ) from the other wild fibers.



Table 6: Percentage weight loss and moisture regain of African wild and *Bombyx mori* cocoon shells and degummed fibers (Mean  $\pm$  SE)

Species	Weight loss (%)	Moisture regain (%)	
		Cocoon shells	Degummed fibers
<i>Bombyx mori</i>	29.35 $\pm$ 0.18 <sup>bc</sup>	7.93 $\pm$ 0.35 <sup>ab</sup>	8.53 $\pm$ 0.32 <sup>b</sup>
<i>Gonometa postica</i>	56.84 $\pm$ 0.32 <sup>a</sup>	7.11 $\pm$ 0.53 <sup>b</sup>	9.95 $\pm$ 0.46 <sup>a</sup>
<i>Epiphora bauhiniae</i>	23.19 $\pm$ 0.45 <sup>d</sup>	5.64 $\pm$ 0.62 <sup>c</sup>	10.42 $\pm$ 0.34 <sup>a</sup>
<i>Argema mimosae</i>	31.39 $\pm$ 0.97 <sup>b</sup>	9.05 $\pm$ 0.52 <sup>a</sup>	9.75 $\pm$ 0.39 <sup>a</sup>
<i>Anaphe panda</i>	25.55 $\pm$ 3.63 <sup>cd</sup>	8.02 $\pm$ 0.35 <sup>ab</sup>	9.91 $\pm$ 0.22 <sup>a</sup>

Means followed by the same letter in a column are not statistically significant ( $P < 0.05$ )

using the least significant difference test (LSD)

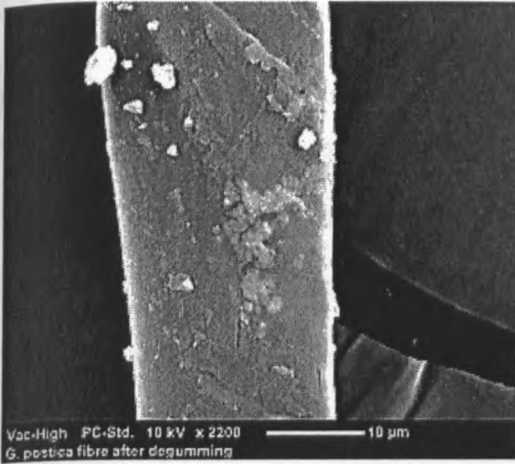
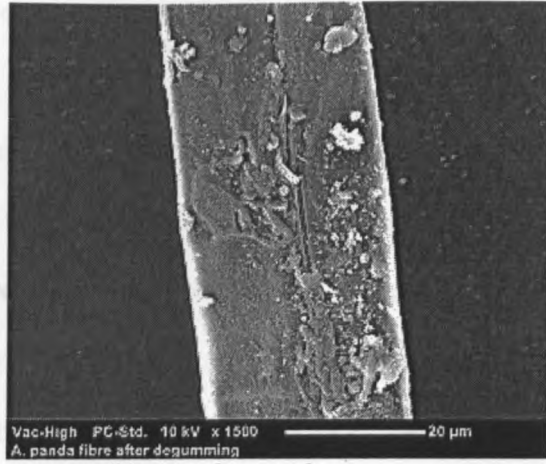
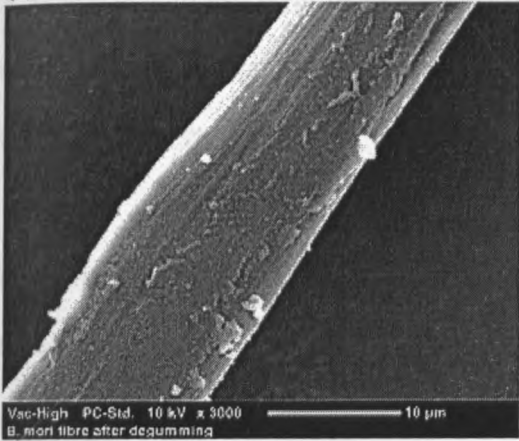
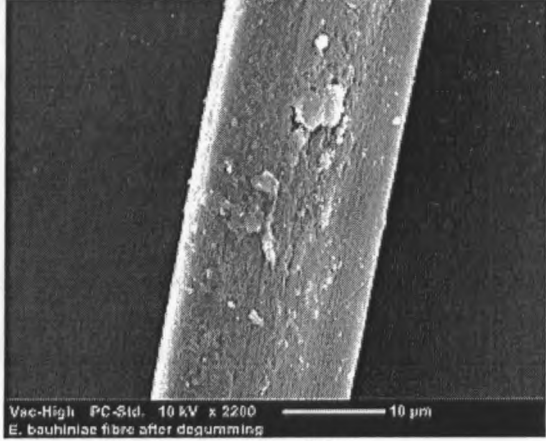
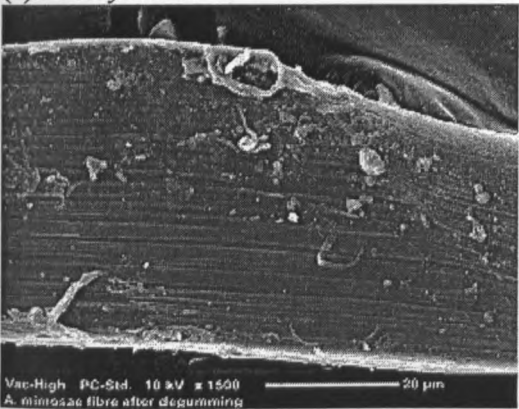
(a) *Gonometa postica*(b) *Anaphe panda*(c) *Bombyx mori*(d) *Epiphora bauhiniae*(f) *Argema mimosae*

Figure 10: SEM micrographs of remnant sericin coating on African wild and *Bombyx mori* fibers after degumming

### 6.3.2. Moisture regain and weight loss of cocoon shell layers

Moisture regain of layers of *E. bauhiniae* and *A. panda* cocoon shells was shown in (Table 7). There was significant difference ( $P > 0.05$ ) in moisture regain among the cocoon shell layers of both species. The inner hard layers had the highest regain (6.8 and 8.6% for *E. bauhiniae* and *A. panda*, respectively). However, there was no significant difference ( $P < 0.05$ ) between the regain percentages of degummed shell layer fibers of *E. bauhiniae* while, *A. panda* degummed layer fibers showed significant difference ( $P > 0.05$ ) with the inner layer regaining more moisture (9.4%). The moisture regain progressively increased towards the inner layer for *A. panda*.

However, there was a highly significant difference ( $P > 0.05$ ) in weight loss percentage from the cocoon shells in both species (Fig. 11). The outer skin like layers had the highest weight losses of 30.5 and 44.6% for *E. bauhiniae* and *A. panda*, respectively and the weight loss significantly decreased to the inner layer in *E. bauhiniae*.

Table 7: Percentage moisture regain of layers of *Epiphora bauhiniae* and *Anaphe panda* cocoon shells (Mean  $\pm$  S.E.)

Species	Layers	Moisture regain (%)	
		Cocoon shells	Degummed fibers
<i>Epiphora bauhiniae</i>	Outer	5.27 $\pm$ 0.35 <sup>c</sup>	8.5 $\pm$ 0.23 <sup>a</sup>
	Middle	5.0 $\pm$ 0.49 <sup>c</sup>	8.63 $\pm$ 0.72 <sup>a</sup>
	Inner	6.83 $\pm$ 0.35 <sup>b</sup>	8.37 $\pm$ 0.22 <sup>a</sup>
<i>Anaphe panda</i>	Outer	6.96 $\pm$ 0.56 <sup>b</sup>	8.85 $\pm$ 0.42 <sup>b</sup>
	Middle	7.46 $\pm$ 0.03 <sup>ab</sup>	8.43 $\pm$ 0.06 <sup>ab</sup>
	Inner	8.63 $\pm$ 0.45 <sup>a</sup>	9.49 $\pm$ 0.08 <sup>a</sup>

Means followed by the same letter in a column are not statistically significant ( $P < 0.05$ )

using the least significant difference test (LSD)

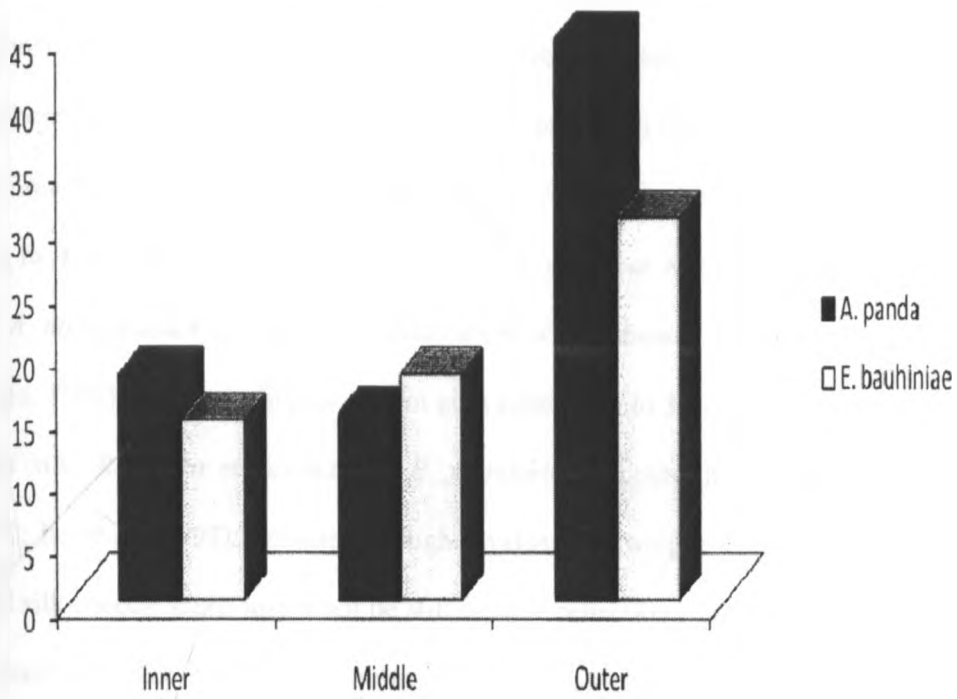


Figure 11: Percentage weight loss of layers of *A. panda* and *E. bauhiniae* cocoon shells

#### 6.4. DISCUSSION

Weight loss and moisture regain varied among the African wild silk cocoon shells and degummed fibers. The weight loss and moisture regain for *B. mori* was well within the limits of 19 to 30% reported in other studies (Arami *et al.*, 2007; Gulrajani, 1988; Sarovart *et al.*, 2003). The weight loss from African wild silk cocoon shells ranged from 23 to 56.8 % and is inconsistent with previous reports that the sericin content of wild silk fibers is less than the mulberry silk and as low as 12 -16% (Cavaco-paulo and Gubitz, 2003; Prasong *et al.*, 2009). Karumar (1999) reported 5 - 15% sericin gum content for tussah silk fibers. The degumming loss in *A. proylei*, *A. assama*, *A. pernyi* and *A. yamamai* was in the range of 7 - 13% except for *A. mylitta* and *Philosamia Cynthia ricicni* which showed 3.7 and 4.5% loss, respectively (Kato, 1991). However, higher sericin gum content up to 38 and 68% have been reported for Thai silk, *Rondotia menciiana* and *B. mandarina* cocoon shells, respectively (Dhavalikar, 1962; Ito *et al.*, 1992). Despite the higher values, the weight losses reported for the African wild silk cocoon shells might not be still the true reflection of the gum content of the cocoons as verified by the presence of remnant traces of sericin gum observed on the SEM images after degumming.

The variations in the amount of sericin gum and fibroin in cocoons shells might be due to a number of factors including genetic differences in the sericin protein as well as external environmental variables (Shamitha and Rao, 2006) which together can determine the quality of cocoons for commercial purposes (Singhvi and Bose, 1991). According to Kato and Hata

(1998) the cocoon filaments of polyphagous silkworms with coarse filaments have higher values for degumming losses than conventional cocoon filaments. This, together with the presence of calcium oxalate crystals, can be an explanation for the high weight loss of *G. postica* which is a polyphagous silkworm feeding on more than one acacia host plants including *Acacia tortilis*, *A. elatior*, *A. nilotica*, , *A. mellifera*, *A. mearnsii*, *A. hockii* and *A. brevispica* (Ngoka, *et al.*, 2007; Fening *et al.*, 2008). Nasreen *et al.* (1999) also reported difference in quality of *B. mori* cocoons from larvae fed on mixed leaves. Chemical composition of sericin also affects its solubility in hot water resulting in considerable variation in weight loss (Komatsu, 1975; Robson, 1985). The presence of certain amount of sericin after degumming shows its important role in processing and application of the fibers.

Physical properties and chemical composition of silk fibers from mulberry and wild silkmoths determine the variability in different parameters (Mondal *et al.*, 2007b; Srisuwan and Srihanam, 2009). Interestingly, there was an increase in moisture regain for all cocoon shells when fibers were degummed. Sen and Babu (2004a) also observed similar results that non-mulberry silk fibers had marginally higher moisture regain values of 10.8%. However, this is in contrast with Snowalker (1993) who reported degummed fibers to have lower moisture regain due to loss of sericin. The difference in moisture regain might be due to variations in compactness of the cocoon shells, change in the quantity, composition and chemistry of sericin gum across layers and surface structure of the fibers. Moisture regain of cocoon shells and fibers could provide information on the extent of areas accessible to water vapour within the fiber. The higher moisture regain for *A. mimosae* cocoon shells might be

due to the presence of holes/perforations on the cocoon surface providing more area for moisture ingress (Fig.7a-b). The presence of higher ratios of hydrophilic versus hydrophobic amino acid residues in the chemical architecture of non-mulberry compared to mulberry silks might also affect in the higher moisture regain of the wild silks (Table 5). The presence of larger voids in the wild silk fibers might also contribute to their higher moisture absorption than *B. mori* (Fig 9k-o).

General trends of decreased weight loss and increased moisture regain from outer to inner shell layers were observed in *A. panda* and *E. bauhinia* cocoons, respectively. Nawaz *et al.* (2002) revealed that with change in filament type and size (denier), moisture regain changes significantly due to the difference in structures of fibers as well as changes in liner density and arrangement of monomers in the polymer (Munro, 1987). The presence of foreign matters such as dust and hair like brittles on outer layer of *A. panda* suggested the influence of physical structure in preventing fibers from absorbing moisture. In conclusion, the variation in weight loss and moisture regain among the different cocoons and shell layers can be the demonstration of the difference in the amount and composition of sericin present in each layer. Such layer wise variation in cocoon properties down the cocoon layers may confound objectionable fabric patterns either from visual or textural perspective (Das and Ghosh, 2010).



## CHAPTER SEVEN

# DISSOLUTION PROPERTIES OF COCOON SHELLS AND DEGUMMED FIBERS

### 7.1. INTRODUCTION

Raw silk consists of essentially two major proteins, fibroin (the core structural protein) and sericin (the surrounding glue gum). Sericin, which covers the periphery of the raw silk fibers, is highly soluble in hot water and can easily be removed in the process of degumming, while fibroin is not soluble in water (Arami *et al.*, 2007). The solution behaviour of silk fibroin is of interest due to its novel self-assembly and processing related to fiber spinning in spiders and silkworms, resulting in remarkable mechanical properties (Matsumoto *et al.*, 2008). In recent years, fibroin from the domesticated silkworm, *B. mori* has been the dominant source for silk-based biomaterials and its dissolution properties are often required for non-textile applications. This is mainly due to the difficulty to dissolve silk fibroin in common solvents for obtaining a true solution because of its high molecular weight and crystallinity (Ki *et al.*, 2007a).

The insolubility of silk fibroin in common organic solvents is due to the intermolecular hydrogen bonding existing in the polymer and its hydrophobic nature (Furuhata *et al.*, 1994; Jin and Kaplan, 2003). Fibroin dissolution is further affected by non-uniformity in chemical composition, supra-molecular structure and morphological features of natural fibers (Sashina

*et al.*, 2006). The environmental factors and the processing conditions used by the silk producing insects also influence the solution behaviour and ultimately the material properties of these fibers (Matsumoto *et al.*, 2008).

Despite these difficulties, the solubility of silk in certain solvents has been studied and several proper solvent systems have been successfully used to dissolve silk fibroin including LiBr (Alessandrino *et al.*, 2008), N-methylmorpholine-N-oxide (NMMO) hydrate (Plaza *et al.*, 2008), phosphoric acid/formic acid mixture (Ki *et al.*, 2007a), calcium nitrate (Kweon *et al.*, 2001), and CaCl<sub>2</sub> (Miyaguchi and Hu, 2005). Ajisawa (1998) also recommended chaotropic reagents such as lithium thiocyanate (LiSCN), LiBr, NaSCN, and CaCl<sub>2</sub> as dissolution reagents for silk fibroin. However, the solubility of different silk fibers in these solvent systems was reported to be inconsistent. Srisuwan and Srihanam (2009) found *B. mori* silk is more soluble than Eri silk. *Antherea pernyi* fibroin is also difficult to dissolve due to the strong inter and intra-molecular interactions between its fibroin molecules and chains (Kweon *et al.*, 2000; 2001). In this regard, the wild silk from Genus *Antheraea* is mostly studied (Dash *et al.*, 2007). The African wild silkworms, which produce commercially important silk are found widely distributed in different geographical regions of Africa. However, little information is available so far on their structure and properties, of which dissolution properties are no exceptions.

## 7.2. MATERIALS AND METHODS

### 7.2.1. Determination of dissolution of cocoon shells and degummed fibers

Degummed fibers were dried in oven at 110°C for 24 hours and stored in desiccators prior to use. Analytical grades of CaCl<sub>2</sub>, NaSCN and LiBr were used. Aqueous solutions (9M) were prepared by dissolving 299.68, 234.48 and 218.84g of CaCl<sub>2</sub>, LiBr and NaSCN, respectively in 300ml distilled water and stirred with a magnetic stirrer at room temperature for ten minutes. Air dried degummed fibers (0.1g) from each species were dissolved in 10ml of each solvent solution at 70°C for 3 hours with gentle shaking of flasks at 40rpm in an incubator (Sah and Pramanik, 2010). Oven dried cocoon shell discs (1g) were also dissolved the same way. The resulting solutions were allowed to settle overnight. The undissolved silk was filtered through filter paper, washed, dried in a vacuum drying oven at 110°C for 24 hours and weighed. The dry weight remaining was expressed as a percentage relative to the initial weight and solubility was calculated as (Rastogi *et al.*, 2001; Kweon *et al.*, 2001):

$$\text{Solubility}(\%) = \frac{W_i - W_f}{W_i} \times 100$$

Where  $W_i$  = initial weight of the sample (g) and

$W_f$  = final weight of the sample (g)

The experiment was replicated four times. Percentage solubility was arcsine transformed to bring the data to normal distribution and analyzed with two-way ANOVA with PROC ANOVA procedure (SAS Institute, 2010). LSD test ( $\alpha=0.05$ ) was used to separate the means.

### **7.2.2. Scanning Electron Microscope observation of fibers after dissolution**

Dried fibroin supernatant of *A. panda*, *A. mimosae* and *E. bauhiniae* were mounted onto copper stubs using double-sided sticking tape and sputter-coated with gold for three minutes. The samples were then observed with SEM.

## 7.3. RESULTS

### 7.3.1. Solubility of cocoon shells

Table 8 showed the percentage solubility of cocoon shells dissolved with 9M aqueous solutions of  $\text{CaCl}_2$ , LiBr and NaSCN. The results confirmed that dissolution property of cocoon shells varied depending on the origin of cocoon shells and the solvents used. The interaction effects of solvents and species was highly significant ( $P > 0.05$ ). *B. mori* had the highest percentage solubility across the solvents used (51.5%) and LiBr had significantly higher dissolving ability (41.2%). There was no significant difference in the solubility of cocoon shells in  $\text{CaCl}_2$  and NaSCN, even though the former had slightly higher dissolving ability (Table 8). Among the wild silk cocoon shells, *G. postica* had higher solubility. *G. postica* cocoon shells were dissolved completely in LiBr solutions and the supernatant was composed of the calcium oxalate crystals and remnants of cocoon spines and hairs.

Table 8: Percentage solubility of cocoon shells of four African wild silkmoths and *Bombyx mori* (Mean  $\pm$  SE)

Species	Solvents			
	CaCl <sub>2</sub>	LiBr	NaSCN	Mean
<i>Bombyx mori</i>	29.8 $\pm$ 0.9 <sup>a</sup>	97.7 $\pm$ 0.4 <sup>a</sup>	26.8 $\pm$ 1.2 <sup>a</sup>	51.5 $\pm$ 23.1 <sup>a</sup>
<i>Anaphe panda</i>	11.2 $\pm$ 0.4 <sup>c</sup>	21.5 $\pm$ 0.8 <sup>c</sup>	11.2 $\pm$ 0.5 <sup>c</sup>	14.6 $\pm$ 3.4 <sup>c</sup>
<i>Argema mimosae</i>	5.7 $\pm$ 0.7 <sup>d</sup>	7.7 $\pm$ 0.6 <sup>d</sup>	3.4 $\pm$ 0.9 <sup>d</sup>	5.6 $\pm$ 1.2 <sup>c</sup>
<i>Epiphora bauhiniae</i>	3.1 $\pm$ 0.5 <sup>c</sup>	3.2 $\pm$ 0.4 <sup>e</sup>	2.4 $\pm$ 0.4 <sup>d</sup>	3.1 $\pm$ 0.3 <sup>c</sup>
<i>Gonometa postica</i>	15.4 $\pm$ 0.9 <sup>b</sup>	74.7 $\pm$ 1.3 <sup>b</sup>	21.6 $\pm$ 0.9 <sup>b</sup>	37.3 $\pm$ 18.8 <sup>b</sup>
<b>Mean</b>	<b>13.1<math>\pm</math>4.7<sup>b</sup></b>	<b>41.2<math>\pm</math>19.1<sup>a</sup></b>	<b>13.1<math>\pm</math>4.8<sup>b</sup></b>	<b>22.4<math>\pm</math>9.3</b>

Means followed by the same letter in the same column are not statistically significant ( $P < 0.05$ ) according to Least Significant Difference (LSD) test

### 7.3.2. Solubility of degummed fibers

The dissolution of degummed fibers also showed significant differences ( $P > 0.05$ ) in interaction of species and solvents. Like the cocoon shells, *B. mori* fibers also showed highest solubility in all the solvents used (59.3%) and LiBr proved the best solvent agent for the fibers (84.5%) (Table 9). *G. postica* had non-significant solubility percentage (97%) as *B. mori* in LiBr. Unlike the cocoon shells, there was a significant difference in dissolution percentage of fibers in  $\text{CaCl}_2$  and NaSCN (18.2 and 25.4%, respectively). Much of the solid fibers of *A. mimosae*, *A. panda* and *E. bauhiniae* in these solvents were intact after three hours of treatment, which indicate that dissolution of fibers was not complete in these species.

Table 9: Percentage solubility of African wild and *Bombyx mori* degummed silk fibers (Mean  $\pm$  SE)


Species	Solvents			
	CaCl <sub>2</sub>	LiBr	NaSCN	Mean
<i>Bombyx mori</i>	29.9 $\pm$ 1.2 <sup>a</sup>	99.1 $\pm$ 0.2 <sup>a</sup>	48.8 $\pm$ 1.9 <sup>a</sup>	59.3 $\pm$ 20.6 <sup>a</sup>
<i>Anaphe panda</i>	12.5 $\pm$ 1.1 <sup>c</sup>	84.4 $\pm$ 0.6 <sup>b</sup>	20.5 $\pm$ 1.8 <sup>c</sup>	39.1 $\pm$ 22.7 <sup>c</sup>
<i>Argema mimosae</i>	12.1 $\pm$ 1.3 <sup>c</sup>	77.2 $\pm$ 0.6 <sup>c</sup>	11.2 $\pm$ 1.5 <sup>d</sup>	33.5 $\pm$ 21.8 <sup>d</sup>
<i>Epiphora bauhiniae</i>	14.1 $\pm$ 1.0 <sup>c</sup>	64.4 $\pm$ 1.0 <sup>d</sup>	11.5 $\pm$ 1.4 <sup>d</sup>	30.1 $\pm$ 17.2 <sup>c</sup>
<i>Gonometa postica</i>	22.2 $\pm$ 0.6 <sup>b</sup>	97.5 $\pm$ 0.2 <sup>a</sup>	35.4 $\pm$ 1.7 <sup>b</sup>	51.7 $\pm$ 23.2 <sup>b</sup>
<b>Mean</b>	<b>18.2<math>\pm</math>3.4<sup>c</sup></b>	<b>84.5<math>\pm</math>6.5<sup>a</sup></b>	<b>25.4<math>\pm</math>7.3<sup>b</sup></b>	<b>42.7<math>\pm</math>21.0</b>

Means followed by the same letter in the same column are not statistically significant ( $P < 0.05$ ) according to Least Significant Difference (LSD) test


The SEM micrographs for these fibers after treatment with LiBr highlighted the differences in the mechanism of dissolution (Figure 12). It was noted that part of the fibers of *A. panda* in LiBr showed a strong tendency of gelling and were difficult to handle (Figure 12a). This might be an indication for the need for longer time of exposure for complete dissolution. On




the other hand, *E. bauhiniae* fibers were cracked and signs of disintegration and fractures were observed on the surface (Fig. 12b), while fibers of *A. mimosae* were broken in to pieces exposing the individual fibrils (Fig. 12c).

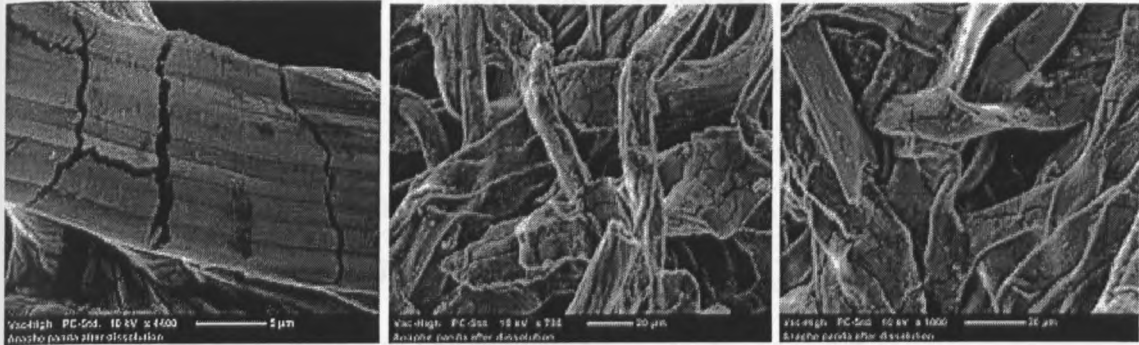

(a) *Anaphe panda*

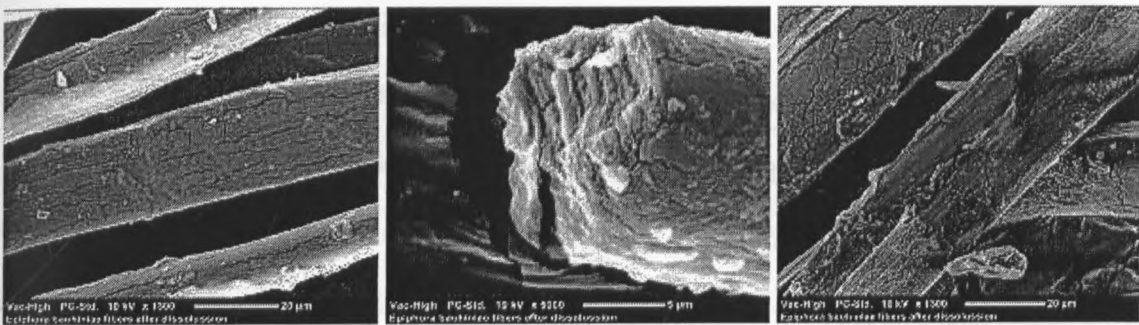

(b) *Epiphora bauhiniae*

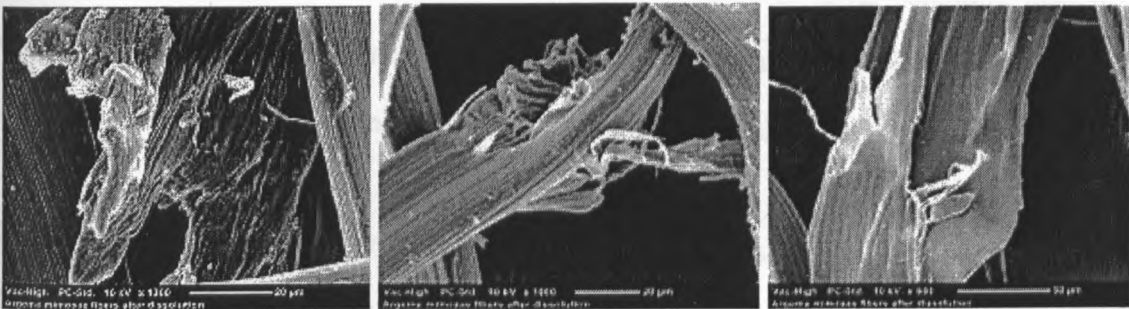

(c) *Argema mimosae*

Figure 12: SEM micrographs of *Anaphe panda*, *Epiphora bauhiniae* and *Argema mimosae* fibers after dissolution with 9M LiBr

#### 7.4. DISCUSSION

The study clearly showed that African wild silk cocoon shells and degummed fibers have variability in their solubility in different solvent systems. LiBr exhibited higher dissolving ability than the other solvents. However, this is in contrast with Srisuwan and Srihanam (2009) who reported that 9M LiBr had the least ability to dissolve *Philosamia ricini* silk fibroin. The low solubility of *A. panda*, *E. bauhiniae* and *A. mimosae* cocoon shells and degummed fibers in all the solvent systems could be due to the short time of treatment or the solvent systems were not strong enough to produce the desired level of dissolution. The temperature and concentration of the solutions could also be a factor for low solubility of the cocoon shells. Other wild silks, such as *A. pernyi* silk fibroin also require a high concentration of chaotropic salts, high temperature, and longer treatment time (Kweon *et al.*, 2000). Miyaguchi and Hu (2005) also reported that the solubility of *B. mori* silk fibroin increased sharply with higher concentration of CaCl<sub>2</sub>, addition of ethanol and longer heating periods. The presence of sericin/gum and other impurities on the cocoon shells might also have prevented the penetration of the solvents and resulted in lower solubility than the degummed fibers. The difference in solubility showed the variability existing in chemical structure and composition among the African wild silk cocoon shells and fibers.

The solubility of the African wild silk cocoon shells and fibers was significantly lower than *B. mori* except *G. postica* in LiBr solution demonstrating the presence of clear difference in chemical composition among the silks tested. Solubilisation of non-mulberry cocoons with

LiBr and LiSCN proved also to be less effective and resulted in low yield than *B. mori* (Mandal and Kundu, 2008). Dissolution of a protein was reported to depend on its structure, molecular weight and structure of its macromolecules, and polarity and steric arrangement of the side groups (Sashina *et al.*, 2003). The amino acid sequence of polypeptides also plays a very important role in the solubility and crystallization of silk fibroins (Tanaka *et al.*, 2002).

Fabrication of large amount of fiber wastes produced from the silk industries involves formation of reGenerated fibroin materials such as solution, powder, film, gel, and filament by dissolving in proper solvent systems depending on its preparation conditions and application field (Sashina *et al.*, 2006). Active efforts are being made to develop processes involving preparation of working solutions of natural polymers and their conversion into particular, fibers and films. Although the African wild silk is solely utilized as a textile raw material, the recent venture and development of silk in various areas of applications requires further processing such as dissolving in different solvent systems using several methods. Solutions of fibroin which can easily be transferred in to gels, powder or films for biomaterial preparation are required. For this, solution systems, which dissociate the intra-molecular bonding of silk fibers without breaking the polypeptide chains, are essential. In this regard, even though this study is far from this confirmation, it sheds light on the solution properties of the African silk fibers and their potential for subsequent preparation of films, scaffolds and fibers for various applications.

## CHAPTER EIGHT

### TENSILE PROPERTIES AND THERMAL DEGRADATION BEHAVIOURS OF COCOON SHELLS AND DEGUMMED FIBERS

#### 8.1. INTRODUCTION

Natural fibers from animals and plants have found their way into commercial applications, once again. Silk is a unique class of structural animal fiber and has long been regarded as a superb natural material due to its characteristic high strength, elongation, feel and luster. The variation in composition, structure and properties of silks from different arthropods has led to their considerations in wider applications expanding from more traditional textile industries to fields such as biomedical, biotechnological, and tissue engineering. The usefulness of silk fibers in these and many other applications is associated with its predominant failure mechanism under the conditions of the application and its adaptability to varied environmental conditions facilitated by the silk's molecular composition and hierarchical structure. These, in turn are both affected by the conditions during its production such as spinning speed, relative humidity, temperature, pH, ionic strength, solvent composition and mechanical stress as well as the degumming process (Chen *et al.*, 2001; Shao and Vollrath, 2002; Pe' rez-Rigueiro *et al.*, 2002; Zhang *et al.*, 2010b; Manjunatha *et al.*, 2010).

The mechanical properties of silk fibers also depend on the structure of the silk constituent proteins (sericin and fibroin) before and after silk fiber formation (Lin *et al.*, 2009). For

example, sericin coating adds to the tensile properties of the silk fiber that are primarily determined by the fibroin structure (Jiang *et al.*, 2006). Sericin could also induce the transition of silk fibroin from the random coil or  $\alpha$ -helix to the  $\beta$ -sheet structure, and further improve the mechanical properties of silk fibers (Ki *et al.*, 2007b). High crystallinity confers the silk material greater strength by virtue of the network of hydrogen bonds between and within the proteins (Sutherland *et al.*, 2010).

Temperature and moisture are among the environmental stresses influencing properties and functions of silk cocoons and fibers. Cocoon shells are important in temperature regulation, water loss reduction from the pupae and acquisition of heat (Rosner and Führer, 1996; Danks, 2004). Temperature also influences the amount of water absorbed by silk fibers resulting in alteration of physical properties. Chemical composition and structure of silk fibers determine the thermal tolerance behaviour of the cocoon shells and fibers and the resulting weight loss due to dehydration and/or decomposition. Hence, it is appropriate to deploy Thermal Analysis (TA) to investigate the response of natural materials such as silk, to temperature scans and to explore together with other data, the structure-property-function relations of natural fibers (Wiedemann and McKarns, 1990). Accordingly, a comparative study of the mechanical properties and thermal degradation behaviours of cocoon shells and degummed fibers from four African wild silkmoth was studied.

## 8.2. MATERIALS AND METHODS

### 8.2.1. Determination of tensile properties of cocoon shells

Cocoon shells of *G. postica* and *A. mimosae* were used due to their single cocoon shell structure. *B. mori* (Race *icipa* II) cocoon shells were used for comparison. Three full cocoon shell strips (dimensions of 5x15mm) were cut longitudinally from the middle sections of each cocoon and five cocoon shells were used for each species. Instron 5542 tensile testing instrument (load cell 500N) was used for tensile testing. Tensile test was carried out at room temperature with gauge length of 5mm and at a speed of 2mm/min.


### 8.2.2. Determination of tensile properties of degummed fibers

The tensile test was carried out in accordance with the American Standard for Test and Measurement (ASTM) D 3379-75. Fibers (100mm long) were obtained by pulling gently after degumming and were left overnight in air before testing. The fibers were then cut gently into 30mm ensuring that the fibers were not stressed plastically during the process. Every fiber was then mounted and taped across a hole, which is 10mm long, of a rectangular cardboard which was then fixed in an Instron 5542 materials testing machine (5N load cell). Before being tested, each specimen was examined under an optical microscope to ensure that only single fibers were used. The gauge length was adjusted at 10mm. The cardboard was then cut on both sides and separated into two parts to ensure tensile loading was completely transmitted to the fiber during test. All tests were conducted at a rate of 0.1mm/sec at 22°C


and 55% RH. Ten tests were made for each species to Generate the average tensile stress-strain curve.

#### **8.2.2.1. Measurement of cross sectional area of fibers**


Cross sectional areas of the fibers were prepared by clamping orientated silk threads in a holder and cutting them across with a new razor blade before sputtering them with gold for SEM viewing. Digital images of transverse sections on the SEM micrographs were nalyzed with ImageJ 1.42q software (Fig 13). Normalized cross-sectional areas were obtained by averaging 150 brins for each sample assuming that sample volume will be conserved during the tensile tests (Pe´rez-Rigueiro *et al.*, 1998).

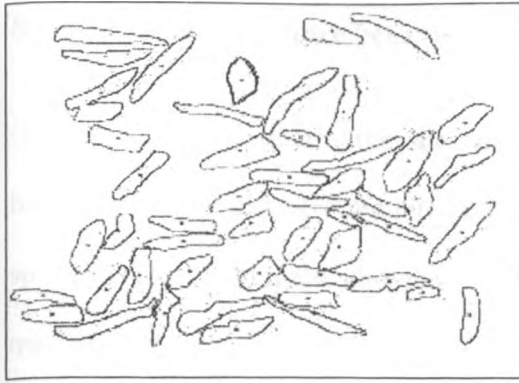


(a) *Argema mimosae*

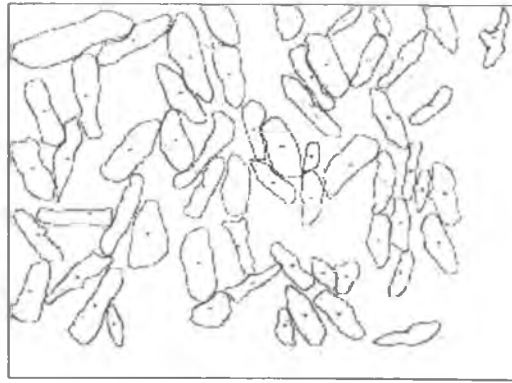


(b) *Epiphora bauhiniae*

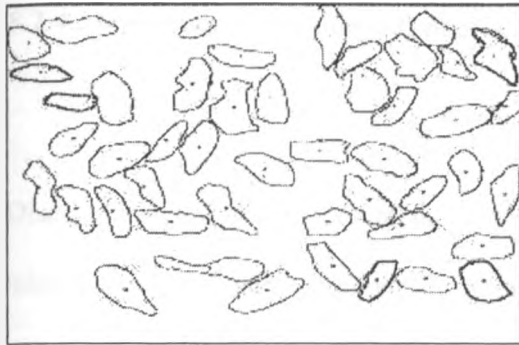

(c) *Gonometa postica*

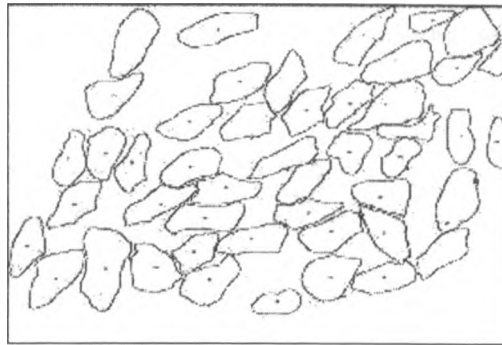

(d) *Bombyx mori*

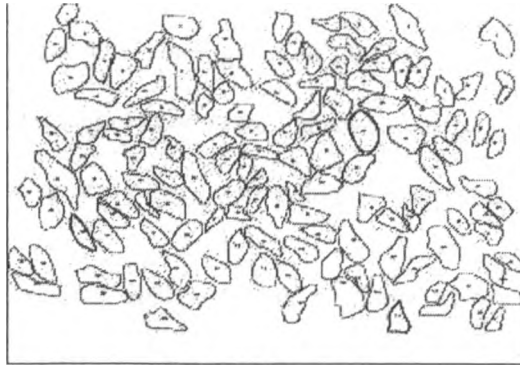

(e) *Anaphe panda*

Figure 13: Imagej software images of the cross sectional area of African wild and *Bombyx mori* silk fibers



### **8.2.3. Analysis of fracture behaviour of cocoons and fibers**

Cocoon shells and fibers after the tensile failure were used. Tested samples which were broken at the middle were mounted on a copper stub with a double-sided sticking tape and sputter coated with gold and then were examined under SEM to analyze the fracture mechanisms.

### **8.2.4. Determination of thermal degradation behaviours of cocoon shells and degummed fibers**

Discs of cocoon shells and degummed fibers (7mm in diameter) were pressed out from middle section of the cocoon and the compressed degummed fibers floss, respectively with a sharp hole-punch. The samples were loaded into a Q50 TGA from TA instruments. Test conditions included temperature ranges of 25 - 900 and 25 - 800°C for cocoon shells and degummed fibers, respectively, at a heating rate of 20°C/min, N<sub>2</sub> flow of 60mL/min and air cool time of 40 minutes. Samples of cocoon shell discs and degummed fibers after TGA were mounted onto copper stubs, sputter-coated with gold and examined with SEM.

All Instron and TGA data were analyzed with one-way ANOVA with PROC ANOVA procedure (SAS Institute, 2010). LSD test ( $\alpha=0.05$ ) was used to separate the means. The tensile parameters were calculated with a home designed program in Excel (Tensile Import v2.0) (developed by University of Oxford Silk Research Group). Stress-strain curves were plotted using Origin Pro 8<sup>®</sup> programme.

## 8.3. RESULTS

### 8.3.1. Tensile properties of cocoon shells

The measured data of the tensile properties of cocoon shells was presented in Table 10, and the average stress-strain curves were presented in Figure 14. The results clearly demonstrated that the tensile properties of silk cocoon shells differed from one species to another. Modulus reduced as strain increased and the binding points between fibers were observed to break progressively in the cocoon shells. After a peak stress, there was rapid fall in stress, which showed the continuous fiber bonding present in the cocoon shells was broken and replaced by simple entangled fibers. *G. postica* and *A. mimosae* had lower breaking stress and breaking energy and higher breaking strain and initial modulus than *B. mori* (Table 10). However, the strain at maximum stress and the modulus were not statistically significant for the cocoons tested.

The SEM micrographs of cocoon shells fracture surfaces after failure were observed (Fig. 15a-c). It was clear that the surrounding gum of the cocoon shells was still intact connecting the cocoon fibers together in a bonded but open network. Fiber debonding was observed in all the species tested. Some of the silk fibers within the fracture area were broken and pulled out from one part of the cocoon specimen. The micrographs also clearly showed fiber pull-out and debonding predominated the fracture mechanism with fairly clean and recognizable fiber surface without matrix adherence. In addition, crack initiation sites and propagation through

the matrix were observed. The clear fracture surfaces showed poor fiber interfacial bonding in cocoon shells.

Table 10: Tensile properties of *Gonometa postica*, *Argema mimosae* and *Bombyx mori* cocoon shells (Mean  $\pm$  SE)

Species	Initial modulus (MPa)	Maximum stress (MPa)	Strain at Max stress (%)	Breaking energy (J/cm <sup>3</sup> )
<i>Argema mimosae</i>	404.6 $\pm$ 59.8 <sup>a</sup>	69.6 $\pm$ 7.0 <sup>c</sup>	21.2 $\pm$ 1.0 <sup>a</sup>	13.8 $\pm$ 1.9 <sup>b</sup>
<i>Gonometa postica</i>	397.4 $\pm$ 63.4 <sup>a</sup>	47.2 $\pm$ 1.7 <sup>b</sup>	23.3 $\pm$ 1.2 <sup>a</sup>	11.4 $\pm$ 0.6 <sup>b</sup>
<i>Bombyx mori</i>	334.5 $\pm$ 28.3 <sup>a</sup>	101.1 $\pm$ 4.2 <sup>a</sup>	20.8 $\pm$ 1.2 <sup>a</sup>	20.1 $\pm$ 0.7 <sup>a</sup>

Means followed by the same letter in the same column are not statistically significant ( $P < 0.05$ ) according to Least Significant Difference (LSD) test

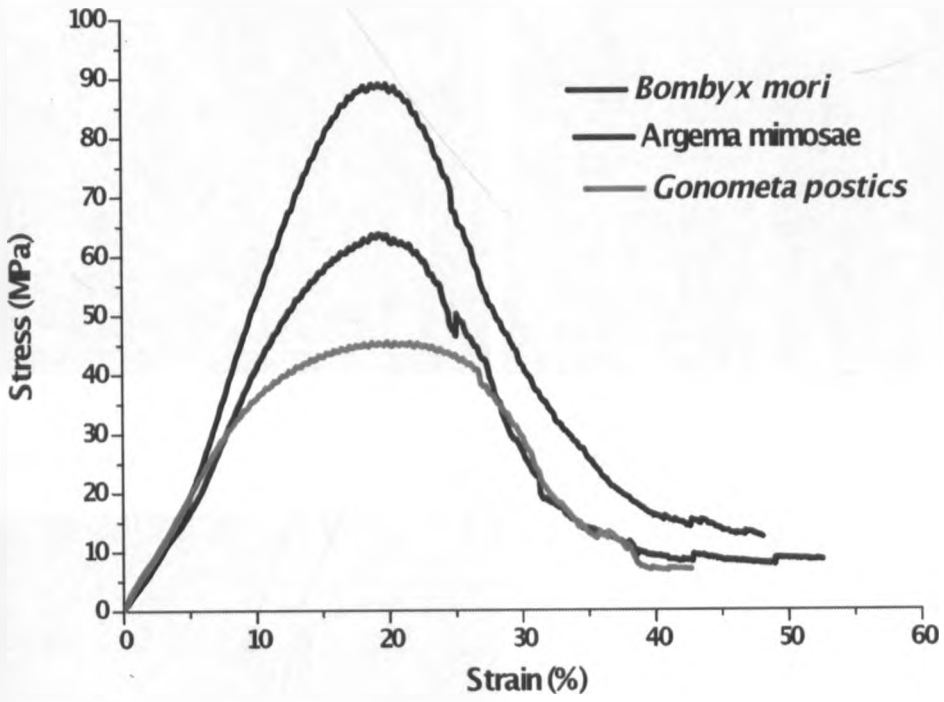


Figure 14: Stress-strain curves for *Gonometa postica*, *Argema mimosae* and *Bombyx mori* cocoon shells

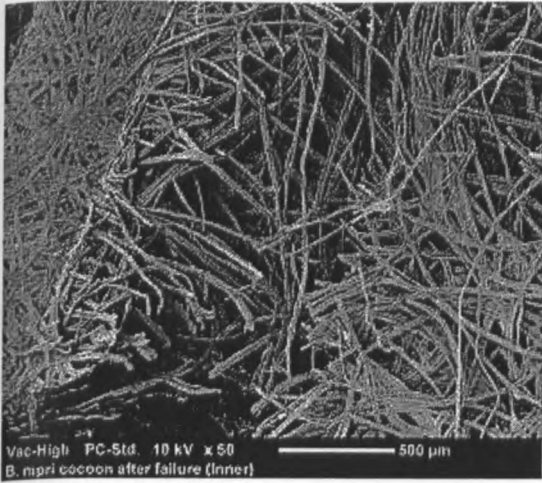
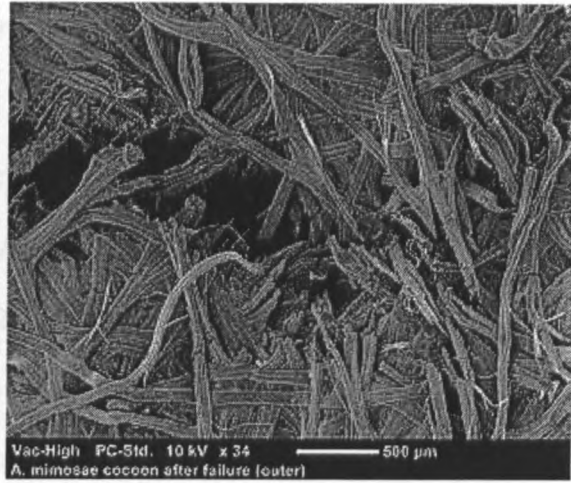
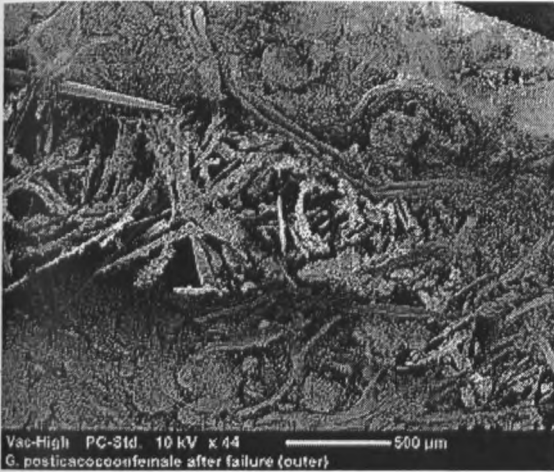
(a) *Bombyx mori*(b) *Argema mimosae*(c) *Gonometa postica*

Figure 15: SEM micrographs of fracture surfaces of *Gonometa postica*, *Argema mimosae* and *Bombyx mori* cocoon shells after tensile failure

### 8.3.2. Tensile properties of degummed fibers

The tensile properties of degummed fibers of African wild silks also showed significant variability ( $P > 0.05$ ) as shown in Table 11. *G. postica* fibers had the highest breaking strain (41.3%) and breaking energy ( $76\text{J}/\text{cm}^3$ ). *E. bauhiniae* had the lowest breaking stress (247MPa). All of the other wild silk fibers had breaking energy between  $34\text{-}52\text{J}/\text{cm}^3$  that was lower than *B. mori* ( $66\text{J}/\text{cm}^3$ ) (Table 11). However, *B. mori* had the highest breaking stress (427MPa), which was not statistically significant with *A. panda* and *A. mimosae*. The stress-strain curves of *A. mimosae*, *E. bauhiniae* and *G. postica* fibers showed sigoidal shape and three regions were distinguished: an initial linear elastic region, a yield region, and a hardening region (Figure 16). However, *B. mori* and *A. panda* fiber started with an elastic region followed directly by strain hardening where the stress increases non-linearly with strain. Despite the average cross sectional area used to calculate the tensile properties, wild silk fibers showed noticeably higher standard deviation than *B. mori* indicating the considerable variation in the diameter of the fibers along their length and between fibers (Table 12).

Table 11: Tensile properties of single African wild and *Bombyx mori* silk fibers (Mean  $\pm$  SE)

Species	Initial modulus (MPa)	Ultimate Tensile Strength (MPa)	Ultimate Tensile Strain (%)	Breaking energy (J/cm <sup>3</sup> )
<i>Anaphe panda</i>	6344.4 $\pm$ 798.9 <sup>b</sup>	365.1 $\pm$ 51.1 <sup>ab</sup>	17.7 $\pm$ 0.7 <sup>c</sup>	43.3 $\pm$ 7.2 <sup>cd</sup>
<i>Argema mimosae</i>	8326.5 $\pm$ 742.0 <sup>a</sup>	363.4 $\pm$ 6.5 <sup>ab</sup>	20.7 $\pm$ 1.0 <sup>bc</sup>	51.6 $\pm$ 2.9 <sup>bc</sup>
<i>Epiphora bauhiniae</i>	7497 $\pm$ 331.7 <sup>ab</sup>	247.7 $\pm$ 6.3 <sup>c</sup>	20.8 $\pm$ 1.3 <sup>b</sup>	34.5 $\pm$ 2.4 <sup>d</sup>
<i>Gonometa postica</i>	7153.9 $\pm$ 544.6 <sup>ab</sup>	310 $\pm$ 37.1 <sup>b</sup>	41.3 $\pm$ 1.4 <sup>a</sup>	76.4 $\pm$ 8.2 <sup>a</sup>
<i>Bombyx mori</i>	8787 $\pm$ 555.1 <sup>a</sup>	427.6 $\pm$ 10.6 <sup>a</sup>	21.8 $\pm$ 0.5 <sup>b</sup>	66 $\pm$ 2.8 <sup>ab</sup>

Means followed by the same letter in the same column are not statistically significant ( $P < 0.05$ ) according to Least Significant Difference (LSD) test

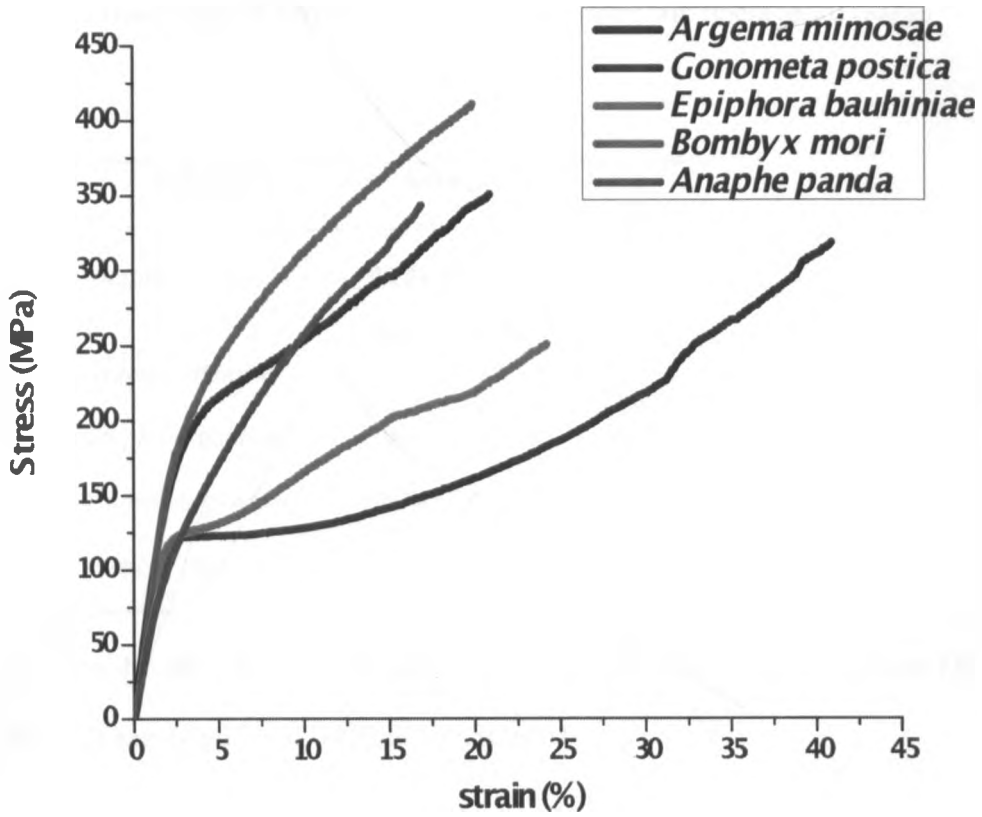


Figure 16: Stress- strain curves for African wild and *Bombyx mori* degummed single silk fibers



Table 12: Cross sectional area of African wild and *Bombyx mori* silk fibers (brin) (Mean  $\pm$ SE)

Silk fibers	Area ( $\mu\text{m}^2$ )	<i>n</i>
<i>Anaphe panda</i>	96.7 $\pm$ 5.7 <sup>c</sup>	150
<i>Argema mimosae</i>	388.5 $\pm$ 14.5 <sup>a</sup>	150
<i>Epiphora bauhiniae</i>	100.4 $\pm$ 5.3 <sup>c</sup>	150
<i>Gonometa postica</i>	161.4 $\pm$ 8.2 <sup>b</sup>	150
<i>Bombyx mori</i>	59.9 $\pm$ 2.5 <sup>d</sup>	150

Means followed by the same letter in the same column are not statistically significant ( $P < 0.05$ ) according to Least Significant Difference (LSD) test

The fractures of fibers after failure were shown in Fig. 17 (a -e). It was not possible to generalize the fracture behaviours for the fibers tested. However, *B. mori* and *A. panda* fibers seemed to store the stress by stretching and then fiber pull-out occurred. *G. postica* fibers showed fiber crack or split during failure. However, *A. mimosae* and *E. bauhiniae* had ripped smooth failure surfaces.

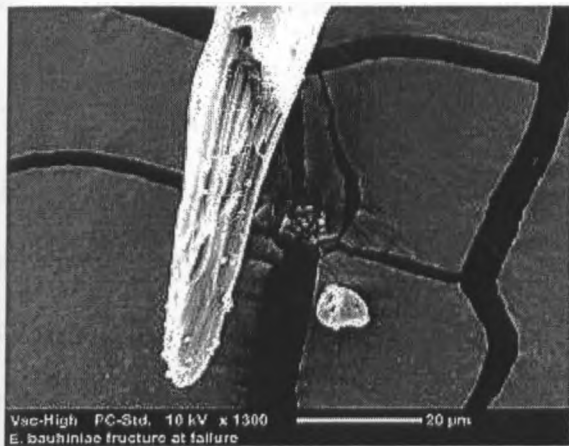
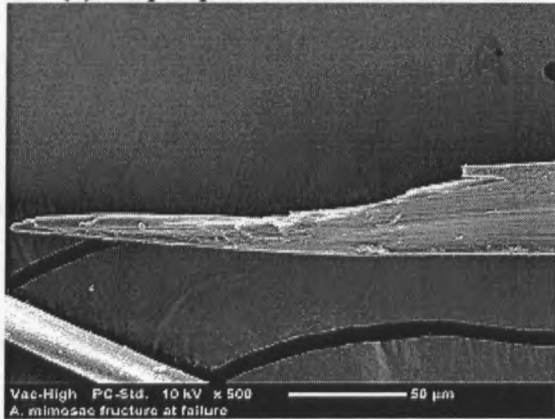
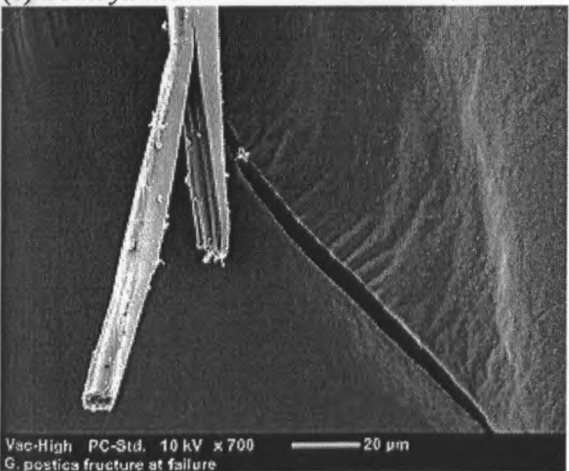
(a) *Epiphora bauhiniae*(b) *Anaphe panda*(c) *Bombyx mori*(d) *Argema mimosae*(e) *Gonometa postica*

Figure 17: SEM micrographs of fracture surfaces of degummed fibers after tensile failure

### 8.3.3. Thermal degradation behaviour of cocoon shells

The dehydration loss from cocoon shells was highest for *A. mimosae* (11.9%) and lowest for *B. mori* (9.8%) (Table 13). However, the weight losses from the other wild silk cocoons were non-significant ( $P < 0.05$ ). Figure 18 illustrated the thermal decomposition behaviours of cocoon shells. The TG curves showed that weight loss due to dehydration of absorbed water molecules associated in cocoon shells continued rapidly up to 101, 120, 125, 154, and 127°C for *B. mori*, *G. postica*, *E. bauhinae*, *A. mimosae*, and *A. panda*, respectively. Substantial weight losses followed the stable or gradual decrease in weight as heating temperature increased. Rapid weight losses begun at 300, 306, 302, 313, and 296°C for *B. mori*, *E. bauhinae*, *A. mimosae*, *A. panda* and *G. postica*, cocoons, respectively. *B. mori* cocoons had relatively inferior thermal resistance than most of the wild silk cocoon shells. The thermal decomposition of *G. postica* cocoons occurred in multiple steps than the rest of the species with additional decompositions occurring at temperature ranges of 483-506 and 710-730°C. In *A. mimosae*, weight loss became stable and constant after the rapid weight loss while other species continued to lose weight gradually to the end. *E. bauhinae* and *G. postica* cocoon shells had the highest and lowest total weight losses of 97.4 and 75.5%, respectively.

The SEM images in Figure 19(a-e) showed the cocoon shells after heat exposure. *A. mimosae*, *A. panda* and *E. bauhinae* decomposed cocoon discs partially maintained the fiber appearance though decomposition was significant, while *B. mori* and *G. postica* cocoon discs were completely decomposed and lost their integrity in the process.

Table 13: Weight loss of African wild and *Bombyx mori* degummed silk fibers and cocoon shells after TG analysis (Mean  $\pm$  SE)

Species	Dehydration (%)		Decomposition (%)		Total weight loss (%)	
	Cocoon	Fibers	Cocoon	Fibers	Cocoon	Fibers
	shells		shells		shells	
<i>Anaphe panda</i>	9.9 $\pm$ 0.5 <sup>b</sup>	11.1 $\pm$ 0.4 <sup>b</sup>	52.0 $\pm$ 0.1 <sup>b</sup>	51.5 $\pm$ 0.3 <sup>b</sup>	91.3 $\pm$ 0.1 <sup>b</sup>	85.9 $\pm$ 4.0 <sup>a</sup>
<i>Argema mimosae</i>	11.9 $\pm$ 0.1 <sup>a</sup>	12.8 $\pm$ 0.0 <sup>a</sup>	61.2 $\pm$ 0.5 <sup>a</sup>	59.2 $\pm$ 1.9 <sup>a</sup>	74.9 $\pm$ 0.5 <sup>c</sup>	71.8 $\pm$ 1.0 <sup>b</sup>
<i>Epiphora bauhiniae</i>	11.8 $\pm$ 0.1 <sup>a</sup>	11.9 $\pm$ 0.0 <sup>b</sup>	46.5 $\pm$ 0.3 <sup>d</sup>	47.2 $\pm$ 1.2 <sup>c</sup>	97.2 $\pm$ 0.1 <sup>a</sup>	87.3 $\pm$ 2.3 <sup>a</sup>
<i>Gonometa postica</i>	11.5 $\pm$ 0.8 <sup>a</sup>	13.3 $\pm$ 0.4 <sup>a</sup>	50.4 $\pm$ 1.1 <sup>c</sup>	53.1 $\pm$ 1.4 <sup>b</sup>	71.2 $\pm$ 1.5 <sup>d</sup>	77.3 $\pm$ 3.4 <sup>b</sup>
<i>Bombyx mori</i>	9.8 $\pm$ 0.1 <sup>b</sup>	8.5 $\pm$ 0.3 <sup>c</sup>	49.5 $\pm$ 0.2 <sup>c</sup>	54.6 $\pm$ 0.3 <sup>b</sup>	95.1 $\pm$ 0.4 <sup>a</sup>	93.4 $\pm$ 2.4 <sup>a</sup>

Means followed by the same letter in the same column are not statistically significant ( $P < 0.05$ ) according to Least Significant Difference (LSD) test

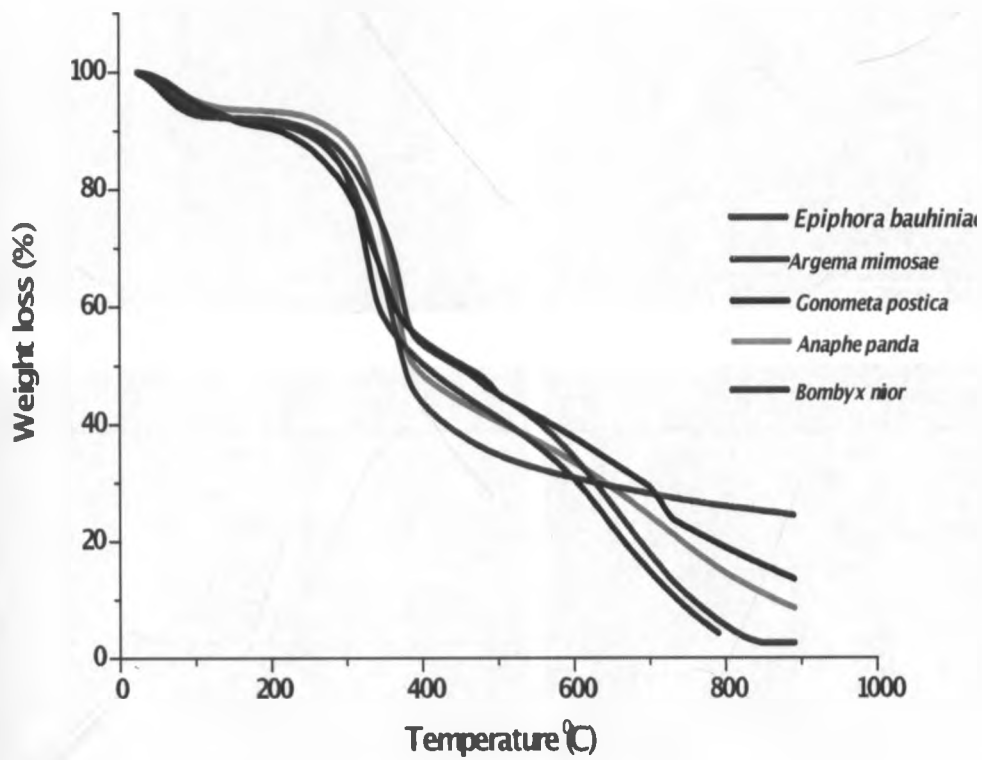


Figure 18: TGA curves for cocoon shells of African wild and *Bombyx mori* silkmoths

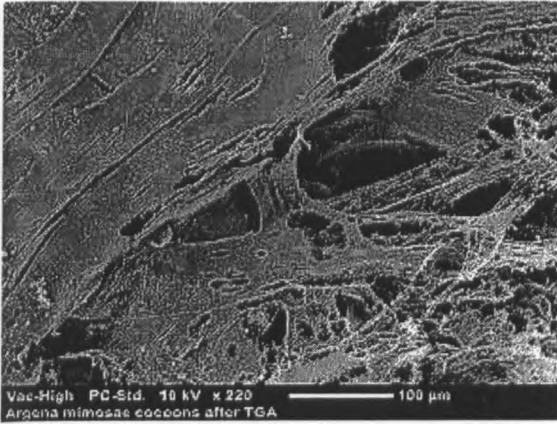
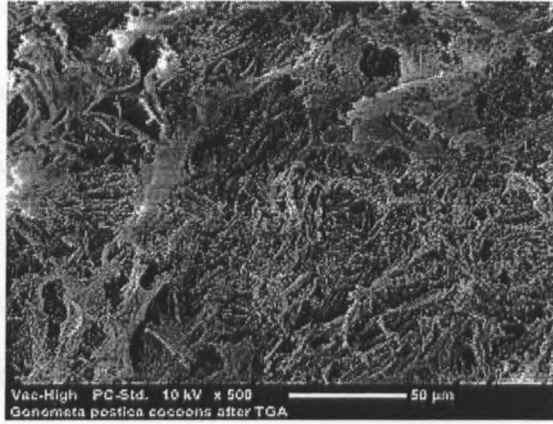
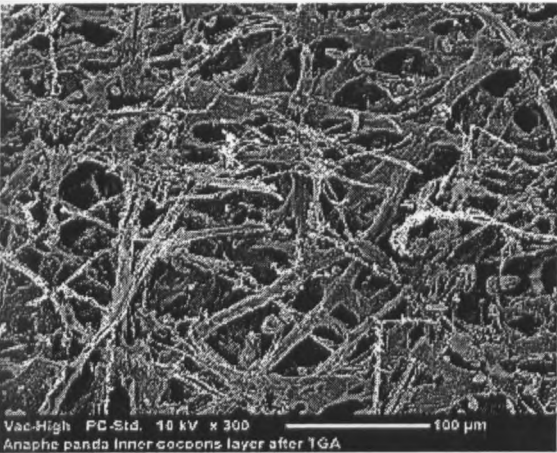
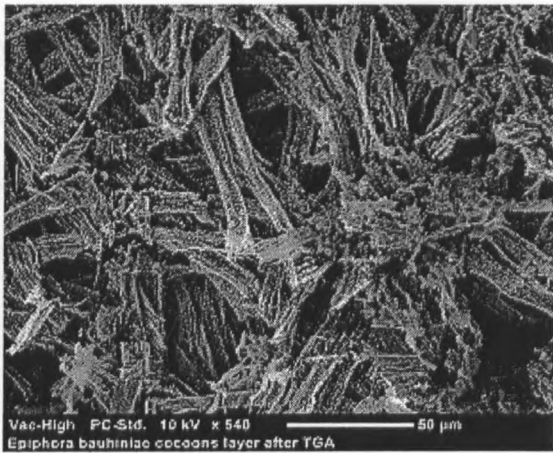
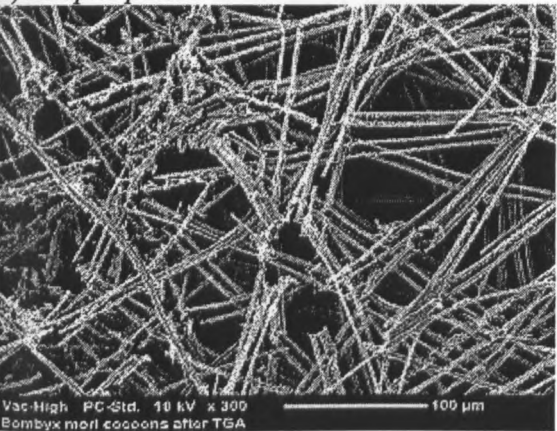
a) *Argema mimosae*b) *Gonometa postica*c) *Anaphe panda*d) *Epiphora bauhiniae*e) *Bombyx mori*

Figure 19: SEM micrographs of cocoon shells discs of African wild and *Bombyx mori* silkmoths after TG analysis

#### 8.3.4. Thermal degradation behaviour of degummed fibers

The TGA curves in Figure (20) showed the weight losses from degummed fibers. Initial weight losses due to dehydration of the fibers occurred rapidly up to 100, 107, 112, 100, and 107°C for *B. mori*, *E. bauhiniae*, *A. mimosae*, *A. panda* and *G. postica*, respectively. The dehydration loss was the highest for *G. postica* (13.3%) and the lowest for *B. mori* fibers (8.5%) (Table 13). Major decomposition of degummed fibers commenced at 303, 301, 292, 312 and 290°C for *B. mori*, *E. bauhiniae*, *A. mimosae*, *A. panda* and *G. postica*, respectively. Unlike the cocoons, *B. mori* fibers were slightly more thermally stable than most of the wild silk fibers. The weight loss after the rapid decomposition was the highest in *A. mimosae* (59.2%) and the lowest in *E. bauhiniae* (47.2%) (Table 13). The multistep thermal degradation of *G. postica* cocoon shells could not be observed in degummed fibers. *B. mori* fibers had the highest total weight loss (93.4%), though it is not significantly different from other species except *A. mimosae* and *G. postica*.

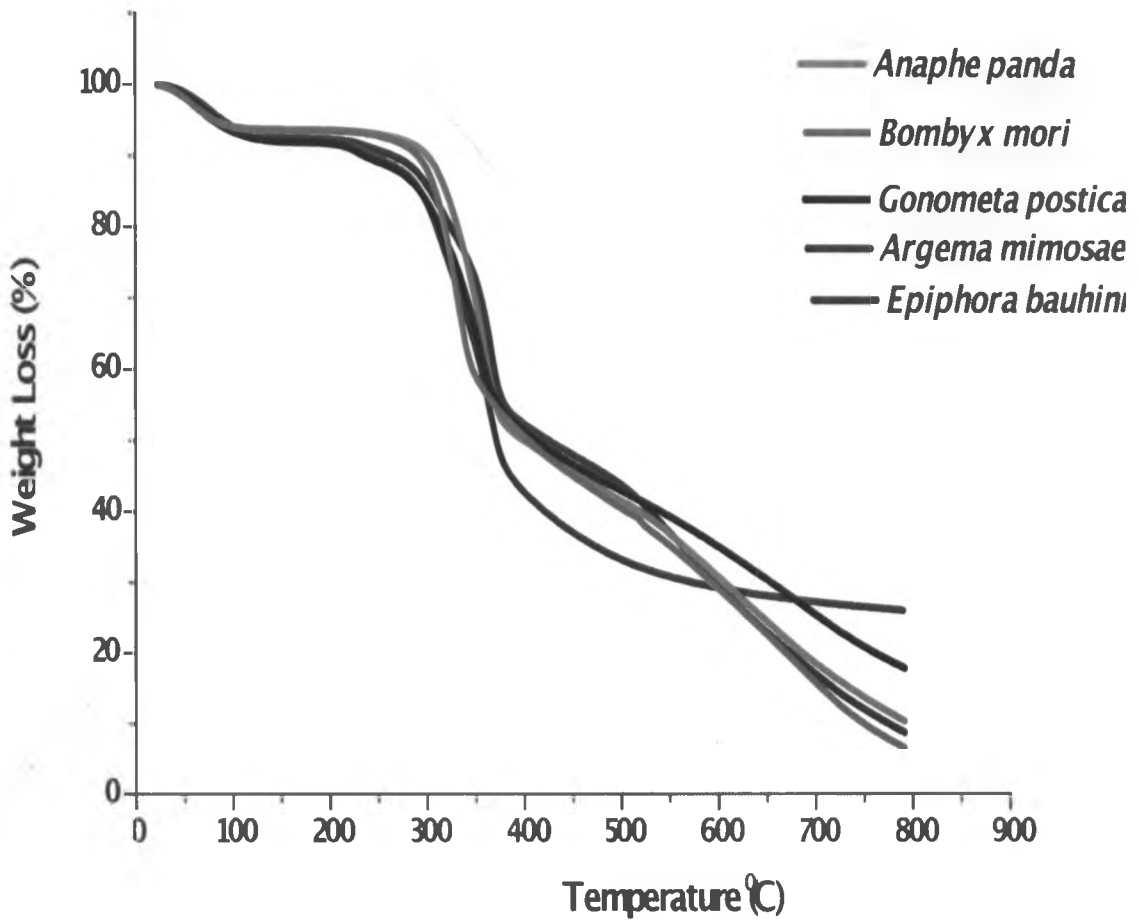


Figure 20: TGA curves of African wild and *Bombyx mori* degummed silk fibers



The SEM images in Figure 21(a-e) showed degummed fibers maintained their shape in *A. mimosae*, *A. panda* and *E. bauhiniae* while *B. mori* and *G. postica* fibers were completely decomposed and lost their integrity in the process. In *A. mimosae* and *E. bauhiniae*, the broken individual fibrils became more exposed and were easily seen after the heat treatment (Fig 22a-b). Rapid decomposition occurred at slightly higher temperature for the cocoon shells than the degummed fibers in all the African wild silks except for *B. mori* (Fig 23).

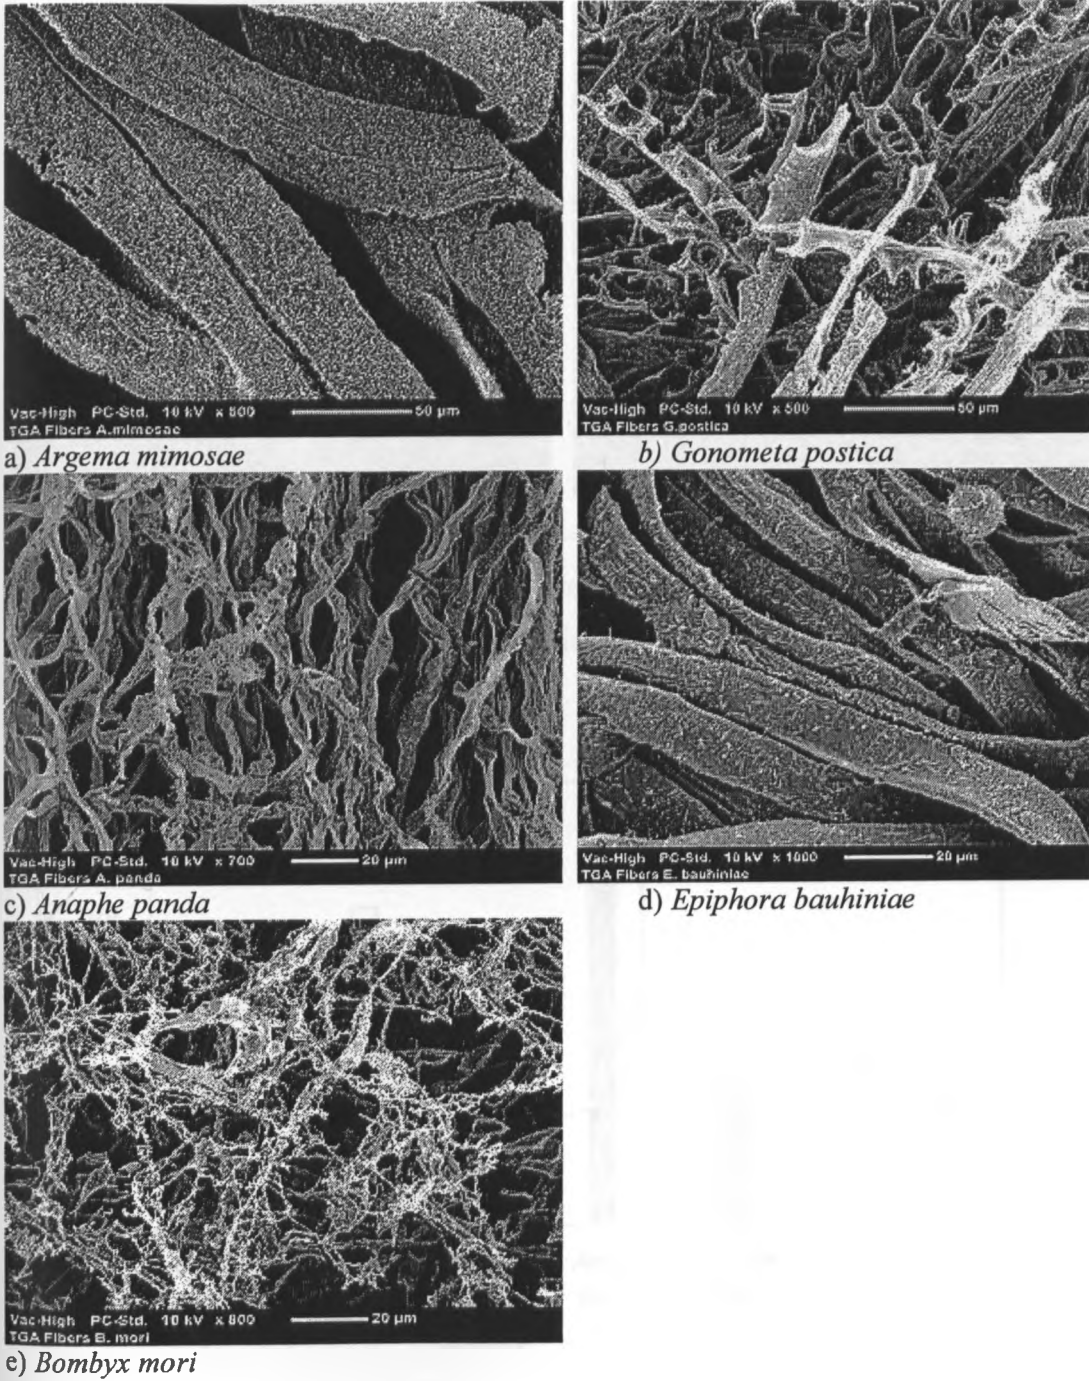


Figure 21: SEM micrographs of African wild and *Bombyx mori* degummed silk fibers after TG analysis

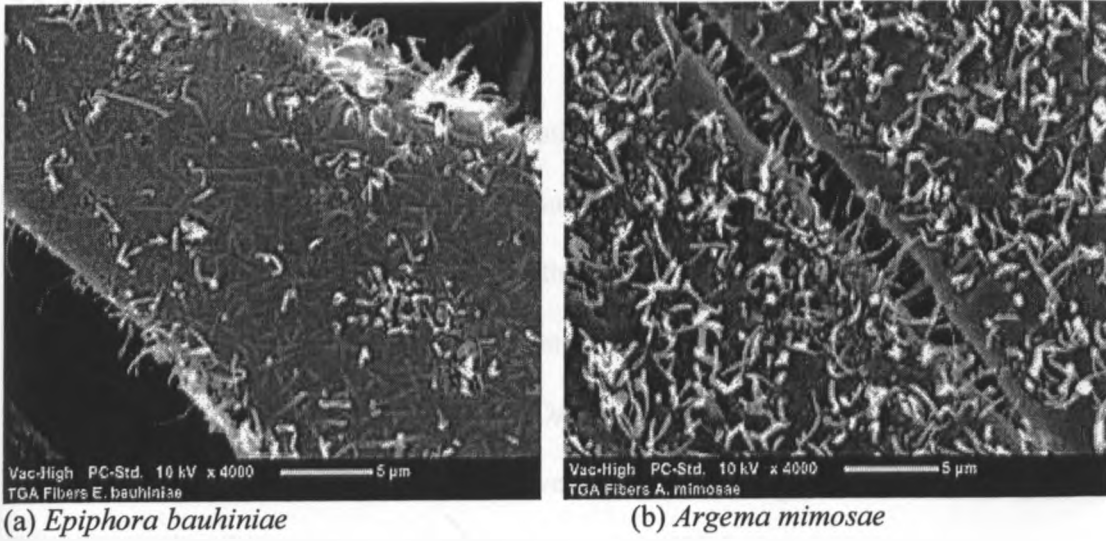


Figure 22: High magnification SEM micrographs of *Argema mimosae* and *Epiphora bauhiniae* fibers after TG analysis

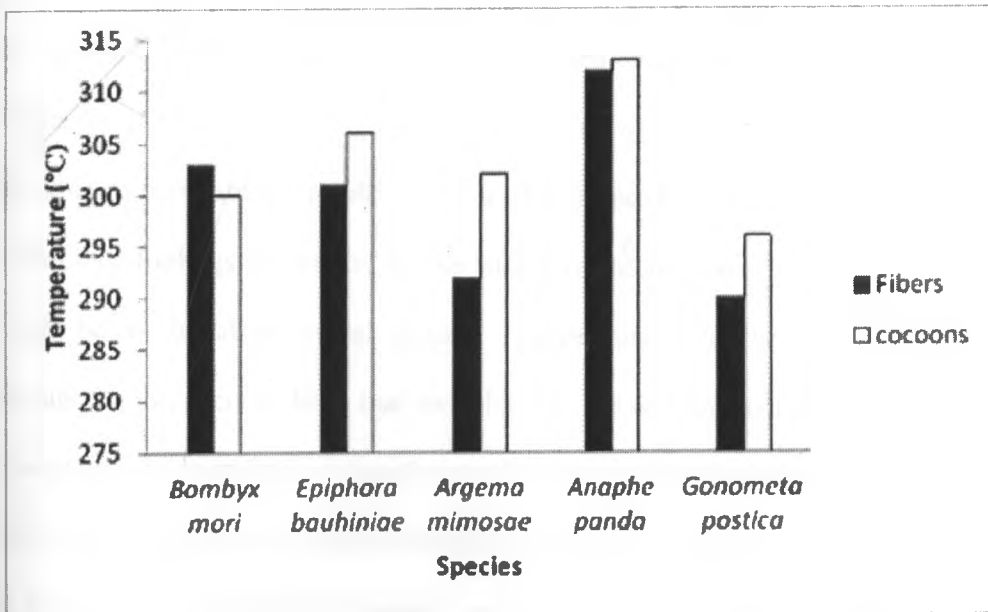


Figure 23: Decomposition on-set temperatures for cocoon shells and degummed fibers of African wild and *Bombyx mori* silks

#### 8.4. DISCUSSION

The results demonstrated the existence of distinct variations in the mechanical properties and thermal degradation behaviours among the four Africa wild silk cocoon shells and degummed fibers. The stress-strain curves, which relate the applied stress to the resulting strain, revealed that each species has its own unique stress-strain response. This has also been reported for other mulberry and non-mulberry varieties (Das *et al.*, 2005; Rajkhowa *et al.*, 2000). *B. mori* and *A. panda* fibers showed absence of a well-defined yielding point and strain-hardening region suggesting the presence of well-developed crystalline regions that are responsible for smaller and gradual elongation with increasing stress (Sen and Babu, 2004b). Other studies reported higher tensile modulus and tensile strength for the normal compact cocoons (0.66GPa and 53.98MPa, respectively) which is inconsistent with the findings here (Huang *et al.*, 2008). However, Zhao *et al.* (2005) reported comparable tensile modulus and breaking strain for *B. mori* compact cocoon shells tested along longitudinal directions. It was not possible to correlate the results of the tensile properties for the African wild cocoon shells with other findings. However, the variations in the measured data for these cocoon shells might be attributed to several reasons. The irregular silk fiber arrangement and wrinkles throughout the cocoon shells that are related to the environmental conditions during cocoon formation and drying play a significant role in determining the cocoon properties. In addition, the variation in cocoon thickness, and the entire spinning process might also have contributed to the observed differences. The main reason for poor mechanical properties in cocoon shells of *G. postica* might be the presence of calcium oxalate crystals combined with the high gum

contents leading to easy rupture and weak bonding between the fibers as can be evidenced from the SEM micrographs of the fractured surfaces.

The study also revealed that *A. panda* and *E. bauhiniae* silk fibers have comparable mechanical properties to the commercial standard, *B. mori*. The typical silk from *B. mori* cocoon has a tensile strength of about 0.5GPa, breaking strain of 15–22%, and tensile elastic modulus 7–17GPa (Gosline *et al.*, 1999; Hakimi *et al.*, 2007). Thus, for *B. mori*, the present findings match consistently with previous results. In most of the results, the wild silk fibers showed non-significant difference in the measured tensile properties. Sen and Babu (2004b) reported that average breaking extension values are greater for non-mulberry varieties (21-24%, 23-30% and 17-24% for Muga, Eri and Tasar silks, respectively) than *B. mori* (12 - 15%). However, in this study most of the wild silk fibers had lesser breaking elongation than *B. mori*. Lucas *et al.*, 1955 reported that *Saturniidae* silks have lower values of the elastic modulus and larger extensibility when compared with the *Thaumetopoeidae*, which is also found to be true in this study. The morphological defects such as partial silk fibroin rupture observed in *G. postica* fibers can also be a possible cause for the drop of the tensile strength. Mechanical properties are also found to be influenced by the fiber denier (Iizuka *et al.*, 1993). Longer period of boiling the cocoons (1.5-5 hours) with alkaline solution might have also affected the mechanical properties of the African wild silk fibers. Reduced proportion of the simple amino acids found in wild silk fibroins which is related to the crystalline fraction, is likely to lead to a more compliant material, and the larger amorphous fraction explains the increase in extensibility. The fracture properties of silk fibers are poorly reproducible and

governed by microstructural defects rather than by intrinsic limitations of the silk polymer (Pe' rez-Rigueiro *et al.*, 2000).

The study further showed that permanent decomposition of cocoon shells started very early for *B. mori* making the African wild cocoons thermally relatively more stable. The wild cocoon shells had higher temperature for dehydration, which suggests the presence of highly adsorbed water molecules (intrinsic structural water) and the variation in chemical composition of constituent proteins. The high heat stability of the cocoon shells contributes as self-thermoregulation structure and helps to avoid severe dehydration except under extreme environmental conditions. In previous studies, similar results were reported for *B. mori* cocoon shells exhibiting dehydration and decomposition losses at 98 and 280°C, respectively (Zhang *et al.*, 2002). They also suggested that the substantial weight decrease is due to the oxidation and cleavage reaction of the -OH chain of the silk fibers. The multistep decomposition of *G. postica* cocoon shells could be due to the presence of calcium oxalate crystals on their surface. *A. pernyi* silk fibers and other silks belonging to the Family *Saturniidae* also undergo several steps of decomposition due to the difference in polymorphs of crystalline structure and amino acid composition (Kweon *et al.*, 2000). The absence of change in structure of *A. mimosae* and *E. bauhiniae* fibers after thermal treatment might be due to the compactness of the fiber discs during the sample preparation process. In conclusion, silks produced by African wild silkmoths revealed properties that have considerable promise for commercial applications.

## CONCLUSIONS AND RECOMMENDATIONS

### GENERAL CONCLUSIONS

The main focus of the study was to determine the extent of variability in structure, composition and properties of silk cocoon shells and fibers produced by four African wild silkmoths with a view to understand and maximize their ecological and economic benefits. The following conclusions can be made from the results of the study.

1. The macro- and microscopic structures of the cocoons and fibers of the African wild silkmoths vary considerably. The cocoons are endowed with structures such as spines and hairs (*A. panda* and *G postica*), holes/perforations (*A. mimosae*), calcium oxalate crystals (*G. postica* and *E. bauhiniae*) and peduncle (*E. bauhiniae*), which aid them in adopting and overcoming specific environmental and biological constraints.
2. All the cocoon shell surfaces are rough and intact with highly cross-linked fibers held together in pairs by sericin gum, other components (tannins) and impurities. The arrangement of the fibers in all the cocoon shells lack uniformity throughout the outer surface and show great cross bindings and networking of twisting filaments in different shapes and forms. The African wild silk fibers have larger and numerous voids that play a significant role in chemical modifications and result in marked increase in cross section. Such physical properties and structures of cocoons affect the methods and ease of processing, and hence, determine the value of the cocoons as source of textiles fibers as well as use in other applications.

4. Fibroins have high proportions of the amino acids, glycine, alanine, and serine representing more than 71 and 82% of the total amino acids present in wild and *B. mori* silks, respectively. The African wild silk fibroins have higher amounts of amino acids with hydrophilic side groups, which are correlated with their high moisture regain properties than *B. mori*.

5. There is a significant difference in weight loss and moisture regain of cocoon shells and shell layers after boiling-off. However, the moisture regain of degummed wild silk fibers was not significantly different among the species. Degummed fibers have higher moisture regain ability than cocoon shells. Inner cocoon layers have higher moisture regain while outer layers have higher weight loss percentages. The observed variation in the properties of cocoon layers suggests the need for separate degumming of layers in contrast to the usual practise of mass boiling if that were practically possible. The results also suggest the need for selection of custom-built degumming techniques for each type of silk in order to optimize quality and quantity of fibers that can be drawn from the different cocoon shells.

6. There is a significant difference in dissolution properties of cocoons and fibers produced by the African wild silkmths. Degummed fibers dissolve more readily than cocoons in all the solvents used. African wild silk cocoons and fibers are less soluble than *B. mori*. *Gonometa postica* cocoons and degummed fibers have the highest solubility (37.3 and 51.7%, respectively) among the wild silks. Lithium bromide is the most effective dissolving agent for both cocoons and fibers (41.2 and 84.5%, respectively).



7. African wild cocoons and fibers have significant variations in tensile properties. *A. mimosae* and *G. postica* cocoons have higher initial moduli and tensile strains at maximum stress than *B. mori*. *B. mori* cocoons have significantly higher maximum stress at break (101MPa), and breaking energy (20J/cm<sup>3</sup>). Fiber pull-out and breakage (debonding) are the dominant fracture mechanisms in cocoon shells. Degummed fibers of *G. postica* have the highest breaking energy (76.4J/cm<sup>3</sup>) and breaking strain (41.3%). *B. mori* has the highest breaking stress than the wild silk fibers (427.6MPa) though it was not statistically significant with *A. panda* and *A. mimosae*. The stress-strain curves of *A. mimosae*, *E. bauhiniae* and *G. postica* fibers show sigoidal shape with an initial linear elastic region, yield region, and hardening regions.

8. The African silks undergo thermal degradation when exposed to heat sources. Permanent degradation starts relatively earlier for *B. mori* making most of the African wild silk cocoons thermally more stable. Degummed fibers of African wild silks also showed comparable heat resistance as *B. mori*. Such relatively higher thermal resistance by the wild fibers make them convenient candidate to use as fiber-insulators up to their decomposition limits.

9. Although *B. mori* and wild silks are both class of natural proteins, their overall properties are different that can be attributed to the selection pressures put forth over time and cocoon shells have maintained these specific and General features to best suit their unique demands placed upon them.

## RECOMMENDATIONS

Wild silkmoths produce commercially important silk and are found distributed along wide range of agro-ecologies in many parts of Africa. They feed primarily on variety of readily available food plants in tropical forests and woodlands. They are known to hold promise in contributing for livelihood and improving the socio-economic status of farm families. Wild silk production could diversify rural people's economy base, and therefore, encourage them to be allied with the current world efforts in enhancing conservation-based development. However, lack of information among farmers and policy makers on economic value of wild silk production coupled with absence of quality standards based on proper properties measurements hindered wide scale silk production in Africa. Accordingly, the following recommendations can be made in relation to the results of the study;

1. The existence of information on diversity in properties and structure revealed among African wild silks can further be exploited to design specific economic and conservation projects and enhance the contribution of wild silk production to the development of a sustainable natural environment, which is under threat due to rapid industrialization, population growth and other man made hazards.
2. The information Generated on silk structure and property relationship should be utilized in broadening its application in fields other than textile. Further studies to test the significance and application of the properties identified should also be initiated to introduce African wild silkmoths to the international market. Moreover, the value of silk types when

compared across taxa should be based on suitability of fiber properties as well as silk potential products.

## REFERENCES

- Acharya, C., S. K Ghosh and S. C. Kundu, 2008. Silk fibroin protein from mulberry and non-mulberry silkworms: cytotoxicity, biocompatibility and kinetics of L929 murine fibroblast adhesion. *Journal of Materials Science: Materials in Medicine.*, 19: 2827–2836.
- Ajisawa, A., 1998. Dissolution of silk fibroin with calcium chloride-ethanol aqueous solution, *Journal of Sericulture Science of Japan*, 67: 91-94.
- Akai, H., 1977. Anti-bacterial function of natural silk materials. *Int. J. Wild Silkmoth Silk* 3: 79–81.
- Akai, H., 2000. Cocoon filament characters and post-cocoon technology. *International Journal of Wild Silkmoths and Silk*, 5: 255-259.
- Akai, H., and T. Nagashima, 2003. Calcium Crystals of Cocoon Shell from African *Gonometa* Silkmoth (Lasiocampidae). *International Journal of Wild Silkmoths and Silk*, 1-5.
- Akai, H., M. Kiuchi and T. Tamura, 1991. Ultrastructure of Silk Glands and Cocoon Filaments of Wild Silkmoths. in: *Antheraea yamamai* and *Antheraea pernyi*, Wild Silkmoths '88, Akai, H. and Z.S. Wu, (Eds.). *International Society of Wild Silkmoths*, Tsukuba, Japan. : 9-23.
- Akai, H., and T. Nagashima, 1999. Fine structural characteristics of *Anaphe* cocoon filament. *International Journal of Wild Silkmoths and Silk*, 4: 13-16.
- Altman, G. H., F. Diaz, C. Jakuba, T. Calabro, R. L. Horan, J. Chen, H. Lu, J. C. Richmond, and D. L. Kaplan, 2003. Silk-based biomaterials. *Biomaterials*, 24: 401–416.
- Alessandrino, A., B. Marelli, C. Arosio, S. Fare, and M. C. Tanzi, and G. Freddi, 2008. Electrospun Silk Fibroin Mats for Tissue Engineering, *Engineering in Life Sciences*, 8 (3): 219–225.

- Amiraliyan, N., M. Nouri, and M H. Kish, 2009.** Effects of some electrospinning parameters on morphology of natural silk-based nanofibers, *Journal of Applied Polymer Science*; 113 (1): 226 – 234.
- Arami, M., R. Sharam, L. Mivehie, F. Mazaheri, and M. N. Mohammad, 2007.** Degumming of Persian silk with mixed proteolytic enzymes, *Journal of Applied Polymer Science*, 106 (1): 267–275.
- Aruga, H., 1994.** Principles of Sericulture. A.A. Balkema, Rotterdam. 376.
- Arunkumar, K. P., M. Metta and J. Nagaraju, 2006.** Molecular phylogeny of silkmoths reveals the origin of domesticated silkmoth, *Bombyx mori* from Chinese *Bombyx mandarina* and paternal inheritance of *Antheraea proylei* mitochondrial DNA. *Molecular Phylogenetics and Evolution*, 40: 419-427.
- Ashiru, M. O., 1988.** Determination of the number of instars of the silkworm *Anaphe venata* Butler (Lepidoptera:Notonidae ). *Insect Science Application*, 9 (3): 405-410.
- Blackledge, T. A., C. Boutry, S. C. Wong, A. Baji, A. Dhinojwala, V. Sahni, and I. Agnarsson, 2009.** How super is super-contraction? Persistent versus cyclic responses to humidity in spider dragline silk. *Journal of Experimental Biology*, 212: 1981-1989.
- Buschle-Diller, G., 2010.** Substrates and their structure, In: A. Cavaco-Paulo and G. M. Gubitz (Eds): Textile Processing with enzymes, CRC Press, USA, 2003.
- Case, S. T., and L. Wieslander, 1992.** Secretory proteins of chironomus salivary glands: structural motifs and assembly characteristics of a novel biopolymer. *Results Probl Cell differ.* 19: 187-226.
- Cavaco-paulo, A., and G. M. Gubitz, 2003.** Textile Processing with Enzymes. CRC Press, USA.
- Cave, C., 1998.** School of Fisheries. University of Washington, Chamisa.freeshell.org (Sept. 10, 2010, 2:05pm).
- Chapman, R. F., 1998.** The Insect Structure and Function. 4th ed. Cambridge University Press, UK.

- Chen, X., Z. Z. Shao, N. S. Marinkovic, L. M. Miller, P. Zhou, and M. R. Chance, 2001.** Conformation transition kinetics of regenerated *Bombyx mori* silk fibroin membrane monitored by time-resolved FTIR spectroscopy. *Biophysical Chemistry*; 89: 25 – 34.
- Cheung, H., 2009.** Study on the mechanical properties of different silkworm silk fiber, *Journal of Composite Materials*, 43 (22): 2521-2531.
- Cheung, H., K. Lau, Y. Zhao, and J. Lu, 2008.** Tensile properties of different silkworm silk fibers, *Advanced Materials Research*, 47 (50): 1213 – 1216.
- Chikwenhere, G.P., 1992.** Distribution and abundance of the African silk moth (*Gonometa rufobrunnae*) in Matebeleland province of Zimbabwe. *Zimbabwe Journal of Agricultural Research*, 29: 133-137.
- Chopra, S., and M. L. Gulrajani, 1994.** Textile Fibers, *Indian Journal of Textile Research*, 19: 76-85.
- Choundhury, A. K. R., 2006.** Textile Preparation and Dyeing. Science Publishers, ISBN: 1-57808-402-1, Enfield, NH, USA.
- Clotuche, G., G. L. E Goff, A. C. Mailleux, J. L Deneubourg, C. Detrain, and T. Hance, 2009.** How to Visualize the Spider Mite Silk? *Microscopy Research and Technique* 72: 659–664.
- Common, I. F. B., 1990.** Moths of Australia. Melbourne University Press, Carlton, Victoria, Australia
- Craig, C., 1997.** Evolution of arthropod silks. *Annual Reviews of Entomology*, 42: 231-267.
- Craig, C., 2003.** Spider Web and Silks: Tracing Evolution from Molecules to Genes to Phenotypes. Oxford University Press, Oxford, New York.
- Craig, C., 2008.** Wild Silk Production to Alleviate Poverty and Preserve the Biodiversity of the Makira Protected area, Madagascar, <http://www.ruffordsmallgrants.org/rsg/projects> (Nov. 7/2010, 09:27pm)
- Craig, C., and C. Riekel, 2002.** Comparative architecture of silks, fibrous proteins and their encoding genes in insects and spiders. *Comparative Biochemistry and Physiology, B* 133: 493–507.

- Craig, C., H. Michael, D. Kaplan, and N. E. Pierce, 1999.** A comparison of the composition of silk proteins produced by spiders and insects *International Journal of Biological Macromolecules*, 24: 109 – 118.
- Cunniff, P. M., S. A. Fossey, M. A. Auerbach, J. W. Song, D. L. Kaplan, W. W. Adams, R. K. Eby, D. Mahoney, and D. L. Vezie, 1994.** Mechanical and thermal properties of dragline silk from the spider *Nephila clavipes*, *Polymers for Advanced Technologies*, 5 (8): 401 – 450.
- Danks, H. V., 2004.** The role of insect cocoons in cold conditions. *European Journal of Entomology*, 101: 433 - 437.
- Das, S., 1992.** Mulberry and Non mulberry silks. *The Indian textile Journal*, 102 (12): 42 - 46.
- Das, S., and A. Ghosh, 2010.** An investigation on the progressive change in filament characteristics from outer to inner layers of mulberry and tasar cocoons. *Journal of Applied Polymer Science*, 117: 1319 – 1324.
- Das, S., R. Chattopadhyay, M. L. Gulrajani and K. Sen, 2005.** Study of property and structural variants of mulberry and tasar silk filaments, *autex Research Journal*, 5 (2): 81 - 86.
- Dash, R., C. Acharya, P. C. Bindu and S. C. Kundu, 2008.** Antioxidant potential of silk protein sericin against hydrogen peroxide-induced oxidative stress in skin fibroblasts. *BMB reports*, 41 (3): 236 - 241.
- Dash, R., S. K. Ghosh, D. L. Kaplan, and S. C., Kndu, 2007.** Purification and biochemical characterization of a 70kDa from tropical tasar silkworm , *Antheraea mylitta*. *Comparative biochemistry and physiology. Part B, Biochemistry and Molecular Biology*, 147: 129 - 134.
- Dash, R., S. Mukherjee, and S. C. Kundu, 2006.** Isolation, purification and characterization of silk protein sericin from cocoon peduncles of tropical tasar silkworm, *Antheraea mylitta*, *International Journal of Biological Macromolecules*, 38 (3-5): 255 - 258.
- Datta, R. K., and M. Nanavaty, 2007.** Global Silk Industry. S. B. Nangia. A P H Publishing Corporation, New Delhi.

- Delport, W., 2006.** Population genetic inference of demographic processes in the African wild silk moth, *Gonometa postica* (Lasiocampidae). Ph D thesis University of Pretoria.
- Dhavalikar, R. S., 1962.** Amino acid composition of Indian silk fibroins and sericins. II. Sericins., *Indian J. Sci. Ind. Res.*, 21(C): 261 - 263.
- Dingle, J. G., E. Hassan, M. Gupta, D. George, L. Anota, and H. Begum, 2005.** Silk production in Australia, A Report for Rural Industries research and Development Corporation, 113p.
- Edgerly, J. S., and E. Rooks, 2004.** Lichens, sun and fire: a search for an embiid-environment connection in Australia (Order Embiidina: Australembiidae and Notoligotomidae). *Environmental Entomology*, 33: 907 – 920.
- Engster, M. S., 1976.** Studies on silk secretion in the trichoptera (F. Limnephilidae), *Cell Tissue Research*; 169 (1): 77 - 92.
- Fang, Q., D. Chen, Z. Yang, and M. Li, 2009.** *In-vitro* and *in-vivo* research on using *Antheraea pernyi* silk fibroin as tissue engineering tendon scaffolds. *Materials science and Engineering C. Biomimetic and Supramolecular Systems*, 29: 1527 - 1534.
- FAO (Food and Agriculture Organization of the United Nations), 2003.** Conservation Status of Sericulture Germplasm Resources in the World - II. Conservation Status of Silkworm (*Bombyx Mori*) Genetic Resources in the World, Rome.
- Fedic, R., M. Zurovec, and F. Sehnal, 2003.** Correlation between fibroin amino acid sequence and physical silk properties. *The Journal of biological chemistry*, 278: 35255 – 35264.
- Fening, K. O., E. N. Kioko, S. K. Raina and J. M. Mueke, 2008.** Monitoring wild silkmoth, *Gonometa postica*, Walker, abundance, host plant diversity and distribution in Imba and Mumoni woodlands in Mwingi, Kenya. *The International Journal of Biodiversity Science and Management*, 4: 104 - 111.
- Ferrar, P., 1980.** Cocoon formation by Musidae (Diptera). *J. Aust. Ento. Soc.* 19: 171 - 174.



- Freddi, G., A. Bianchi Svilkos, H. Ishikawa, and M. Tsukada, 1993.** Chemical composition and physical properties of *Gonometa rufobrunnea* silk. *Journal of Applied Polymer Science*, 48: 99 – 106.
- Freddi, G., Y. Gotoh, T. Mori, I. Tsutsui, and M. Tsukada, 1994.** Chemical structure and physical properties of *Antheraea assama* silk. *Journal of Applied Polymer Science*, 52 (6): 775 – 781.
- Furuhata, K., A. Okada, Y. Chen, Y. Y. Xu and M. Sakamoto, 1994.** Dissolution of silk fibroin in lithium halide/organic amide solvent systems, *Journal of Sericulture Science of Japan*, 63 (4): 315 - 322.
- Fut, C., D. Porter and Z. Shao, 2009.** Moisture effects on *Antheraea pernyi* silk's mechanical property. *Macromolecules*, 42: 7877 – 7880.
- Fuzek, J. F., 1985.** Absorption and desorption of water by some common fibers. *Journal of Industrial and Engineering Chemistry Product and Research Development*, 24: 140 – 144.
- Gamo, T., T. Inokuchi, and H. Laufer, 1977.** Polypeptides of fibroin and sericin secreted from the different sections of silk gland in *B. mori*. *Insect Biochemistry*, 7: 285 - 295.
- Gary, E. W., and B. L. Gary, 2008.** *Encyclopedia of biomaterials and biomedical engineering*, 4, second ed.
- Gellynck, K., 2006.** Silk and Spider Silk in Tissue Engineering, Ph.D thesis, University of Ghent, Belgium.
- Gellynck, K., P. Verdonk, R. Forsyth, K. F. Almqvist, E. Van Nimmen, T. Gheysens, J. Mertens, L. Van Langenhove, P. Kiekens, and G. Verbruggen, 2008.** Biocompatibility and biodegradability of spider egg sac silk. *Journal of Materials in Science: Materials in Medicine*, 19: 2963 - 2970.
- Gheysens, T., A. Collins, S. K. Raina, F. Vollrath and D. Potter, 2011.** Demineralization enables reeling of wild silkmoth cocoons. *Biomacromolecule* 12 (6): 2257-2266.
- Gosline, J. M., M. E. Demont, and M. Denny, 1984.** The structure and properties of spider silks. *Endeavour*, 10: 37 – 43.

- Gosline, J. M., P. A. Guerette, C. S. Ortlepp, and K. N. Savage, 1999.** The mechanical design of spider silks: from fibroin sequence to mechanical function. *Journal of Experimental Biology*, 202: 3295 -3303.
- Gowdey, C. C., 1953.** On the utilization of an indigenous African silk worm (*Anaphe infracta*) in Uganda. *Bulletin of Entomological Research*, 3: 269-274.
- Gulrajani, M. L., 1988.** Degumming of Silk. In: Silk Dyeing Printing and Finishing, Gulrajani, M.L., (Ed.). Department of Textile Technology Indian Institute of Technology, New Delhi, pp: 63 - 95.
- Gulrajani, M. L., 2006.** Sericin- A bio-molecule of value. *Indian Silk*, 45 (2): 16 - 22.
- Hakimi, O., D. Knight, F. Vollrath, and P. Vadgama, 2007.** Spider and mulberry silkworm silks in “*Bio-engineered Composites*” of Composites Part B: *Engineering*. 38 (3): 324 - 337.
- Hardy, J. G., and T. Scheibel, 2009.** Production and Processing of Spider Silk Proteins, *Journal of Polymer Science: Part A: Polymer Chemistry*, 47: 3957 – 3963.
- Hartland-rowe, R., 1992.** The biology of the wild silk moth *Gonometa rufobrunnea* Aurivillus (Lasiocampidae) in north eastern Botswana, with some comments on its potential as a source of wild silk. *Botswana notes and records*, 24: 123 - 133.
- Herberstein, M. E., C. L. Craig, J. A. Coddington and M. A. Elgar, 2000.** The functional significance of silk decorations of orb-web spiders: a critical review of the empirical evidence. *Biological Reviews of the Cambridge Philosophical Society*, 75 (4): 649 - 669.
- Holland C., A. E. Terry, D. Porter and F. Vollrath, 2006.** Comparing the rheology of native spider and silkworm spinning dope. *Nature materials*, 5.
- Hollen, N., and J. Saddler, 1973.** Textiles. 4th Edition. New York: The Macmillan Company.
- Huang, S. Q., H. P. Zhao, X. Q. Feng , W. Cui, Z. Lin and M. Q. Xu, 2008.** Mechanical properties of cocoons constructed consecutively by a single silkworm caterpillar, *Bombyx mori*, *Acta Mech Sin* 24: 151 – 160.

- Gosline, J. M., P. A. Guerette, C. S. Ortlepp, and K. N. Savage, 1999.** The mechanical design of spider silks: from fibroin sequence to mechanical function. *Journal of Experimental Biology*, 202: 3295 -3303.
- Gowdey, C. C., 1953.** On the utilization of an indigenous African silk worm (*Anaphe infracta*) in Uganda. *Bulletin of Entomological Research*, 3: 269-274.
- Gulrajani, M. L., 1988.** Degumming of Silk. In: Silk Dyeing Printing and Finishing, Gulrajani, M.L., (Ed.). Department of Textile Technology Indian Institute of Technology, New Delhi, pp: 63 - 95.
- Gulrajani, M. L., 2006.** Sericin- A bio-molecule of value. *Indian Silk*, 45 (2): 16 - 22.
- Hakimi, O., D. Knight, F. Vollrath, and P. Vadgama, 2007.** Spider and mulberry silkworm silks in “*Bio-engineered Composites*” of Composites Part B: *Engineering*. 38 (3): 324 - 337.
- Hardy, J. G., and T. Scheibel, 2009.** Production and Processing of Spider Silk Proteins, *Journal of Polymer Science: Part A: Polymer Chemistry*, 47: 3957 – 3963.
- Hartland-rowe, R., 1992.** The biology of the wild silk moth *Gonometa rufobrunnea* Aurivillius (Lasiocampidae) in north eastern Botswana, with some comments on its potential as a source of wild silk. *Botswana notes and records*, 24: 123 - 133.
- Herberstein, M. E., C. L. Craig, J. A. Coddington and M. A. Elgar, 2000.** The functional significance of silk decorations of orb-web spiders: a critical review of the empirical evidence. *Biological Reviews of the Cambridge Philosophical Society*, 75 (4): 649 - 669.
- Holland C., A. E. Terry, D. Porter and F. Vollrath, 2006.** Comparing the rheology of native spider and silkworm spinning dope. *Nature materials*, 5.
- Hollen, N., and J. Saddler, 1973.** Textiles. 4th Edition. New York: The Macmillan Company.
- Huang, S. Q., H. P. Zhao, X. Q. Feng , W. Cui, Z. Lin and M. Q. Xu, 2008.** Mechanical properties of cocoons constructed consecutively by a single silkworm caterpillar, *Bombyx mori*, *Acta Mech Sin* 24: 151 – 160.

- Inoue, S., K. Tanaka, F. Arisaka, S. Kimura, K. Ohtomo and S. Mizuno, 2000. Silk Fibroin of *Bombyx mori* Is Secreted, Assembling a High Molecular Mass Elementary Unit Consisting of H-chain, L-chain, and P25, with a 6:6:1 Molar Ratio, *The Journal of Biological Chemistry*, 275:40517 – 40528.
- Iizuka, E., R. Kawano, Y. Kitani, Y. Okachi, M. Shimizu, and A. Fukuda, 1993. Studies on the physical properties of Indian Non-Mulberry silk I: *Antheraea proylei* Indian *Journal of Sericulture*, 32: 27 – 36.
- Ito, T., J. Xu, and K. Hamano, 1992. Amino acid composition of cocoon shell of the mulberry white caterpillar, *Rondotia menciiana*, and the wild silk worm, *Bombyx mandarina*. *Journal of Sericulture Science of Japan*, 61 (2): 105 - 109.
- Jiang, P., H. Liu, C. Wang, L. Wu, J. Huang, and C. Guo, 2006. Tensile behaviour and morphology of differently degummed silkworm (*Bombyx mori*) cocoon fibers. *Materials Letters* 60: 919 – 925.
- Jin, H. J., and D. L. Kaplan, 2003. Mechanism of silk processing in insects and spiders. *Nature*, 424:1057 – 1061.
- Jolly, M. S., S. N. Chowdhury and S.K. Sen, 1975. Non-Mulberry Sericulture in India. Central Silk Board, Bombay, India.
- Kakati, L. N., and B. C. Chutia, 2009. Diversity and ecology of wild sericigenous insects in Nagaland, India. *Tropical Ecology* 50 (1): 137 - 146.
- Kaplan, D. L., 1998. Fibrous proteins-silk as a model system, *Polymer degradation and stability*, 59: 25 - 32.
- Kaplan, D. L., S. J. Lombardi, and S. A. Fossey, 1991. In *Biomaterials: Novel Materials from Biological Sources*, D. Byrom, Ed., Stockton Press, New York.
- Kaplan, D., W. W. Adams, B. Farmer and C. Viney, 1994. Silk: Biology, structure, Properties and genetics, *ACS symposium Series*, 544: 2 - 16.
- Karumar, S. R., 1999. Chemical Technology in the pre treatment process of textiles. 1<sup>st</sup> Edn., Elsevier Science, New York.
- Kato, H., 1991. Tests for production of blended yarns with anisoshrinking from mori silk and reeled raw threads of wild silks. *Journal of Sericulture Science of Japan*, 60: 432 - 444.

- Kato, H., and T. Hata, 1998.** Degumming and dyeing properties of cocoon filaments with a special feature differed from conventional silkworm races. *Bulletin of the National Institute of Sericultural and Entomological Science*, 20: 101 - 114.
- Kawahara, Y., and M. Shioya, 1999.** Characterization of Microvoids in Mulberry and Tussah Silk Fibers Using Stannic Acid Treatment, *Journal of Applied Polymer Science*, 73: 363 – 367.
- Kerkam, K., C. Viney, D. Kaplan and S. Lombardi, 1991.** Liquid crystallinity of natural silk secretions. *Nature* 349: 596 - 598.
- Ki, C. S., K. H. Lee, D. H. Baek, M. Hattori, I. C. Um, D. W. Ihm, and Y. H. Park, 2007a.** Dissolution and Wet Spinning of Silk Fibroin using Phosphoric acid/Formic acid Mixture Solvent System, *Journal of Applied Polymer Science*, 105: 1605 – 1610.
- Ki, C. S., J. W. Kim, H. J. Oh, K. H. Lee and Y. H. Park, 2007b.** The effect of residual silk sericin on the structure and mechanical property of reGenerated silk filament, *International Journal of Biological Macromolecules*, 41 (3): 346 - 353.
- Kim, E., T. Bayaraa, E. Shin, and C. Hyun, 2009.** Fibroin-Derived Peptides Stimulate Glucose Transport in Normal and Insulin-Resistant 3T3-L1 Adipocytes; *Biological and Pharmaceutical Bulletin*, 32 (3): 427 - 433.
- Kim, H. J., U. Kim, H. Kim, C. Li,, M. Wada, G. G. Leisk, and D. L. Kaplan, 2008.** Bone Tissue Engineering with Premineralized Silk Scaffolds, *Bone*, 42 (6): 1226 – 1234.
- Kioko, E. N., 1998.** Biodiversity of the wild silk moths (Lepidoptera) and their potential for silk production in East Africa. Ph D Thesis, Kenyatta University, Nairobi, Kenya.
- Kojima, K., Y. Kuwana, H. Sezutsu, I. Kobayashi, K. Uchino, T. Tamura, and Y. Tamada, 2007.** A new method for the modification of fibroin heavy chain protein in the transgenic silkworm. *Bioscience, Biotechnology, and Biochemistry*, 71 (21): 2943 - 2951.
- Komatsu, K., 1975.** Studies on dissolution behaviours and structural characteristic of silk Sericin. *Bull. Sericult. Exp. Sta.* 26: 135 - 256.
- Komatsu, K., 1980.** The chemical and structure of wild silks, in N. Hojo (ed.), *Zoku Kenshi no Kozo*, Shinshu University, Ueda: 353 – 377.

- Kumaresan, P., R. K. Sinha and S. R. Urs, 2007.** Sericin-a versatile by-product. *Indian Silk*, 45(12): 11-13.
- Kweon, H. Y., I. C. Um and Y. H. Park, 2000.** Thermal behaviour of reGenerated *Antherraea pernyi* silk fibroin film treated with aqueous methanol, *Polymer*, 41: 7361-7367.
- Kweon, H., S. Woo, and Y. H. Park, 2001.** Effect of Heat Treatment on the Structural and Conformational Changes of ReGenerated *Antherraea pernyi* Silk Fibroin Films, *Journal of Applied Polymer Science*, 81: 2271-2276.
- Lemaire, C., and J. Minet, 1998.** The Bombycoidea and their relatives. In: N.P. Kristensen (ed.) Lepidoptera, Moth and Butterflies. Volume 1: Evolution, Systematics, and Biogeography. Walter de Gruyter, Inc., Hawthome. pp. 321-353.
- Lewis, R. V., 2006.** Spider Silk: Ancient Ideas for New Biomaterials, *Chem Rev*, 106: 3762-3774.
- Li, Y., C. W. M. Yuen, J. Y. Hu, and Y. F. Cheng, 2006.** Analysis of the Structural Characteristics of Nanoscale Silk Particles. *Journal of Applied Polymer Science*, 100: 268-274.
- Li, Y., R. Xia, H. Wang, X. Li, Y. Liu, Z. Wei, C. Lu, and Z. Xiang, 2009.** Construction of a full-length cDNA Library from Chinese oak silkworm pupa and identification of a KK-42-binding protein gene in relation to pupa-diapause termination, *International Journal of Biological Sciences*, 5: 451-457.
- Lin, Y., T. Liou, C. Liu, Y. Liu, T. Wu and Y. Chang, 1993.** An introduction to Taiwan wild silkworms. In: Wild Silkmths '92. *International Society for Wild Silkmths*. Tsukuba. Japan: 105-114.
- Lin, Z., W. Huang, J. Zhang, J. Fan, and D. Yang, 2009.** Solution structure of eggcase silk protein and its implications for silk fiber formation, *PNAS*, 106 (22): 8906-8911.
- Liu, T. L., J. C. Miao, W. H., Sheng, Y. F. Xie, Q. Huang, Y. B. Shan, and J. C. Yang, 2010.** Cytocompatibility of reGenerated silk fibroin film: a medical biomaterial applicable to wound healing. *JZUS-B* 11: 10-16.

- Lombardi, S. J., and D. Kaplan, 1990.** The amino acid composition of major ampullate gland silk (dragline) of *Nephila clavipes* (Araneae, Tetragnathidae). *Journal of Arachnology*, 18: 297–306.
- Lovett, M. L., C. Cannizzaro, L. Daheron, B. Messmer, G. V. Novakovic and D. L. Kaplan, 2007.** Silk fibroin micro-tubes for blood vessel engineering, *Biomaterials*, 28 (35): 5271-5279.
- Lu, P., B. S. Lai, and X. L. Yan, 1998.** Purification and determination of  $\alpha$ -Linolenic acid in silkworm pupa by urea adduction fractionation method. *Chin. J. Pharma. Anal.* 18 (6): 390–393.
- Lucas, F., J. T. B. Shaw and S. G. Smith. 1955.** The chemical constituents of some silk fibroins and its bearing on their physical properties, *Journal of Textile Inst.*, 46: 440-445.
- Lucas, F., J. T. B. Shaw, and S. G. Smith, 1958.** The silk fibroins. In *Advances in Protein Chemistry*, 13, (ed. C. B. Anfinsen, JR.), pp. 107-242.
- Lucas F., and K. M. Rudall, 1968.** In: Florkin M, Stotz EH, 1968. Editors. *Comprehensive Biochemistry*, vol. 26B. Amsterdam: Elsevier, pp. 475–558.
- Lyon, B. E., and R. V. Cartar, 1996.** Functional significance of the cocoon in two arctic *Gynaephora* moth species. *Proc. R. Soc.Lond. (Ser. B, Biol. Sci.)* 263: 1159–1163.
- MacIntosh, A. C., A. Crawford and P. V. Hatton, 2006.** Investigation of Spider Egg Case Silks for Cartilage Tissue Engineering, *European Cells and Materials* 11 (3): 77-89.
- Madsen, B., Z. Z. Shao, and F. Vollrath, 1999.** Variability in the mechanical properties of spider silks on three levels: inter-specific, intra-specific and inter-individual. *International Journal of Biological Macromolecules*, 24: 301–306.
- Mandal, B. B., and S. C. Kundu, 2008.** A Novel Method for Dissolution and Stabilization of Non-Mulberry Silk Gland Protein Fibroin Using Anionic Surfactant Sodium Dodecyl Sulfate, *Biotechnol. Bioeng.* 9: 1482–1489.
- Manjunatha, H. B., R. K. Rajesh, and H. S. Aparna, 2010.** Silkworm thermal biology: A review of heat shock response, heat shock proteins and heat acclimation in the domesticated silkworm, *Bombyx mori*, *Journal of Insect Science*, 10 (204):1-16.

- Mase, K., T. Iizuka, E. Okada, K. Nakajima, Y. Tamura, T. Miyazima and T. Yamamoto, 2008. Breeding of the Silkworm Race "Sericin Flavo" for Production of Sericin Cocoons Containing Flavonol, *Journal of Insect Biotechnology and Sericology*, 77 (3):3171-3174.
- Matsumoto, A., A. Lindsay, B. Abedian, and D. L. Kaplan, 2008. Silk Fibroin Solution Properties Related to Assembly and Structure, *Macromol. Biosci.* 8: 1006–1018.
- Mbahin, N., 2008. The Ecology And Economic Potential Of Wild Silkmoth *Anaphe Panda* (Boisduval) (Lepidoptera: Thaumetopoeidae) In The Kakamega Forest, Thesis Submitted In Fulfillment Of The Requirements For The Award Of The Degree Of Doctor Of Philosophy In Agricultural Entomology, School Of Pure And Applied Sciences, Kenyatta University, Kenya.
- Michalak, M., M. Tszedel, J. Bilska, and I. Krucińska, 2005. Products of Caddis-fly Larvae (*Trichoptera*) Silk Glands as a New Natural Textile Fiber; *Fibers and Textiles In Eastern Europe*, 13 (6) (54): 28-32.
- Miller, J. E., and B. M. Reagan, 1989. Degradation in weighted and unweighted historic silks. *Journal of the American Institute for Conservation*, 28 (2):97 – 115.
- Min, B., L. Jeong, Y. S. Nam, J. Kim, J. Y. Kim, and W. H. Park, 2004. Formation of silk fibroin matrices with different texture and its cellular response to normal human keratinocytes, *International Journal of Biological Macromolecules*, 34 (5): 223-230.
- Minoura, N., M. Tsukada, and M. Nagura, 1990. Physico-chemical properties of silk fibroin membrane as a biomaterial. *Biomaterials* 11: 430-434.
- Mishira, N., N. C. Hazarika, K. Narian, and J. Mahanta, 2003. Nutritive value of non mulberry and mulberry silkworm pupae and consumption pattern in Assam, *India. Nutr. Res.*, 23: 1103-1311.
- Miyaguchi, Y., and J. Hu, 2005. Physicochemical Properties of Silk Fibroin after Solubilization Using Calcium Chloride with or without Ethanol, *Food Sci. Technol. Res.*, 11(1): 37-42.
- Miyashita, T., 1999. Sweat and sebum absorbing cosmetics containing cellulose fibers, Jpn Kokai Tokkyo Koho, *Chem abstract*, 131 (2): 223-271.



- Mondal, M., K. Trivedy and S. N. Kumar, 2007 (a).** The silk proteins, sericin and fibroin in silkworm, *Bombyx mori* Linn.: A review , *Caspian Journal of Environmental Sciences*, 5 (2): 63-76.
- Mondal, M., K. Trivedy and S. N. Kumar, 2007(b).** Scanning electron microscopic study on the cross sections of cocoon filament and degummed fiber of different breeds/hybrids of mulberry silkworm, *Bombyx mori* Linn. *Journal of Entomology.*, 4: 362-370.
- Munro, J. M., 1987.** Cotton. 2nd Edn., John Wiley and Sons, N.Y., USA. pp: 368.
- Nadiger, G. S., N. V. Bhat, and M. R. Padhye, 1985.** Investigation of amino acid composition in the crystalline region of silk fibroin. *Journal of Applied Polymer Science*, 30: 221-225.
- Nagai, N., T. Murao, Y. Ito, N. Okamoto, and M. Sasaki, 2009.** Enhancing Effects of Sericin on Corneal Wound Healing in Rat Debrided Corneal Epithelium, *Biol. Pharm. Bulletin*, 32 (5): 933-936.
- Nagaraju, J., V. Klimenko, and P. Couble, 2001.** The silkworm, *Bombyx mori*: A model genetic system. In: *Encyclopaedia of Genetics*. Edt. Eric C.R.Reeve. Fitzroy Dearborn Publishers, London. pp. 219-239.
- Nakpathom, M., B. Somboon and N. Narumol, 2009.** Papain enzymatic degumming of thai *Bombyx mori* silk fibers. *J. Micr. Soc. Thailand*, 23: 142-146.
- Narumi, T., M. Kobayashi and T. Mori, 1992.** Fine structure of cocoon filament of silkworms. In: Wild Silkmooths '91. *Int. Soc. Wild Silkmooths*. Tsukuba. Japan, 179-185.
- Narumi, T., M. Kobayashi and T. Mori, 1993.** Electron microscopic observations of voids in cocoon filaments of silk-spinning moths. *Journal of Sericulture Science of Japan*, 62: 489-495.
- Narumi, T., and M. Kobayashi, 1995.** A method of morphometry for voids in Saturniidae cocoon filaments using image processing techniques. *Journal of Sericulture Science of Japan*, 64: 203-208.
- Nasreen, A., G. M. Cheema and M. Ashfaq, 1999.** Rearing of silkworm *Bombyx mori* L. on alternate food plants. *Pak. J. Biol. Sci.*, 2: 843-845.

- Nassig, W.A., R. E. J. Lempe and S. Kger. 1996. The Saturniidae of Sumatra (Lepidoptera). *Heterocera Sumatrana*, 10: 3-10.
- Nawaz, S. M., N. A. Jamil, A. Farooq and T. Mahmood, 2002. Comparative study of shrinkage and moisture regain of silk, viscose rayon and polyester filament yarn. *Int. J. Agric. Biol.*, 4: 493-495.
- Nel, F., 2007. The Evaluation Of Mixed Yarn Fabrics Of *Gonometa Postica* Silk, Acrylic And Wool, Dissertation Submitted In Accordance With The Requirements For The Master Of Science In Home Economics In The Faculty Of Natural And Agricultural Sciences Department Of Microbial, Biochemical And Food Biotechnology:consumer science at the university of the free state, Bloemfontein, South Africa.
- Ngoka, B. M., E. N. Kioko, S. K. Raina, J. M. Mueke and D. M. Kimbu, 2007. Semi-captive rearing of the African wild silkworm *Gonometa postica* (Lepidoptera: Lasiocampidae) on an indigenous and a non-indigenous host plant in Kenya. *Int. J. Trop. Insect Sci.*, 27: 183-190.
- Padamawar, M. N., and A. P. Pawar, 2004. Silk sericin and its application: A review. *J. Sci. Ind. Res.*, 63: 323-329.
- Peigler, R. S., 1993. Wild silks of the world, *American Entomologist*, 39 (3): 151-161.
- Peigler, R. S., 2004. Discovery and publication of unpublished manuscript pages on African Noctuidae (Lepidoptera) by Max Gaede (1871-1946) / Entdeckung und Publikation bisher unbekannter Manuskriptseiten über afrikanische Noctuidae (Lepidoptera) von Max Gaede (1871-1946). *Galathea* (Nürnberg), *Suppl.* 15: 23-30.
- Pérez-Rigueiro, J., C. Viney, J. Llorca, and M. Elices, 1998. Silkworm silk as an engineering material. *Journal of Applied Polymer Science*, 70: 2439-2447.
- Pérez-Rigueiro, J., C. Viney, J. Llorca, and M. Elices, 2000. Mechanical Properties of Single-Brin Silkworm Silk. *Journal of Applied Polymer Science*, 75: 1270-1277.
- Pérez-Rigueiro J, M. Elices, and C. Viney, 2001. Tensile properties of *Argiope trifasciata* drag line silk obtained from the spider's web. *Journal of Applied Polymer Science*, 82: 2245-2251.

- Pérez-Rigueiro, J., M. Elices, J. Llorca, and C. viney, 2002.** Effect of Degumming on the Tensile Properties of Silkworm (*Bombyx mori*) Silk Fiber, *Journal of Applied Polymer Science*, 84: 1431–1437.
- Perepelkin, K. E., 2007.** Physicochemical principles of spinning of natural fibroin fibers and ways of using them in chemical fiber technology-Part 2. Structure and Properties of natural fibroin fibers, Use of principles of biomimetics in developing chemical fiber technologies, *Fiber Chemistry*, 39 (5): 363-371.
- Platnick N. I., 2009.** The World Spider Catalog, Version 9.5. New York: American Museum of Natural History.
- Plaza, G. R., C. Paola, J. Pe´rez-Rigueiro, E. Marsano, Gustavo V. Guinea, and M. Elices, 2008.** Effect of Water on Bombyx mori ReGenerated Silk Fibers and Its Application in Modifying Their Mechanical Properties, *Journal of Applied Polymer Science*, 109: 1793–1801.
- Poza, P., J. Pérez-Rigueiro, M. Elices, and J. L. Lorca, 2002.** Fractographic analysis of silkworm and spider silk *Engineering Fracture Mechanics*, 69: 1035–1048.
- Prasong, S., S. Yaowalak, and S. Wilaiwan, 2009.** Characteristics of silk fiber with and without sericin component: A comparison between *B. mori* and *Philosamia ricini* silks, *Pakistan Journal of Biological sciences*, 12 (11): 872 – 876.
- Raina, S. K., 2004.** Commercial Insects: A practical Guide for Raising and Utilising Silkmooths and Honey Bess in Africa. Volumes 1-3. ICIPE Science Press, Nairobi.
- Raina, S. K., E. N. Kioko, I. Gordon and C. Nyandiga, 2009.** Improving forest conservation and community Livelihoods through income Generation from commercial insects in three Kenyan forests, Project Report.
- Rajkhowa, R., V. B. Gupta, and V. K. Kothar, 2000.** Tensile stress–strain and recovery behaviour of Indian silk fibers and their structural dependence, *Journal of Applied Polymer Science*, 77 (11): 2418–2429.
- Ranganathaian, C., 2003.** Positron Lifetime study of thermally induced microstructural changes in nastari silk fibers. *Chinese J. Polym. Sci.*, 21: 325-332.

- Rastogi, D., K. Sen and M. Gulrajani, 2001.** Photofading of reactive dyes on silk and cotton: effect of dye–fiber interactions, *colouration technology*, 117: 193-198.
- Razafimanantsoa, T., O. R. Ravoahangimalala, and C. L. Craig, 2006.** Indigenous silk moth farming as a means to support Ranomafana National Park, Report on a feasibility study. *Madagascar Conservation and Development*, 1(1): 34-39.
- Reddy, R. M., 2009.** Innovative and Multidirectional Applications of Natural Fiber, Silk - A Review; *Academic Journal of Entomology*, 2 (2): 71-75.
- Reddy, N., and Y. Yang 2010 (a).** Morphology and tensile properties of silk fibers produced by uncommon Saturniidae, *International Journal of Biological Macromolecules*, 46: 419–424.
- Reddy, N., and Y. Yang, 2010 (b).** Structure and properties of cocoons and silk fibers produced by *Hyalophora cecropia*, *Journal of Materials Science*, 45 (16): 4414-4421.
- Regier, J. C., M. C. Grant, C. Mitter, C. P. Cook, R. S. Peigler and R. Rougerie, 2008.** Phylogenetic relationships of wild silkmoths (Lepidoptera: Saturniidae) inferred from four protein-coding nuclear genes. *Systematic Entomology*, 10: 1-10.
- Richards, O. W., and R. G. Davies, 1977.** IMM'S General textbook of entomology. 10<sup>th</sup> Edn. I- Structure, Physiology and Development. Chapman and Hall, USA.
- Robson, R. M., 1985.** Silk composition, structure and properties; in Hand book of fiber Science and Technology, vol IV, Lewin, M and E.M pearce (ed), Mercel.Dekker Inc, New York. pp. 649-700.
- Römer, L., and T. Scheibel, 2008.** The elaborate structure of spider silk: Structure and function of a natural high performance fiber, *Prion*, 2: 154–161.
- Rosner, S., and E. Führer, 1996:** Zur Überwinterungstrategie der kleinen ichtenblattwespe, *Pristiphora abietina* Christ. (Hym., Tenthredinidae). *J. Appl. Entomol.*, 120: 225-230.
- Rudall, K. M., 1962.** Silk and other cocoon proteins. In: Florkin M, Mason HS, eds. *Comparative Biochemistry*, vol. 4. New York: Academic Press; 397- 443.
- Rudall, K. M., and W. Kenchington, 1971.** Arthropod Silks: the problem of fibrous proteins in animal tissues; *Annu. Rev. Entomol.*, 16: 73 – 96.

- Sadov, F., M. Korchagin and A. Matetsky, 1987.** Chemical Technology of Fibrous Materials. Mir Publication, Moscow, pp: 306-307.
- Sah, M. K. and K. Pramanik, 2010.** ReGenerated Silk Fibroin from *B. mori* Silk Cocoon for Tissue Engineering Applications, *International Journal of Environmental Science and Development*, 1 (5): 404-408.
- Sakamoto, K., and K. Yamakishi, 2000.** Sericin containing cleaning composition. Jpn Kokai Koho Jap 2000073090 A2 ; Chem Abstract 132.
- Sakabe, H., H. Ito, T. Miyamoto, Y. Noishiki, and W. S. Ha, 1989.** In vivo blood compatibility of reGenerated silk fibroin. *Sen-i Gakkaishi*, 45: 487-490.
- Salamone, J. C., 1999.** Concise Polymeric Materials Encyclopaedia. CRC Press, USA.
- Saravanan, D., 2006.** Spider silk: structure, properties and spinning. *Journal of Textile and Apparel, Technology and Management*; 5 (1): 1-20.
- Sarovart, S., B. Sudatis, P. Meesilpa, B. P. Grady and R. Magaraphan, 2003.** The use of sericin as an antioxidant and antimicrobial for polluted air treatment. *Rev. Adv. Mater. Sci.*, 5: 193-198.
- SAS Institute 2010.** The SAS Statistical System, Version 9.2 (32). SAS Institute, Carry, NC.
- Sashina, E.S., A. M., Bochek, N. P., Novoselov and D. A. Kirichenko, 2006.** Structure and solubility of natural silk fibroin, *Russian Journal of Applied Chemistry*, 79 (6): 869-876.
- Sashina, E. S., N. P. Novoselov, and K. Heinemann, 2003.** Dissolution of Silk Fibroin in N-methylmorpholine-N-oxide and Its Mixtures with Organic Solvents, *Russian Journal of Applied Chemistry*, 76 (1): 128-131.
- Schoeser, M., 2007.** Silk. Yale University Press, USA.
- Sehnal, F., and T. Sutherland, 2008.** Silks produced by insect labial glands. *Prion*, 2 : 1-9
- Sen, K., and M. K. Babu, 2004a.** Studies on Indian silk. I. Macrocharacterization and analysis of amino acid composition, *Journal of Applied Polymer Science*, 92 (2): 1080-1097.
- Sen, K., and M. K. Babu, 2004b.** Studies on Indian Silk. II. Structure-Property Correlations, *Journal of Applied Polymer Science*, 92: 1098-1115.

- Shamitha, G., and A. P. Rao, 2006.** Studies on the filament of tasar silkworm, *Antheraea mylitta* D (Andhra local ecorace), *Current Science*, 90 (12): 1667-1671.
- Shao, Z. Z., and F. Vollrath, 2002.** "Materials: Surprising strength of silkworm silk," *Nature*, 418 (6899): 741-741.
- Shimra, K., 1983.** Chemical composition and biosynthesis of silk proteins. *Experientia*. 39:455--461.
- Simmons, A. H., C. A. Michal, and L. W. Jelinski, 1996.** Molecular orientation and two-component nature of the crystalline fraction of spider dragline silks. *Science*, 271: 84–87.
- Singhi, N. R., and P. C. Bose, 1991.** Sericin: A deciding factor for the quality of cocoons and raw silk. *Indian Silk*, 26-28.
- Snowwalker, T. N., 1993.** Handbook of Silk Technology. Newage International Publishers Ltd., New Delhi.
- Sonthisombat, A., and P. T. Speakman, 2004.** Silk: Queen of fibers- the concise story, [http://www.en.rmutt.ac.th/prd/Journal/Silk\\_with\\_figuresnew.pdf](http://www.en.rmutt.ac.th/prd/Journal/Silk_with_figuresnew.pdf)
- Spradbery, J. P., 1973.** Wasps. London: Sidgwick and Jackson, UK.
- Srisuwan, Y., and P. Srihanam, 2009.** Dissolution of *Philosamia ricini* silk film: Properties and functions in different solutions. *J. Applied Sci.*, 9: 978-982.
- Srivastava, P. K., and K., Thangavelu, 2005.** Sericulture and Seri-biodiversity. Associated Publishing Company, New Delhi.
- Stitzel, J., J. Liu, S. J. Lee, M. Komura, J. Berrya, S. Sokerc, G. Limc, M. V. Dykec, C. Richard, and J. Y. James, 2006.** Controlled fabrication of a biological vascular substitute, *Biomaterials*, 27: 1088–1094.
- Sutherland, T. D., J. Young, S. Weisman, C. Y. Hayashi, and D. J. Merritt, 2010.** Insect silk: one name, many materials, *Annual Review of Entomology*, 55: 171-188
- Swanson, B. O, T. A. Blackledge, J. Beltra'n, and C.Y. Hayashi, 2006.** Variation in the material properties of spider dragline silk across species. *J Appl Phys A* , 82: 213–218.

- Tagawa J., and Y. Sato, 2009.** Investment in cocoon-silk and structure of the clusters of cocoons produced by gregarious microgastrine wasps (Hymenoptera: Braconidae). *Eur. J. Entomol.*, 106 (3): 353–356.
- Takeshita, T., K. Ishida, and Y. Kamiishi, 2000.** Production of fine powder from silk by radiation, *Macromol. Mater. Eng.*, 283: 126–131.
- Tanaka, K., and S. Mizuno 2001.** Homologues of fibroin L-chain and P<sub>25</sub> of *Bombyx mori* are present in *Dendrolimus spectabilis* and *Papilio xuthus* but not detectable in *Antheraea yamamai*. *Insect Biochemistry and Molecular Biology*, 31: 665–677.
- Tanaka, K., S. Inoue and S. Mizuno, 1999.** Hydrophobic interaction of P25, containing Asn- linked oligosaccharide chains, with the H-L complex of silk fibroin produced by *Bombyx mori*. *Insect Biochem. Mol. Biol.*, 29: 269-276.
- Tanaka, T., J. Magoshi, Y. Magoshi, S. ichi Inoue, M. Kobayashi, H. Tsuda, M. A. Becker, and S. Nakamura, 2002.** Thermal properties of *Bombyx mori* and several wild silkworm silks Phase transition of liquid silk, *Journal of Thermal Analysis and Calorimetry*, 70 (3): 825-832.
- Tanaka, C., R. Takahashi, A. Asano, T. Kurotsu, H. Akai, K. Sato, D. P. Knight, and T. Asakura, 2008.** Structural Analyses of Anaphe Silk Fibroin and Several Model Peptides Using 13 C NMR and X-ray Diffraction Methods, *Macromolecules*, 41 (3): 796-803.
- Terada, S., T. Nishimura, M. Sasaki, H. Yamada, and M. Miki, 2002.** Sericin, a protein derived from silkworms, accelerates the proliferation of several mammalian cell lines including a hybridoma. *Cytotechnology*, 40: 3–12.
- Teramoto, H., T. Kameda, and Y. Tamada, 2008.** Preparation of gel film from *B. mori* silk sericin and its characterization as a wound healing dressing, *Biosci. Biotechnol. Biochem.*, 72 (12): 3189-3196.
- Thangavelu, K., 2002.** Future research strategy for non-mulberry sericulture with particular reference to tasar culture: Advances in Indian sericulture research. Proceedings of the National Conference on Strategies for Sericulture Research and Development, Nov. 16-

- 18, Central Sericultural Research and Training Institute, Central Silk Board, Mysore, India, pp: 365-368.
- Tsai, L. and V. Prakash, 2005.** Structure of weak shock waves in 2-D layered material systems. *International Journal of Solids and Structures*, 42: 727–750.
- Tsukada, M., Y. Gotoh, G. Freddi, and J. S. Criton, 1994.** Physical characteristics of silk fibers modified with dibasic acid anhydrides, *Journal of Applied Polymer Science*, 51: 345-352.
- Tsubouchi, K., H. Yamada, and Y. Takasu, 2002.** Japan Kokia Tokkyo Koho -128691 (May 9, 2002)
- Tsubouchi, K., Y. Igarashi, Y. Takasu and H. Yamada 2005.** Sericin enhances attachment of cultured human skin fibroblasts, *Biosci. Biotechnol. Biochem.*, 69: 403—405.
- Triped, J., W. Sanongraj, B. Oonkhanond, and S. Sanongraj, 2009.** Synthesis of silk fibroin fiber for indoor air particulate removal, *World Academy of Science, Engineering and Technology*, 51: 85-90.
- Trivedy, K., S. N. Kumar, M. Mondal and C. A. K. Bhat, 2008.** Protein Banding Pattern and Major Amino Acid Component in De-oiled Pupal Powder of Silkworm, *B. mori* Linn. *Journal of Entomology*, 5 (1): 10-16.
- Vasumathi, B. V., C. Takabayashi, N. Kenichi and H. S. Turvekere, 2004.** Studies on the Relationship between Cocoon Parameters and Raw Silk Uniformity Characteristics, *Journal of Insect Biotechnology and Sericology*, 73: 47-56.
- Veldtman, R., 2005.** The ecology of southern Africa wild silk moths (Gonometa species, Lepidoptera: Lasiocampidae): consequences for their sustainable use, Ph D Thesis, University of Pretoria.
- Victoriano, E., D. O. Pinheiro E Elisa and A. Gregório, 2007.** Histochemical and Ultrastructural Evidence of Lipid Secretion by the Silk Gland of the Sugarcane Borer *Diatraea saccharalis* (Fabricius) (Lepidoptera: Crambidae), *Neotropical Entomology*, 36 (5): 707-711.





- Vishuprasad, N., 2004.** Composite quality index of silk cocoons-application of discriminant analysis. *J. Acad. Bus. Econ.*, Date: Monday, March 1, 2004, URL: <http://www.allbusiness.com/accounting/300390-1.html>.
- Voegeli, R., J. Meier, and R. Blust, 1993.** Sericin silk protein: unique structure and properties. *Cosmetics & Toiletries*, 108: 101–108.
- Vollrath F., 2000.** Strength and structure of spiders' silks. *J. Biotechnol*; 74: 67-83.
- Vollrath, F., and D. P. Knight, 2001.** Liquid crystalline spinning of spider silk. *Nature*, 410: 541-548.
- Vollrath, F., B. Madsen, and Z. Z. Shao, 2001.** The effect of spinning conditions on the mechanics of a spider's dragline silk. *Proceedings of the Royal Society of London Series B-Biological Sciences*, 268: 2339-2346.
- Vollrath, F., P. Barth, A. Basedow, W. Engstrom, and H. List, 2002.** Local tolerance to spider silks and protein polymers in vivo. *In Vivo*, 16: 229-234.
- Vollrath, F., and D. Porter, 2006.** Spider silk as archetypal protein elastomer, *Soft Matter*, 2: 377–385.
- Vollrath, F., and P. Selden, 2007.** The role of behaviour in the evolution of spiders, silks, and webs. *Annu Rev Ecol Evol Syst*, 38: 819 - 846.
- Wang, Y. Z., D. J. Blasioli, H. J. Kim, H. S. Kim, and D. L. Kaplan, 2006.** Cartilage tissue engineering with silkscaffolds and human articular chondrocytes, *Biomaterials*, 27: 4434- 4442.
- Wang, X., X. Hu, A. Daley, O. Rabotyagova, P. Cebe, and D. L. Kaplan, 2007.** Nanolayer biomaterial coatings of silk fibroin for controlled release. *J Control Release*, 121 (3):190–199.
- Warwicker, J. O., 1960.** Comparative studies of fibroins. II. The crystal structures of various fibroins. *J. Mol. Biol.*, 2: 350–362.
- Weijers, M., K. Broersen, P. A. Barneveld, M. A. Cohen Stuart, R. J. Hamer, H. H. J. De Jongh and R. W. Visschers, 2008.** Net Charge Affects Morphology and Visual Properties of Ovalbumin Aggregates, *Biomacromolecules*, 9 (11): 3165–3172.



- Wiedemann, H. G. and T. Mckarns, 1990. Thermal characteristics of polymer fibers *Thermochimica Acta*, 169: 1-13.
- Wilaiwan, S., S. Yaowalak, B. Yodthong and S. Prasong, 2010. Silk fibroin/gelatin hybrid films for medical applications: Study on chlorhexidine diacetate. *J. Biol. Sci.*, 10: 455-459.
- Work, R. W., 1976. The force-elongation behaviour of web fibers and silks forcibly obtained from orb-web-spinning spiders. *Textile Res. J.*, 46: 485-492.
- Xia, W., and D. Zhao, , 2003. The chrysalis of silkworm synthesizes to develop the present condition and technique. *J. Shaanxi Normal Univ. (Natural Science Edition)* 31: 265–269.
- Xio, S., W. Stacklies, M. Cetinkaya, B. Markert, and F. Gra“te, 2009. Mechanical Response of Silk Crystalline Units from Force-Distribution Analysis, *Biophysical Journal*, 96: 3997–4005
- Yamada, H., H. Nakao, Y. Takasu, and K. Tsubouchi, 2001. Preparation of undergraded native molecular fibroin solution from silkworm cocoons. *Mater Sci Eng C*. 14 (1/2): 41–46.
- Yanagihara, K., S. Terada, M. Miki, M. Sasaki, and H. Yamada, 2006. Effect of the silk protein sericin on the production of adenovirusbased gene-therapy vectors. *Biotechnology and AppliedBiochemistry*, 45: 59–64.
- Yang, Y., L. Tang, L. Tong and H. Liu, 2009. Silkworms culture as a source of protein for humans in space. *Advances in Space Research*, 43 (8): 1236-1242.
- Yonemura, N., K. Mita, T. Tamura, and F. Sehnal, 2009. Conservation of Silk Genes in Trichoptera and Lepidoptera. *J Mol Evol*, 68: 641–653.
- Zhang, M., A. Haga, H. Sekiguchi, and S. Hirano, 2000. Structure of insect chitin isolated from beetle larva cuticle and silkworm (*Bombyx mori*) pupa exuvia. *International Journal of Biological Macromolecules*, 27: 99–105.
- Zhang, H., J. Magoshi, M. Becker, J. Yu Chen, and R. Matsunaga, 2002. Thermal Properties of *Bombyx mori* Silk Fibers, *Journal of Applied Polymer Science*, 86: 1817–1820.


- Zhang, Q., 2002. Application of natural silk protein sericin in biomaterials. *Biotechnol Adv.*, 20: 91-100.
- Zhang, Y., Y. Ma, Y. Xia, W. Shen, J. Mao and R. Xue, 2006. Silk Sericin-Insulin bioconjugates: synthesis, characterization and biological activity. *Journal of Controlled Release*, 115: 307– 315.
- Zhang, Y., H. Yang, H. Shao, and X. Hu, 2010 (a). *Antheraea pernyi* Silk Fiber: A Potential Resource for Artificially Biospinning Spider Dragline Silk, *Journal of Biomedicine and Biotechnology*, 1-8.
- Zhang, K., F. W. Si, H. L. Duan, and J. Wang, 2010 (b). Microstructures and mechanical properties of silks of silkworm and honeybee, *Acta Biomaterialia*, 6: 2165–2171.
- Zhao, H., X. Feng, S. Yu, W. Cui, and F. Zou, 2005. Mechanical properties of silkworm cocoons, *Polymer*; 46: 9192–9201.
- Zhou, J., and D. Han, 2006. Safety evaluation of protein of silkworm (*Antheraea pernyi*) pupae, *Food and Chemical Toxicology*, 44 (7): 1123-1130.
- Zhou, C. Z, F. Confalonieri, N. Medina, Y. Zivanovic, C. Esnault, T. Yang, M. Jacquet, J. Janin, M. Duguet, R. Perasso, and Z. G. Li, 2000. Fine organization of *Bombyx mori* fibroin heavy chain gene, *Nucleic Acids Research*, 28 (12):2413–2419.

## APPENDICES

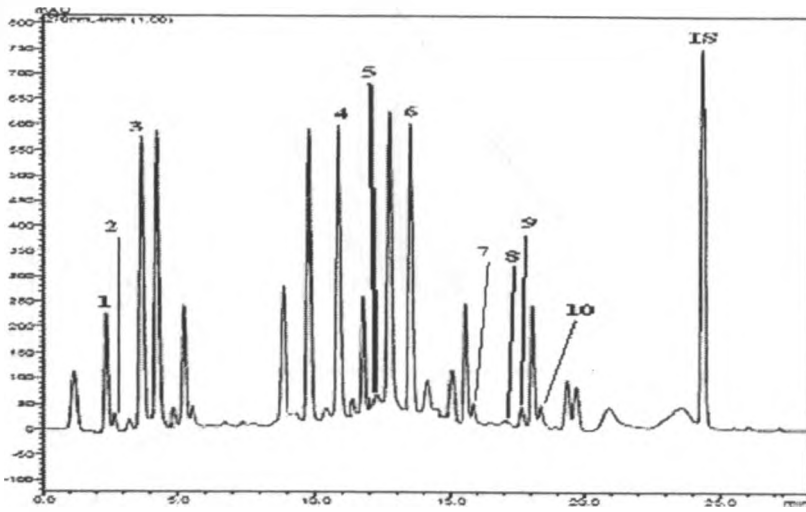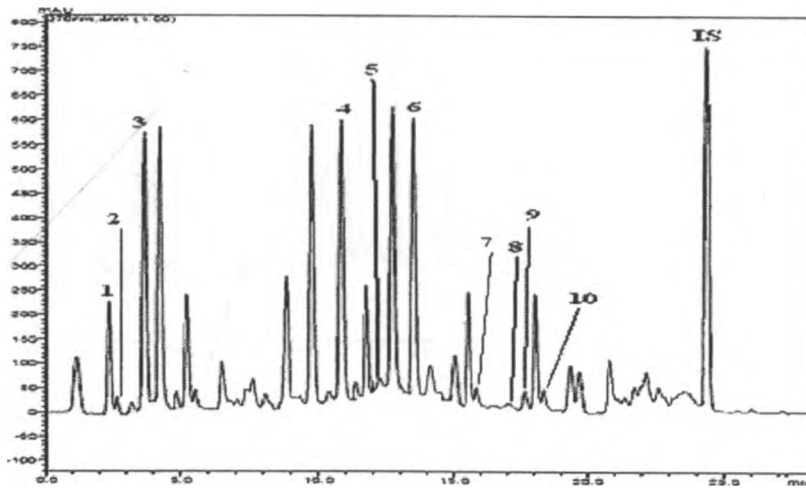(a) *Argema mimosae*(b) *Epiphora bauhiniae*

(d) *Gonometa postica*

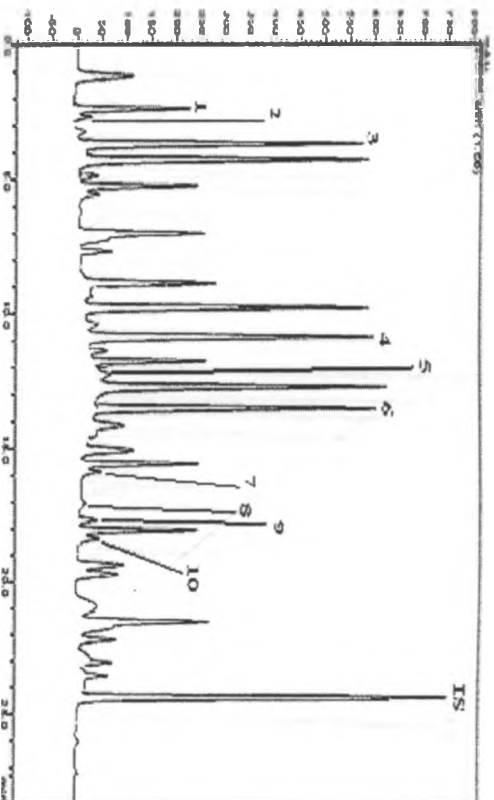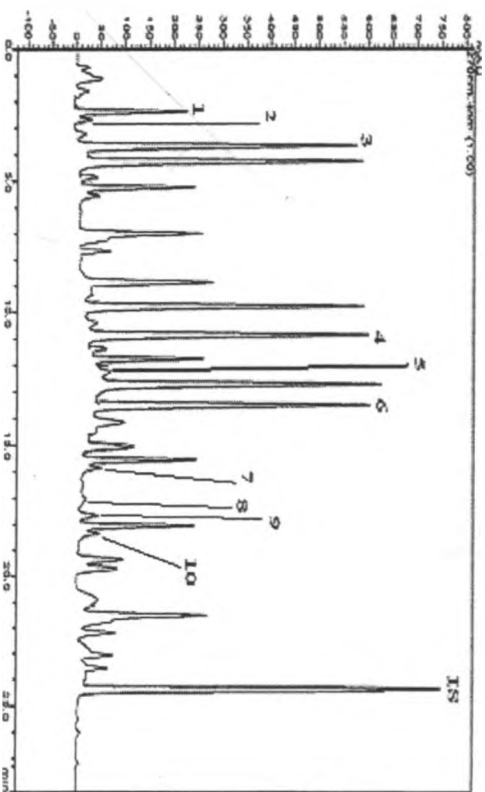(c) *Anaphie pumda*

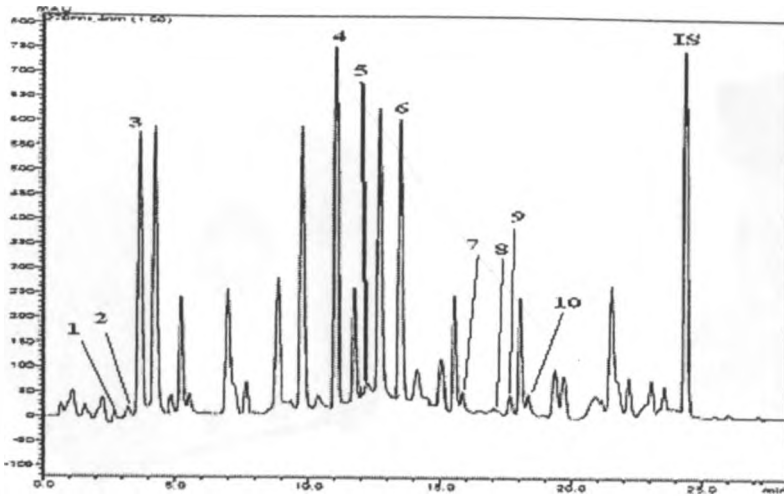

(e) *Bombyx mori*

Appendix 1: HPLC peaks for the amino acid analysis of African wild and *Bombyx mori* fibroins



(a) Scanning Electron Microscope (SEM)



(b) Thermogravimetric Analyzer (TGA)



(c) Instron Tensile Tester (5542)



(d) Fourier Transform Infrared spectroscopy

Appendix 2: Some of the Equipments used in the study  
([http://users.ox.ac.uk/~abrg/spider\\_site/machines.html](http://users.ox.ac.uk/~abrg/spider_site/machines.html))




**List of published journal articles from the thesis**

1. Addis T., S. K. Raina, F. Vollrath, J. M. Kabaru, J. Onyari and E. Nguku, 2011. Study on moisture regain and weight loss of African wild silk cocoon shells and degummed fibers, *Journal of Entomology* , 8 (5): 450-458
2. Addis T., F. Vollrath, S. K. Raina, J. M. Kabaru, and J. Onyari, 2012. Study on microstructures of African Wild silk cocoon shells and fibers, *International Journal of Biological Macromolecules*, 50 (1): 63-68
3. Addis T., J. M. Onyari, S. K. Raina, J. M. Kabaru, and F. Vollrath, 2013. Mechanical and thermal degradation properties of silk from African wild silkmoths, *Journal of Applied Polymer Sciences*, 127 (1): 289-297.

**Manuscripts submitted related to the thesis**

1. Addis T., S. K. Raina and F. Vollrath, 2012. Structure and properties of indoor reared African wild silkmoth, *Gonometa postica*, cocoon shells and degummed fibers, *Journal of Insect Science*.
2. Addis T. and S. K. Raina, 2012. Properties and structures of silk from the African Wild Silkmoth, *Anaphe panda* Boisduval (Lepidoptera: Thaumetopoeidae) *Journal of Natural Fibers*
3. Addis T., S. K. Raina, J. M. Kabaru and J. M. Onyari, 2012. Dissolution properties of silk cocoon shells and degummed fibers from African wild silkmoths, *Journal of Applied Sciences*



## Study on the microstructure of African wild silk cocoon shells and fibers

Addis Teshome<sup>a,c,\*</sup>, Fritz Vollrath<sup>b</sup>, Suresh K. Raina<sup>a</sup>, J.M. Kabaru<sup>c</sup>, J. Onyari<sup>c</sup>

<sup>a</sup> *icipe-African Insect Science for Food and Health, P.O. Box 30772-00100, Nairobi, Kenya*

<sup>b</sup> *University of Oxford, Department of Zoology, Silk Research Group, South Parks Road, Oxford OX1 3PS, UK*

<sup>c</sup> *University of Nairobi, School of Biological and Physical Sciences, P.O. Box 30197-00100, Nairobi, Kenya*

### ARTICLE INFO

#### Article history:

Received 9 August 2011

Received in revised form

26 September 2011

Accepted 27 September 2011

Available online 5 October 2011

#### Keywords:

SEM

Voids

Wild silkworm

### ABSTRACT

Silk fibers and cocoon shells from four African wild silkworms *Gonometa postica*, *Anaphe panda*, *Argema mimosae* and *Epiphora bauhiniæ*—were studied to gain insight into the structure–property–function relations and potential commercial application. The surface and cross-section of cocoon shells and fibers revealed the presence of prominent structural variations. Cocoon shells were multilayered and porous structures constructed from highly cross-linked fibers that are densely packed within the sericin/gum. Fibers had fibrillar sub-structures running along the fiber axis and with greater number and size of voids. The ecological significance and implication of these structures for further application are discussed.

Crown Copyright © 2011 Published by Elsevier B.V. All rights reserved.

### 1. Introduction

Silk, from both domesticated and wild silkworms and spiders, represents a unique and important class of polymeric composite materials in nature providing a wide range of evolutionary and ecological functions with optimum microstructures and properties [1,2]. Larvae of silkworms spin silk threads and form cocoon shells to enclose themselves completely prior to metamorphosis. These cocoon shells are non-woven structures majorly composed of two proteins, fibroin and sericin. They exhibit extensive variation in structure, property and composition which imposes direct influence on their adaptive function. The functional significance of these proteinaceous structures includes crypsis, provision of barricade from predators, pathogens and parasitoids and assisting the pupae to complete their metamorphosis by improving thermal and/or moisture conditions [3]. The multitude of variations in diet, breed and climate resulted in considerable diversity in the type and properties of the cocoons and fibers produced by silk producing insects of different origins and within the same type. Thus, species-specific fiber mechanical, chemical and physical properties reflect the ecology and behaviour of cocoon-spinning insects [4,5] and can significantly influence the quality, quantity and efficiency of the reeling process in commercial varieties [6].

Studies have shown the existence of macro- and microscopic level structure and property variations among cocoon shells and fibers from mulberry and wild silkworms. Narumi et al. [7] revealed the presence of a large number of voids in the cross-sections of wild silk fibers in contrast to mulberry silk. The silk fibers from the wild silkworms have many longitudinal striations on their surface and are porous which make them lighter than mulberry silk [8]. Wild silk fibers also consist of flattened, ribbon-like filaments of much greater diameter than mulberry silk [9]. Although the potential of African wild silkworms for production of large cocoons with economic importance has been documented, the microscopic structure and properties of these fibers and cocoon shells have not been studied in detail. Comprehensive studies of such structures will lead to better understanding of the cocoon spinning behaviour of the silkworms and how silk fibers are arranged in the cocoon shells to suit their designed purposes. This information would be of immense value in the prudent evaluation of the potential of silks for commercial application and further investigate the structure–property–function relations of silk fibers and cocoon shells. In this study, we investigate the surface and cross-sectional structures of silk fibers and cocoon shells produced by four species of wild silkworms using scanning electron microscope (SEM) and Fourier transform infrared (FTIR) spectroscopy.

### 2. Materials and methods

#### 2.1. SEM study on surface and cross-sections of cocoon shells

Cocoon shells of four wild silkworm species (*Anaphe panda* Biosduval, *Argema mimosae* Biosduval, *Epiphora bauhiniæ* Guer and

\* Corresponding author at: icipe-African Insect Science for Food and Health, P.O. Box 30772-00100, Nairobi, Kenya. Tel.: +254 20 8632054; fax: +254 20 8632001/2; mobile: +254 719 698782.

E-mail addresses: [additi09@gmail.com](mailto:additi09@gmail.com), [akebede@icipe.org](mailto:akebede@icipe.org) (A. Teshome).

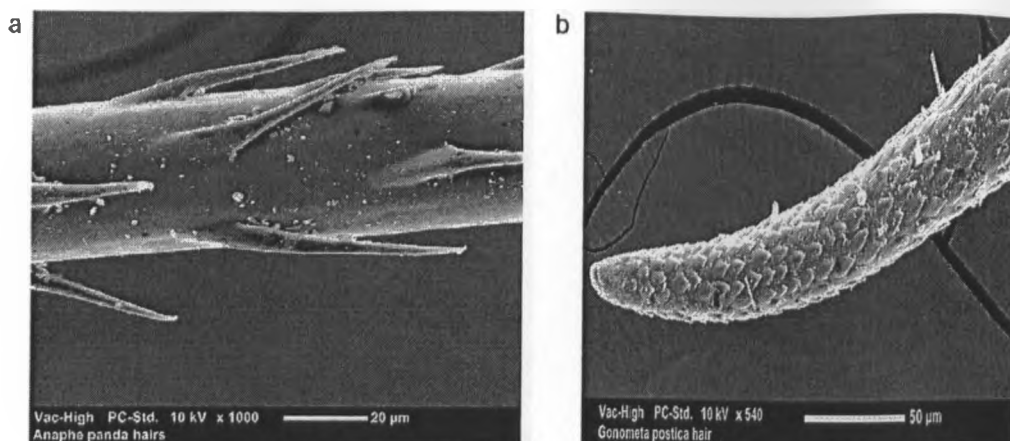


Fig. 1. SEM micrographs of (a) *Anaphe panda* cocoon hair, (b) *Gonometta postica* spine (Tip).

*Gonometta postica* Walker) were collected from four different eco-  
 systems in Kenya namely; Kakamega forest, Arabuko-Sokoke forest,  
 West Pokot and Mwingi Districts. Cocoons of *Bombyx mori* Linn  
 (ICRISAT ICIPE II) were obtained for comparison from the Commercial  
 Insects Programme of the International Centre of Insect Physiol-  
 ogy and Ecology (ICIPE). Cocoon shell discs of 5 mm diameter were  
 cut out of the middle section of the cocoon with a sharp hole-  
 punch for external and internal cocoon surface studies. Ten cocoons  
 were sampled five times at random locations and the thicknesses  
 and weight of the discs were measured using a digital micrometer  
 (Mitutoyo<sup>®</sup>, IP 65) and digital balance, respectively.  
 Cocoon shells were cut into cross-section slices by using a sharp  
 blade for cross-sectional observation. Spines and hairs from *G. pos-*  
*tica* and *A. panda* cocoons were collected using forceps. All samples  
 were separately mounted onto copper stubs using double side  
 sticky tape and were then sputter-coated with gold (JEOL JFC-  
 1200 ion sputter) for three minutes to minimise charging under  
 electron beam. The samples were then studied with SEM (Jeol  
 microscope, JCM-5000 (Nikon<sup>®</sup>, UK)) under an accelerating voltage  
 of 10 kV with a beam current of 0.1 nA.

#### Longitudinal and cross-sectional analysis of fibers

Cleaned cocoons were degummed by boiling with 5g/L of  
 Na<sub>2</sub>CO<sub>3</sub> solution for 3 h. Boiled cocoons were soaked in StarSoft  
 solution of 50 mL/L of distilled water for 3 minutes and washed  
 with hot and cold distilled water. The degumming pro-  
 cedure was repeated for all except *B. mori* and *G. postica* cocoons.  
 Degummed fibers were soaked in 70% ethanol for three days to  
 remove remnant sericin and fatty materials and then dried at room  
 temperature. Fiber cross-sections were made by linearly mounting  
 fiber strands in plastic tubes and cut end of the tube was inserted  
 into a cutting device and a clean cut was made by using a new  
 razor blade. For longitudinal surface studies, fibers were horizon-  
 tally mounted. The slices were mounted onto copper stubs using  
 double side sticky tape and were coated with gold on their cut  
 surface to be observed using SEM.

#### FTIR study

Nicolet 6700 FTIR equipped with liquid nitrogen cooled MCT-  
 detector was used. Outer and inner surfaces of three cocoon  
 discs of each species were sampled three times. Spectra were  
 obtained at 4 cm<sup>-1</sup> resolution from 7000 to 400 cm<sup>-1</sup> and average  
 of 16 scans. All spectral operations were performed using Omnic<sup>®</sup>  
 (Thermo Scientific, Madison, WI).

### 3. Results

#### 3.1. Surface and cross-sections of cocoon shells

Being a typical protective structure, the surface of the cocoon  
 shells exhibited extensive variation to meet the specific needs of a  
 given species. *A. panda* and *G. postica* cocoon shells had dense white  
 and brown hairs and spines embedded from the body of the larvae  
 during spinning. The average diameter of *A. panda* hair was 34 μm  
 and had thorny spines (6–8 μm in diameter) arranged alternatively  
 over the surface (Fig. 1a). *Gonometta* cocoons had short white hairs  
 interwoven throughout the cocoon layers while the brown needle-  
 like spines with sharp buds on their surface were found attached  
 to the outer cocoon surface (Fig. 1b). The sharpness of the buds  
 decreased towards the base of the spines.

Cocoons of *E. bauhiniae* had a strong silk thread (peduncle) spun  
 to attach the cocoon to the twig of a plant. The peduncle was com-  
 posed of highly cross-linked fibers embedded with a mass of sericin  
 gum (Fig. 2). In the rest of the species, cocoons were sessile and  
 were directly attached along their full length to twigs and forked  
 branches. The attachment surfaces for *A. mimosae* and *G. postica*  
 were smooth and plastered with massive amount of gum and crys-  
 tals. *G. postica* and *E. bauhiniae* cocoon shells were covered with

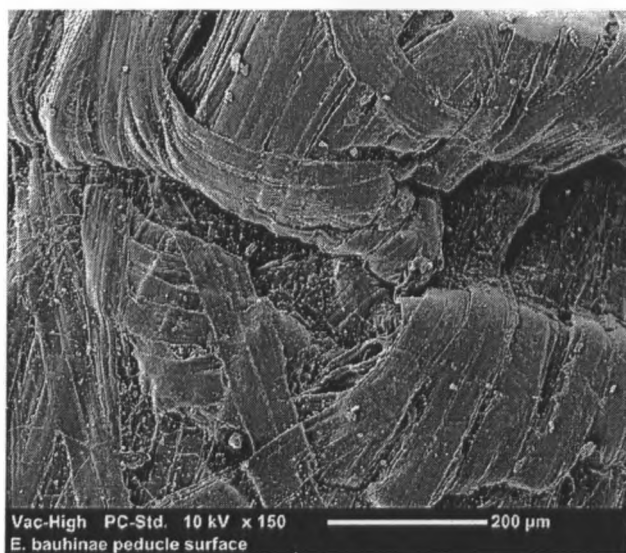


Fig. 2. *Epiphora bauhiniae* cocoon peduncle.

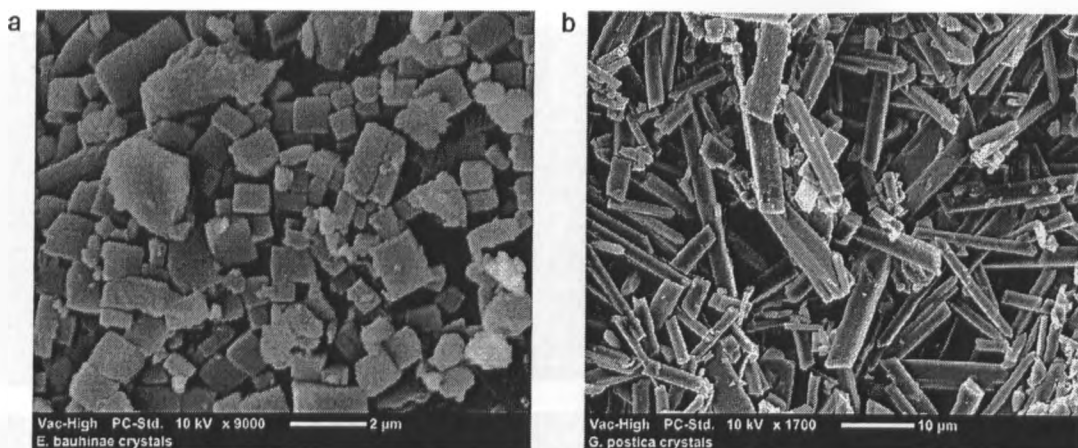


Fig. 3. Cocoon shell crystals of (a) *Epiphora bauhiniae* and (b) *Gonometa postica*.

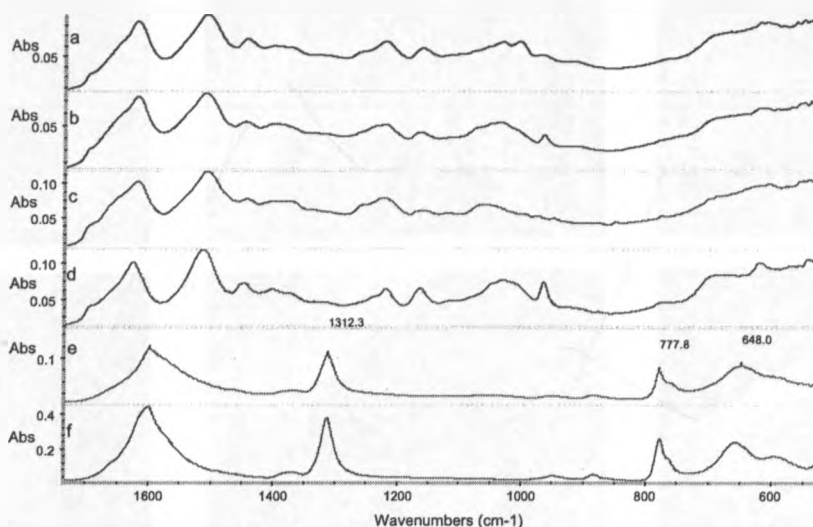


Fig. 4. FTIR spectroscopy of outer cocoon shell surfaces of (a) *Anaphe panda*, (b) *Argema mimosae*, (c) *Bombyx mori*, (d) *Epiphora bauhiniae*, (e) *Gonometa postica*, and (f) calcium oxalate hydrate.

white rectangular and cubic shaped granular crystalline materials throughout the surface except areas of fiber intrusion (Fig. 3a and b). FTIR spectra showed the peaks at  $1312\text{ cm}^{-1}$  and  $777\text{ cm}^{-1}$  were attributed to Calcium Oxalate crystal monohydrate (Sigma) (Fig. 4). However, *G. postica* cocoons had prominently higher level of the crystals than *E. bauhiniae*. Inner surface of *G. postica* had less calcium oxalate crystals. Unlike others, *A. mimosae* cocoons had considerable amount of holes/perforations formed as a ring like pattern (Fig. 5). The width of the holes ranged between 448 and 112  $\mu\text{m}$ . However, the number, size, distribution and structure of these holes varied with the position on the cocoon.

The SEM images clearly showed the wild silkworm cocoon shells were intact on their outer surface with highly cross-linked fibers and the space among the fiber strands and successive layers were smaller than *B. mori* (Fig. 6a–d). The surface of the cocoons had fibers held together in pairs by sericin gum, other secretions and impurities. The arrangement of the fibers in all the cocoon shells lacked uniformity throughout the outer surface and showed great cross-bindings, wrinkles and networking of twisting filaments in different shapes and forms. Such random twisting and bending of fibers imparted rough outer surfaces. *A. panda*, the fibers appeared flossy and randomly arranged. *G. postica*, *A. mimosae* and *Bauhiniae* had smooth and uniformly plastered inner walls and

the fibers were tightly bound together by large amounts of sericin (gum) making them appear more solid and intact. The bave of *A. mimosae* were distinctively flat and had larger thickness (80  $\mu\text{m}$ ) while *B. mori* bave had the smallest thickness (26  $\mu\text{m}$ ). *G. postica*

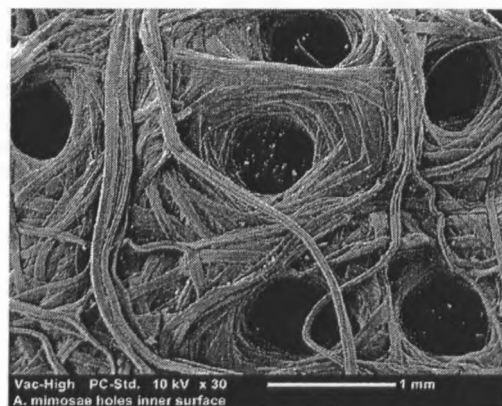


Fig. 5. Hole/perforations of *Argema mimosae* cocoon shells.

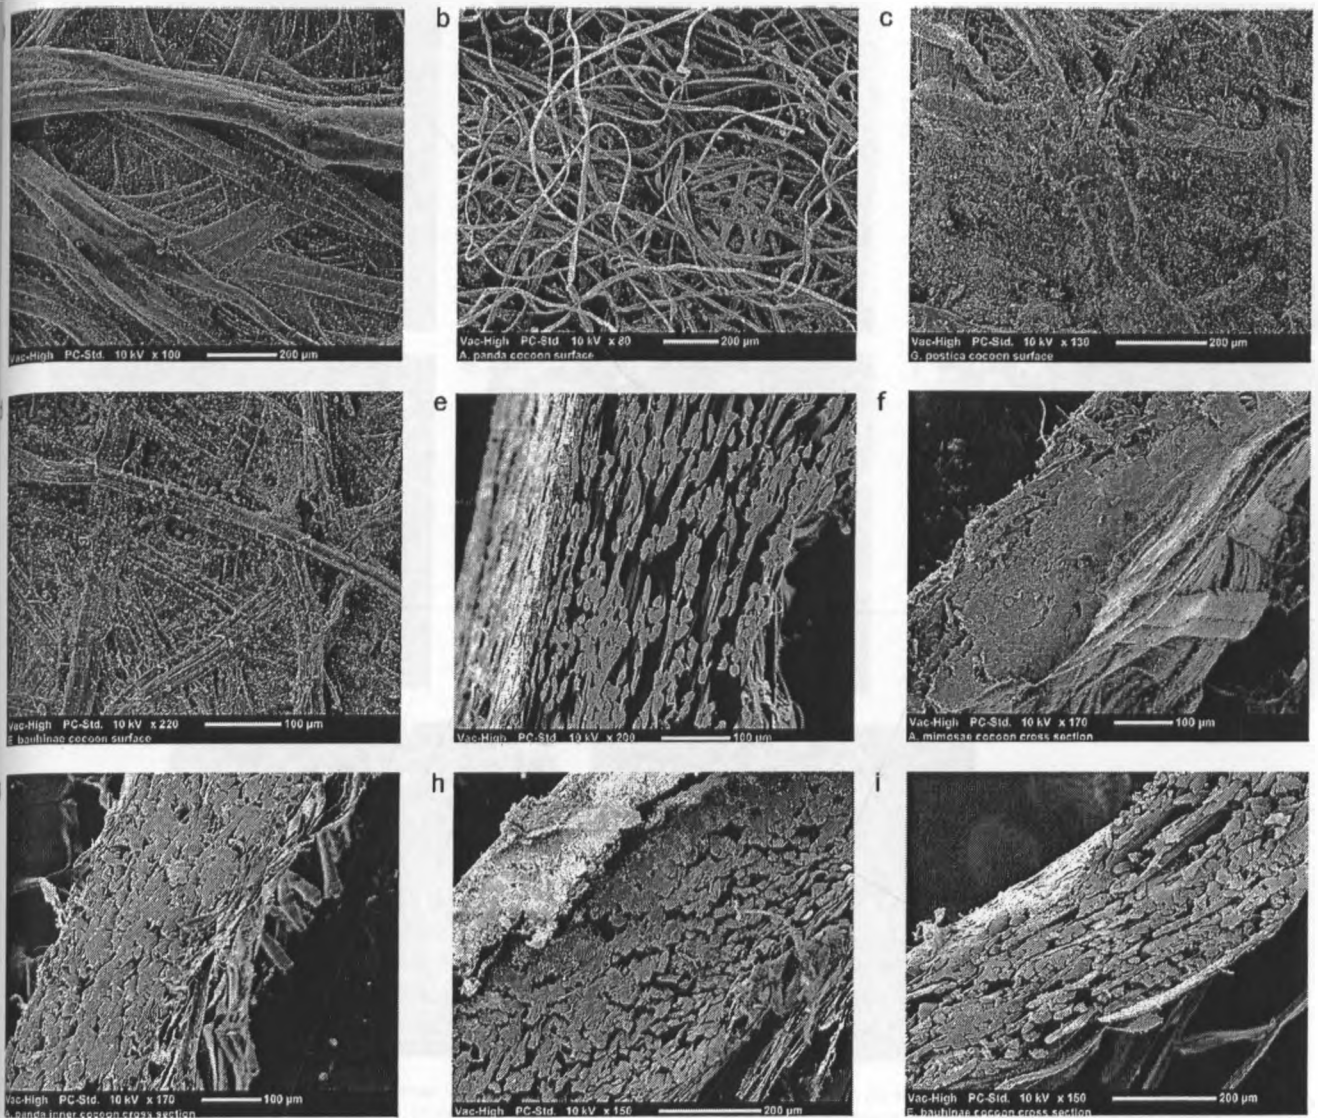


Fig. 6. Outer (a–d) and cross sections (e–i) of the African wild silk and *B. mori* cocoon shells of the African wild silk and *B. mori* cocoon shells: (a) *Argema mimosae* outer cocoon shell surface; (b) *Anaphe panda* outer cocoon shell surface; (c) *Gonometa postica* outer cocoon shell surface; (d) *Epiphora bauhinae* outer cocoon shell surface; (e) *Bombyx mori* cocoon shell cross-section; (f) *Argema mimosae* cocoon shell cross-section; (g) *Anaphe panda* cocoon shell cross-section; (h) *Gonometa postica* cocoon shell cross-section; (i) *Epiphora bauhinae* cocoon shell cross-section.

and *B. mori* had the largest and smallest cocoon shell thickness of 0.536 and 0.222 mm, respectively (Table 1).

Depending on the number of layers, the cocoon shells can be divided in to two groups; single and double layered cocoons. The first group composed of *A. mimosae*, *G. postica* and *B. mori*, had single compact cocoon layer, while the second group composed of *E. bauhinae* and *A. panda* had two hard layers (outer and inner

most layers) joined by a middle connective flossy layer of silk fibers. However, all the cocoon shells were multilayered structure of fibers packaged in different fashion (Fig. 6e–i). In *B. mori*, the fiber layers were arranged in more or less orderly but slack manner with wider spacing. Fibers of *A. mimosae* and *G. postica* were deeply encrusted and were slightly visible making the cocoons more compact and rigid. *G. postica* cocoons had 110–130 μm thick Calcium oxalate crystal layer deposit. However, the thin outer layer of *A. panda* and *E. bauhinae* were composed of loosely packed and visible fibers.

Table 1  
Cocoon shell thickness and cocoon disk weight (P > 0.001 significance level).

Species	Cocoon disc		Host plant
	Thickness (mm)	Weight (mg)	
<i>B. mori</i>	0.21 ± 0.02 <sup>d</sup>	63.4 <sup>c</sup>	Mulberry plant
<i>A. mimosae</i>	0.24 ± 0.01 <sup>d</sup>	70.4 <sup>c</sup>	<i>Sclerocarya birrea</i>
<i>A. panda</i>	0.42 ± 0.018 <sup>b</sup>	134.6 <sup>a</sup>	<i>Bridelia micranth</i>
<i>E. bauhinae</i>	0.33 ± .08 <sup>c</sup>	86.9 <sup>b</sup>	<i>Zizyphus mucronata</i> , <i>Z. mauritania</i>
<i>G. postica</i>	0.53 ± .08 <sup>a</sup>	139.6 <sup>a</sup>	<i>Acacia</i> species

### 3.2. Fiber surface and cross-sections

The degumming process forced the bave to be separated into individual brins. *A. mimosae* and *B. mori* had the thickest and smallest brin with a diameter of 49 and 10.5 μm, respectively. Fig. 7a and d shows the existence of several longitudinal striations and fibrillar structures in *A. mimosae* and *E. bauhinae* fibers. The fibers of *A. panda* were distinctly unique from other species with their bamboo-like appearance with jointed nods at intervals (Fig. 7b). G.

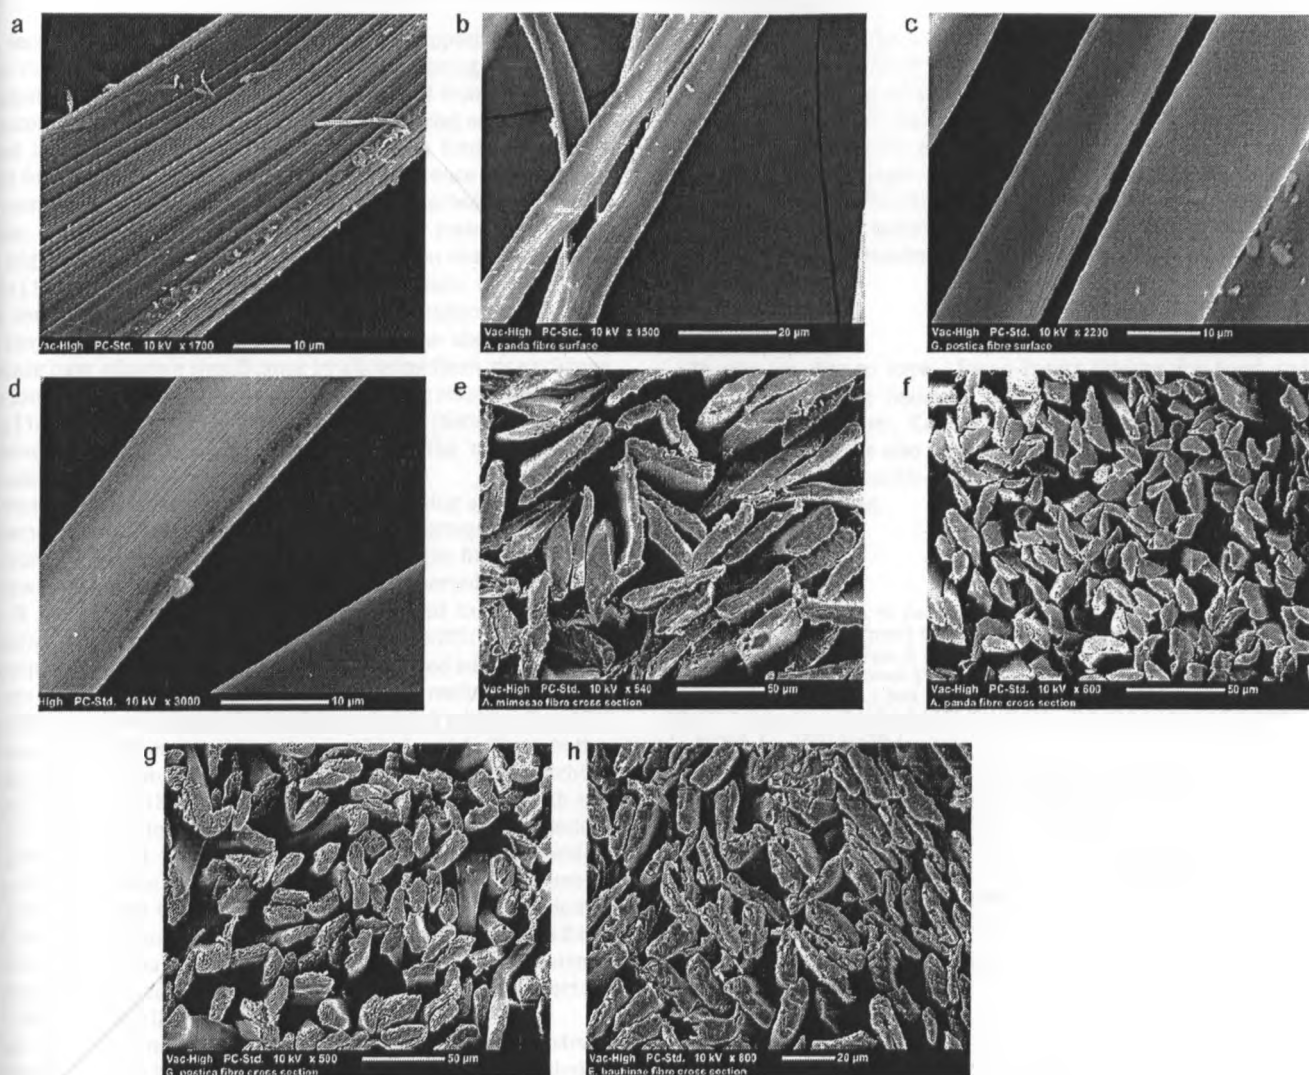


Fig. 7. Cross-sections, surface and macrovoids of Afrocan wild silk fibers: (a) surface of *Argema mimosae* fiber; (b) surface of *Anaphe panda* fibers; (c) surface of *Gonometta postica* fibers; (d) surface of *Epiphora bauhiniae* fibers; (e) cross-sections of *Argema mimosae* fibers; (f) cross-sections of *Anaphe panda* fibers; (g) cross-sections of *Gonometta postica* fibers; (h) cross-sections of *Epiphora bauhiniae* fibers.

*postica* fibers had relatively smooth fiber surface with occasional grooves and ridges. The wild silk fibers were ribbon-like, twisted with uneven width along the fiber and their surface showed numerous irregularities such as fissures.

The silk fibers also showed tremendous variabilities, even between fibers of the same species, in shape and size of their cross-section. *A. mimosae* and *E. bauhiniae* fibers had mostly flattened, elongated and rectangular shapes (Fig. 7e and h), while fibers of *G. postica* had globular and triangular cross-sections. The silk filaments spun by *A. panda* had crescent-shaped, triangular or round cross-sections. The fibers also showed great variability in the shape, size and number of voids present. Even though the study failed to quantify the number and size of the voids, the SEM micrographs showed that *B. mori* silk fibers had few and small voids compared to the wild silk fibers (data not presented).

#### 4. Discussion

From the cocoon macro and microstructures, it is evident that larvae ensure the pupae will be well protected from natural enemies and environmental calamities. The needle like spines and hairs on *G. postica* and *A. panda* are important structures for protecting

the larvae and cocoons against natural enemies such as predating birds. Peilger [10] reported that the genera *Gonometta* and *Boro-cera* embed what were previously protective body spines in the cocoon surface hence protecting the developing chrysalis. These spines and hairs can sometimes be irritant on contact and along with other cocoon chemicals and dusts might be reasons for eye and skin irritations that make working with the cocoons uncomfortable and causing allergies in workers. The surface and the interstices between fibers and layers of the cocoon shell of *G. postica* and *E. bauhiniae* cocoons are also packed with Calcium oxalate crystals, defecated during spinning, which confer lower risk of bird attack and hardening of the cocoon shells [11]. The functional adaptations of these crystals and the colour of cocoons range from camouflage to heat absorption or light transmission [12]. Other wild silk cocoons, such as *A. assama*, also showed the presence of calcium oxalate crystal deposits on their surface [13]. The difference in the size and shape of the crystals suggests the role they might have on influencing the texture of the cocoon surface. Reeling of silk from *Gonometta* and other wild silk cocoon shells with these crystals is difficult due to their extensive infiltration between the silk fibers [14]. The larvae of the wild silkmoths also utilized different mechanisms to ensure the cocoons are firmly

securely attached to a substrate before pupating. This prevents the cocoons from falling to the ground or being carried away by wind and water. Further, they are protected from attack from predators like birds. The silken petiole (peduncle) of *E. bauhiniæ* varied in fiber arrangement and compactness from the cocoon shells indicating that there might also be difference in the chemical composition. Such variations had been reported in *Antheraea mylitta*, where the peduncle sericin has higher molecular weight and slight difference in amino acid composition than the cocoon shells [15]. The other wild silk cocoons were sessile, however, had high sericin gum content at the attachment surface which contributed to strong binding to the substrate. The cocoon shell holes of *A. mimosæ* have adaptive significance by allowing fresh air exchange in the inner cocoon atmosphere where the pupae reside. Reddy and Gloor [16] also reported *Copaxa multifenestrata* (Saturniidae) have perforated construction with many holes on the surface of the cocoons.

Wild silk cocoon shells exhibited cross-linking and branching filaments forming an intricate network and irregularly shaped structures with more cementing gum between the filaments. Such structures of cocoon shells have been also reported in *A. mylitta* [17]. *B. mori* shells were more loosely arranged than their wild counterparts. Such loose arrangement together with comparatively complicated sericin removal might be an added advantage to its use in textile application by allowing easy reeling with minimum breaking percentage. The multilayered and porous structure of the cocoon shells serve as a mechanical barrier and offers a better energy absorbing property due to the wave impedance matching between different plies [18]. The spacing of the fibers varied with species mainly due to the spinning behaviour and amount of sericin and fibroin present. Such porous structure can also be viewed as a trade-off between optimizing the use of a limited amount of raw materials from the silk gland and construction of efficiently woven cocoon structures which can withstand possible attacks from the outside. Tagawa and Sato [19] also emphasized the balance between economy and robustness of cocoons as important factors for cocoon-spinning insects.

The variability in fiber size, surface and cross-sectional structures might be due to wide variation in cocoon size [20]. Mbahin [21] and Nel [22] reported that the size of *A. panda* and *G. postica* silk fibers are about 20 and 15–25 µm, respectively. The cross-sectional shapes of the brins were rectangular, wedge-shaped, triangular, globular in wild silk fibers. This is in agreement with reports on other wild silk species [23,24]. Freddi et al. [25] reported that threads spun by *Gonometa rufobrunnae*, are variable in cross-sectional dimension and can be round, triangular or even flat and ribbon like. Fibers of *A. mimosæ* and *E. bauhiniæ* exhibited a distinctly flattened surface with longitudinal micro fibrils similar to *A. mimosæ* silk fibers [13]. Thus, it can be concluded that these fibers are made up of bundles of microfibrils oriented along the fiber axis. The larval body movement, speed of spinning, twisting and stretching during the cocoon forming process and elasticity of the fibers when emerging from the spinnerets might force the fibers to acquire different shapes and sizes. The resulting cross-sectional size and shape of fibers have been reported to have a direct relationship with the yarn's luster, friction and mechanical properties [26]. The wrinkles on outer cocoon surfaces are formed due to non-uniform stretching during drying [1].

The cocoon filaments of various wild silkmoth species were also found to have voids which were absent in *B. mori* silk fibers [7,27]. However, in this study, we observed the presence of voids in *B. mori* fibers. Narumi et al. [28] and Mondal et al. [29] also reported the rare voids in cocoon filaments of *B. mori* and *B. mandarina*. The African wild silk fibers have larger and numerous voids which could be an advantage for their chemical modifications as these voids play a significant role in the penetration of water and other chemicals to the fiber resulting in marked increase in cross-section.

## Acknowledgments

Thanks are due to *icipe*-African Insect Science for Food and Health for providing logistical and research support. We are indebted to Rolf Gloor, Cabesi project leader, for providing *E. bauhiniæ* cocoons. We also highly appreciate the technical support of the Oxford Silk Research Group members in sample preparation and viewing with SEM.

## References

- [1] H. Zhao, X. Feng, S. Yu, W. Cui, F. Zou, *Polymer* 46 (2005) 9192–9201.
- [2] H. Cheung, K. Lau, Y. Zhao, J. Lu, *Adv. Mater. Res.* 47 (50) (2008) 1213–1216.
- [3] B.E. Lyon, R.V. Cartar, *Proc. R. Soc. Lond. Ser. B: Biol. Sci.* 263 (1996) 1159–1163.
- [4] H.V. Danks, *Eur. J. Entomol.* 101 (2004) 4333–4437.
- [5] N. Reddy, Y. Yang, *Int. J. Biol. Macromol.* 46 (2010) 419–424.
- [6] B.V. Vasumathi, C. Takabayashi, N. Kenichi, H.S. Turvekere, *J. Insect Biotechnol. Sericol.* 73 (2004) 47–56.
- [7] T. Narumi, M. Kobayashi, T. Mori, *J. Seric. Sci. Jpn.* 62 (1993) 489–495.
- [8] K. Sen, M.K. Babu, *J. Appl. Polym. Sci.* 92 (2) (2004) 1080–1097.
- [9] S. Das, *Indian Text. J.* 102 (12) (1992) 42–46.
- [10] R.S. Peigler, *Galathea (Nürnberg) (Suppl. 15)* (2004) 23–30.
- [11] R. Veldtman, *The ecology of southern Africa wild silk moths (Gonometa species, Lepidoptera: Lasiocampidae): consequences for their sustainable use*, PhD thesis, University of Pretoria, 2005.
- [12] R.S. Peigler, *Am. Entomol.* 39 (3) (1993) 151–161.
- [13] G. Freddi, Y. Gotoh, T. Mori, I. Tsutsui, M. Tsukada, *J. Appl. Polym. Sci.* 52 (6) (1994) 775–781.
- [14] H. Akai, T. Nagashima, *Int. J. Wild Silkmoths Silk* (2003) 1–5.
- [15] R. Dash, S. Mukherjee, S.C. Kundu, *Int. J. Biol. Macromol.* 38 (3–5) (2006) 255–258.
- [16] N. Reddy, Y. Yang, *J. Mater. Sci.* 45 (16) (2010) 4414–4421.
- [17] G. Shamitha, A.P. Rao, *Curr. Sci.* 90 (12) (2006) 1667–1671.
- [18] L. Tsai, V. Prakash, *Int. J. Solids Struct.* 42 (2005) 727–750.
- [19] J. Tagawa, Y. Sato, *Eur. J. Entomol.* 106 (3) (2009) 353–356.
- [20] K. Komatsu, in: Hojo (Ed.), *The Chemical and Structure of Wild Silks*, Shinshu University, Ueda, 1980, pp. 353–377.
- [21] N. Mbahin, *the ecology and economic potential of wild silkmoth Anaphe Panda (Boisduval) (Lepidoptera: Thaumetopoeidae) in the Kakamega Forest*, Thesis submitted in fulfillment of the requirements for the award of the Degree of Doctor of Philosophy in Agricultural Entomology, School of Pure and Applied Sciences, Kenyatta University, Kenya, 2008.
- [22] F. Nel, *The evaluation of mixed yarn fabrics of Gonometa postica silk, acrylic and wool*, Dissertation submitted in accordance with the requirements for the Master of Science in Home Economics in the Faculty of Natural and Agricultural Sciences, Department of Microbial, Biochemical and Food Biotechnology: Consumer Science at the University of the Free State, Bloemfontein, South Africa, 2007.
- [23] G. Buschle-Diller, *Substrates and their structure*, in: A. Cavaco-Paulo, G.M. Gubitza (Eds.), *Textile Processing with enzymes*, CRC Press, USA, 2003.
- [24] K. Zhang, F.W. Si, H.L. Duan, J. Wang, *Acta Biomater.* 6 (2010) 2165–2171.
- [25] G. Freddi, A. Bianchi Svolokos, H. Ishikawa, M. Tsukada, *J. Appl. Polym. Sci.* 48 (1993) 99–106.
- [26] T. Narumi, M. Kobayashi, *J. Seric. Sci. Jpn.* 64 (1995) 203–208.
- [27] Y. Lin, T. Liou, C. Liu, Y. Liu, T. Wu, Y. Chang, *Wild Silkmoths '92*, International Society for Wild Silkmoths, Tsukuba, Japan, 1993, pp. 105–114.
- [28] T. Narumi, M. Kobayashi, T. Mori, *Wild Silkmoths '91*, International Society for Wild Silkmoths, Tsukuba, Japan, 1992, pp. 179–185.
- [29] M. Mondal, K. Trivedy, S. Nirmal Kumar, *J. Entomol.* 4 (2007) 362–370.

## Study on Weight Loss and Moisture Regain of Silk Cocoon Shells and Degummed Fibers from African Wild Silkmoths

<sup>1</sup>Addis Teshome, <sup>1</sup>S.K. Raina, <sup>3</sup>F. Vollrath, <sup>2</sup>J.M. Kabaru, <sup>2</sup>J. Onyari and <sup>1</sup>E.K. Nguku

<sup>1</sup>International Centre for Insect Physiology and Ecology, P.O. Box-30772-00100, Nairobi, Kenya

<sup>2</sup>School of Biological Sciences, University of Nairobi, P.O. Box 30197-00100, Kenya

<sup>3</sup>Department of Zoology, Oxford University, South Parks Road, Oxford OX1 3PS, United Kingdom

Corresponding Author: Addis Teshome, International Centre for Insect Physiology and Ecology, P.O. Box 30772-00100, Nairobi, Kenya

### ABSTRACT

A study was conducted to determine weight loss and moisture regain properties of silk cocoon shells, shell layers and degummed fibers of the four African wild silkmoths *Anaphe panda*, *Argema mimosae*, *Epiphora bauhinae* and *Gonometa postica* and compare with the industry standard mulberry silkmoth, *Bombyx mori*. No. significant difference was observed between the moisture regain of the wild silk fibers after degumming. However, there were significant differences in weight loss and moisture regain between cocoon shells as well as shell layers. *E. bauhinae* had the lowest weight loss and moisture regain of 23.19 and 5.64%, respectively while *G. postica* had the highest weight loss and moisture regain, 56.84 and 9.05%, respectively. The SEM micrographs also showed the presence of remnant sericin gum on the fibers surface. In both *A. panda* and *E. bauhinae*, the outer shell layers had the lowest moisture regain and highest weight loss while the inner layer of *E. bauhinae* and middle layer of *A. panda* lost the least weight. The physical structure and chemical composition of the cocoon shells and fibers contribute towards the variation in the moisture regain and weight loss and these features may have commercial implications due to their direct effect on the resulting fabric.

**Key words:** *Bombyx mori*, cocoon layer, silk fiber, sericin, wild silkmoth

### INTRODUCTION

Silks are natural polymers which have been gaining wide use in variety of applications such as degradable biomaterials, biomedical and functional bio-membrane materials and fibers besides their traditional use as a textile raw material (Zhang, 2002; Mondal *et al.*, 2007a; Wilaiwan *et al.*, 2010). The use of such silks, depending on their origin, can be justified both by the combination of mechanical properties, non-toxicity, biocompatibility and biodegradability depending on source and treatment. African wild silk fibers from Saturniidae (*Epiphora* and *Argema* spp.), Lasiocampidae (*Gonometa* spp.) and Thaumetopoeidae (*Anaphe*, *Epanaphe* and *Hyposoides* spp.) genera produce silk of potential commercial value and with significant economic importance due to their interesting mechanical properties (Raina, 2004; Delport, 2006). However, the performances of all silk biopolymers are affected when exposed to adverse environments.

Specifically, absorbed moisture is likely to determine the mechanical and physical properties of both the sericin gum coating and the integral structural proteins of the silks (Fut *et al.*, 2009). Some silks can indeed be hygroscopic with a moisture regain of 11 at 65% Relative Humidity (RH) and



27°C (Ranganathaian, 2003; Sonthisombat and Speakman, 2004) which is larger than many other commercial fibers and more in line with wool (Salamone, 1999). This interaction of moisture and fiber has technical as well as commercial consequences. For example, in *Bombyx mori* Linn. silk, the absorption of water causes 1.6% fiber swelling in the longitudinal crosswise (Schoeser, 2007). This apparently small degree of swelling can influence the rate of heat and moisture vapour transfer through the textile fiber. Moreover, the weight change resulting from moisture absorption can affect the commercial weight of the fibers as well as affecting properties such as dyeing, finishing and apparent comfort of the product (Salamone, 1999).

However, most silk contains not only the fiber matrix protein but in addition have a coating of sericin or similar compounds. This sericin component of the composite silk fibre (typically of two fibre brins held together into the bave by the sericinaceous gum), is usually expressed as weight loss and is an important additional factor affecting the quality of a silk (Vishuprasad, 2004). The sericin content of a fiber is estimated by boiling silk (using a range of chemicals) and calculating the weight loss (Sonthisombat and Speakman, 2004). This weight loss from a raw silk filament depends on the water solubility and higher alkali sensitivity of the sericin as compared to the fibroin (Choundhury, 2006). Quantity and nature of sericin are fundamental characteristics in conferring distinctive traits to the cocoon. Sericin coating has important biological properties such as oxidation and UV resistance as well as antibacterial and moisture control properties (Mondal *et al.*, 2007a). However, the sericin coating also gives a callous and stiff feeling to the fiber and hides the rich luster and whiteness of the silk brins (Arami *et al.*, 2007) in addition to preventing the penetration of dye. These necessitate its removal by process of boiling to obtain an ideal fiber for the textile industry and any other specific applications. Because of these effects, understanding the amount of sericin present in silk bave as wells as their water absorption properties of fibers has considerable technical implications for a silk as a commercial proposition. Hence, this study was conducted with the objective to determine the quantity of sericin gum and moisture regain properties in African wild silk cocoon shells and fibers.

## MATERIALS AND METHODS

**Weight loss:** This study was conducted between June to August, 2010 at the International Centre of Insect Physiology and Ecology, Commercial Insects Program Laboratory. Cocoon shells of four wild silk species were collected from four rather different ecotypes in Kenya namely; the Kakamega (*Anaphe panda* Biosduval), the Arabuko Sokoke (*Argema. Mimosa* Biosduval), the West Pokot (*E. bauhiniæ* Guer) and Mwingi district acacia bush lands (*G. postica* Walker) (Fig. 1). Cocoons of *B. mori* (Race ICIPE II) were obtained for comparison from the Commercial Insect Program of icipe, International Centre for Insect Physiology and Ecology. Cocoons were cut with a surgical blade and cleaned by removing the pupal debris and other foreign materials such as leaves and branches. Twenty grams of cleaned cocoons were enclosed in wire mesh cages with a volume of 717 cm<sup>3</sup> and boiled with 5 g L<sup>-1</sup> of Na<sub>2</sub>CO<sub>3</sub> (Magadi soda) solution for 180 min. Boiled cocoons were soaked in star soft solution of 50 mL L<sup>-1</sup> of distilled water for 3 min and washed with hot and cold distilled water twice. Excess water was removed by filter paper and cocoon filaments were allowed to spend 24 h in oven at 110°C to insure uniform drying. The weight loss, expressed in percentage, was obtained using the equation (Nakpathom *et al.*, 2009).

**Moisture regain of cocoon shells:** Moisture regain of undegummed but clean and weighed cocoon shells was determined by the oven drying procedure. Known weight of cocoon shells were

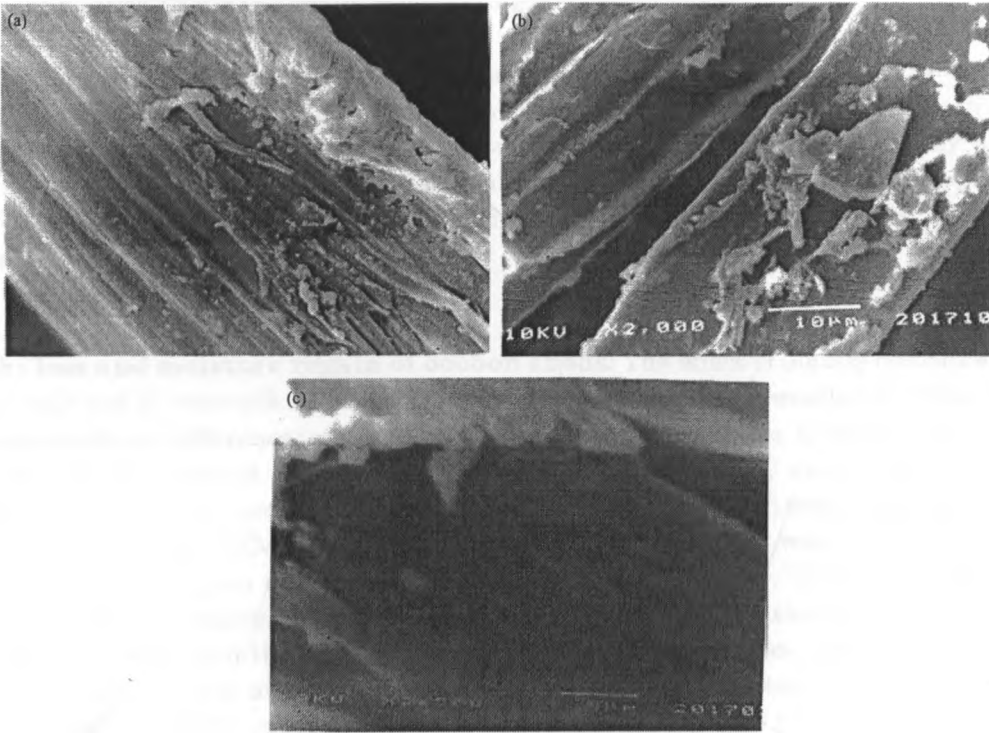


Fig. 1: Degummed fibers of (a) *Argema mimosae*, (b) *Anaphe panda* and (c) *Gonometa postica* showing the remnant gum

placed in an oven at 110°C for 24 h. Twenty grams of oven dried shells were placed at laboratory bench for 72 h at room conditions (23±2°C and 71±3% RH). The moisture regain percentage for the cocoon shells was obtained by Nawaz *et al.* (2002).

To avoid initial weight gain during the weighing process care was taken not to expose the samples to moisture.

**Moisture regain of degummed fibers:** Cleaned cocoon shells were first dugmmed and then dried in the oven for 24 h at 110°C. Twenty gram of degummd fibers were left on laboratory bench under room conditions (23±2°C and 71±3% RH) for 72 h. The moisture regain percentage for the fibers were obtained according to Nawaz *et al.* (2002).

**Weight loss and moisture regain of cocoon shell layers:** For this study, only cocoon shells of *A. panda* and *E. bauhiniae* were used. These species had been selected because of the clear distinction in the physical structure of the three layers; a leathery outer envelope, a fluffy intermediate layer and thick walled and rigid inner layer in their cocoon shells. Three distinct layers designated as outer, middle and inner were separated. Weight loss and moisture regain were determined by the same procedure as described above.

**Scanning Electron Microscope (SEM) observation:** Degummed fibre samples were embedded in black wool and mounted onto copper stubs using double side sticking tape. The mounted

specimens were immediately coated with gold (JEOL JFC-1100E ion sputter) and observed with SEM (JEOL-JSM T330A) under an accelerating voltage of 10 kV.

**Data analysis:** All percentage data were logarithmic transformed to stabilize the variance before the final statistical analysis. Both moisture regain and weight loss of the cocoon shells were analyzed using one-way Analysis of Variance (ANOVA) ( $p < 0.01$ ) while two-way analysis was employed to analyze the difference in cocoon layers of *A. panda* and *E. bauhiniae* with PROC ANOVA (SAS Institute, 2010). Least Significance Difference (LSD) test was used to separate means.

## RESULTS

**Weight loss and moisture regain of cocoon shells:** The effect of boiling cocoons shells of four African wild and *B. mori* silk on weight loss and moisture regain is presented in Table 1. There was a highly significant difference in weight loss between the cocoon shells. *G. postica* and *E. bauhiniae* cocoons had the highest and lowest weight loss (57 and 23%, respectively). *B. mori* and *A. mimosae* cocoons had comparable weight losses (29 and 31%) which were marginally higher than *A. panda* (26%). The SEM micrographs revealed that the fibers were covered with different quantities of sericin gum after the degumming treatment (Fig. 1). There were also significant differences in the moisture regain percentage between cocoon shells and degummed fibers. *A. mimosae* cocoons had the highest regain (9%) while *E. bauhiniae* cocoons gained the lowest moisture (5.64%). *B. mori* and *A. panda* cocoons gained marginally (statistically insignificant) more moisture (7.93 and 8.02%, respectively) than *G. postica* cocoon shells (7.11%) (Table 1). In contrast to the cocoon shells, the moisture regain of degummed wild silk fibers was not significantly different between species with *E. bauhiniae*, *G. postica* and *A. panda* gaining 10, 9.9 and 9.9%, respectively. However, *B. mori* had the lowest value (8.53%) which was significantly different from the other wild fibers (Table 1).

**Moisture regain and weight loss of cocoon shell layers:** Moisture regain of layers of *E. bauhiniae* and *A. panda* cocoon shells is shown in Table 2. There was significant difference in moisture regain of cocoon shell layers of *E. bauhiniae* and *A. panda*. The inner hard layers of both species have the highest regain (6.8 and 8.6% for *E. bauhiniae* and *A. panda*, respectively).

Table 1: Mean±SE of weight loss and moisture regain of African wild cocoons and degummed fibers

Species	Weight loss (%)	Moisture regain (%)	
		Cocoon shells	Degummed fibers
<i>B. mori</i>	29.35±0.18 <sup>bc</sup>	7.93±0.35 <sup>ab</sup>	8.53±0.32 <sup>b</sup>
<i>G. postica</i>	56.84±0.32 <sup>a</sup>	7.11±0.53 <sup>b</sup>	9.95±0.46 <sup>a</sup>
<i>E. bauhiniae</i>	23.19±0.45 <sup>d</sup>	5.64±0.62 <sup>c</sup>	10.42±0.34 <sup>a</sup>
<i>A. mimosae</i>	31.39±0.97 <sup>b</sup>	9.05±0.52 <sup>a</sup>	9.75±0.39 <sup>a</sup>
<i>A. panda</i>	25.55±3.63 <sup>cd</sup>	8.02±0.35 <sup>ab</sup>	9.91±0.22 <sup>a</sup>
CV	3.97	6.86	3.24
df	4	4	4
F-value	26.96	7.18	4.27
p-value	<0.01	<0.05	<0.05

\*Means followed by the same letter in a column are not statistically significant ( $p < 0.05$ ) using the least significant difference test (LSD)

Table 2: Mean±SE of moisture regain of layers of *E. bauhiniae* and *A. panda* cocoon shells

Species	Layer	Moisture regain (%)	
		Cocoon shells	Degummed fibers
<i>E. bauhiniae</i>	Outer	5.27±0.35 <sup>c</sup>	8.5±0.23 <sup>a</sup>
	Middle	5.0±0.49 <sup>c</sup>	8.63±0.72 <sup>a</sup>
	Inner	6.83±0.35 <sup>b</sup>	8.37±0.22 <sup>a</sup>
CV		7.46	4.26
df		2	2
F-value		5.95	0.05
p-Value		<0.05	>0.05
<i>A. panda</i>	Outer	6.96±0.56 <sup>b</sup>	8.85±0.42 <sup>b</sup>
	Middle	7.46±0.03 <sup>ab</sup>	8.43±0.06 <sup>ab</sup>
	Inner	8.63±0.45 <sup>a</sup>	9.49±.08 <sup>a</sup>
CV		8.97	4.83
df		2	2
F-value		4.63	4.61
p-value		<0.05	<0.05

\*Means followed by the same letter in a column are not statistically significant (p<0.05) using the least significant difference test (LSD)

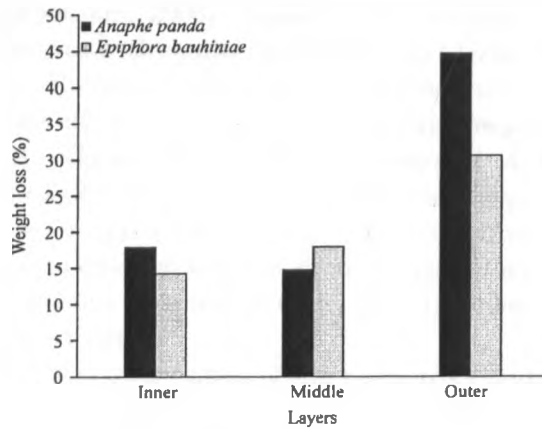


Fig. 2: Weight loss of the three layers of *A. panda* and *E. bauhiniae* cocoon shells

However, there was no significant difference between the regain percentages of degummed shell layer fibers of *E. bauhiniae* while *A. panda* degummed layer fibers showed significant difference with the inner layer gaining more moisture (9.4%). The moisture regain for *A. panda* shell layers progressively increased towards the inner layer. There was highly significant difference in weight loss in both species. The outer skin like layers had the highest weight losses of 30.5 and 44.6% for *E. bauhiniae* and *A.panda*, respectively and the weight loss significantly decreased to the inner layer in *E. bauhiniae* (Fig. 2).

**DISCUSSION**

The result clearly demonstrated that weight loss and moisture regain varies among the African wild silk cocoon shells and degummed fibers. The weight loss and moisture regain for *B. mori* was well within the limits of other studies, 19 to 30% (Arami *et al.*, 2007; Gulrajani, 1988;

Sarovart *et al.*, 2003) and 6.7 to 12% (Maji *et al.*, 2002), respectively. In this study, the weight loss of wild silk fibers ranged from 23 to 56.8% and is inconsistent with previous reports that the sericin content of wild silk fibers is less than the mulberry silk and is as low as 12-16% (Cavaco-paulo and Gubitz, 2003; Prasong *et al.*, 2009). Karumar (1999) reported 5-15% sericin gum coating content for tussah silk fibers. The degumming loss in *Antheraea proylei*, *A. assama*, *A. pernyi* and *A. yamamai* was in the range of 7-13% except for *A. mylitta* and *Philosamia Cynthia ricicni* which showed a 3.7 and 4.5% loss, respectively (Kato, 1991). However, higher sericin (gum) content of 38, 45 and 67.9% have been reported for Thai silk, *Rondotia menciaana* and *Bombyx mandarina* cocoon shells, respectively (Dhavalikar, 1962; Ito *et al.*, 1992). The food plants and the environment might have contributed to the higher quantity and differential solubility of sericin gum in African wild silk cocoon shells. Despite these higher values, the weight losses reported in this study for the wild silk cocoons might not be the true reflection of the gum content of the cocoons as verified by the intact inner hard parchment like layers for *A. panda* and *E. bauhiniae* and traces of sericin gum observed on the SEM images after degumming.

The variations in the amount of gum cementing substance (sericin) and fibroin in the cocoons shells might be due to a number of factors including taxonomic (genetic) difference in the sericin protein as well as external environmental variables (Shamitha and Purushotham, 2006) which together can determine the quality of cocoons for commercial purposes (Singhvi and Bose, 1991 cited in Shamitha and Purushotham, 2006). According to Kato and Hata (1998), the cocoon filaments of polyphagous silkworms with coarse filaments have higher values for the degumming loss than conventional cocoon filaments. This can be an explanation for the high weight loss of *G. postica* which is a polyphagous silkworm feeding on more than one acacia host plants including *Acacia tortilis*, *A. elatior*, *A. nilotica*, *A. mellifera*, *A. mearnsii*, *A. hockii* and *A. brevispica* (Fening *et al.*, 2008; Ngoka *et al.*, 2007). Nasreen *et al.* (1999) also reported difference in quality of *B. mori* cocoons from larvae fed on mixed leaves. Chemical composition of sericin also affects its solubility in hot water resulting in considerable variation in weight loss (Komatsu, 1975; Robson, 1985). The presence of certain amount of sericin after degumming shows its important role in the processing and application of the fibers.

Physical properties and chemical composition of silk fibers from mulberry and wild silkmths exhibit variability in different parameters (Mondal *et al.*, 2007b; Srisuwan and Srihanam, 2009). Degummed wild silk fibers have higher regains than those of commercial mulberry silk fibers. Sen and Babu (2004) also observed similar results with the non-mulberry silk fibers having marginally higher moisture regain values of 10.76%. This is in contrast with Snowalker (1993) who reported degummed fibers to have lower moisture regain due to the loss of sericin. The difference in moisture regain might be due to variations in compactness of fibers, change in the quantity, composition and chemistry of the gum and surface structure of the shells. The moisture regain of cocoon shells and fibers could provide information on the extent of areas accessible to water vapour within the fibre. The higher moisture regain for *A. mimosae* cocoon shells might be due to the presence of holes/perforations in the cocoon surface providing more area for moisture ingress. The presence of higher ratios of hydrophilic versus hydrophobic amino acid residues in the chemical architecture of non mulberry compared to mulberry silks may also affect in the higher moisture regain of the wild silks.

The study showed decreased weight loss and increased moisture regain from outer to inner shell layers. Nawaz *et al.* (2002) revealed with the change in filament type and size (denier), moisture regain changes significantly due to the difference in structures of fibres as well as changes in liner

density and the arrangement of monomers in the polymer (Munro, 1987). The presence of foreign matters such as dust and the hair like bristles on the outer layer of *A. panda* suggested the influence of physical structure in preventing fibers from absorbing moisture. The variation in weight loss and moisture regain among the different shell layers can be the demonstration of the difference in the amount and composition of sericin present in each layer. Such layer wise variation in cocoon property down the cocoon layers may confound objectionable fabric patterns either from visual or textural perspective (Das and Ghosh, 2010).

In conclusion, with other important qualities determined for some of the African wild silk cocoons and fibers, understanding the moisture regain and sericin content will have a significant importance in establishing quality parameters of the different fibers. The observed variation in the properties of cocoon layers suggests the need for separate boiling of layers in contrast to the usual practise of mass boiling if that were practically possible. Finally, present result suggests the need to selection bespoke degumming techniques for each type of silk in order to optimize the quality and quantity of the fibers that can be drawn from the different cocoon shells.

#### ACKNOWLEDGMENTS

Thanks are due to ICIPE-African Insect Science for Food and Health for providing logistical and research support. We are indebted to Rolf Gloor, Cabesi project leader, for providing *E. bauhiniæ* cocoons. We also highly appreciate the technical support of other staff of the Commercial Insect Program.

#### REFERENCES

- Arami, M., S. Rahimi, L. Mivehie, F. Mazaheri and N.M. Mahmoodi, 2007. Degumming of Persian silk with mixed proteolytic enzymes. *J. Applied Polymer Sci.*, 106: 267-275.
- Cavaco-paulo, A. and G.M. Gubitz, 2003. *Textile Processing with Enzymes*. CRC Press, USA.
- Choundhury, A.K.R., 2006. *Textile Preparation and Dyeing*. Science Publishers, Enfield, NH, USA.
- Das, S. and A. Ghosh, 2010. An investigation on the progressive change in filament characteristics from outer to inner layers of mulberry and tasar cocoons. *J. Applied Polymer Sci.*, 117: 1319-1324.
- Delpont, W., 2006. Population genetic inference of demographic processes in the African wild silk moth, *Gonometa postica* (Lasiocampidae). Ph.D. Thesis, University of Pretoria.
- Dhavalikar, R.S., 1962. Amino acid composition of Indian silk fibroins and sericins. II. Sericins. *Indian J. Sci. Ind. Res.*, 21: 303-304.
- Fening, K.O., E.N. Kioko, S.K. Raina and J.M. Mueke, 2008. Monitoring wild silkworm, *Gonometa postica* Walker, abundance, host plant diversity and distribution in Imba and Mumoni woodlands in Mwingi, Kenya. *Int. J. Biodiver. Sci. Ecosyst. Serv. Manage.*, 4: 104-111.
- Fut, C., D. Porter and Z. Shao, 2009. Moisture effects on *Antheraea pernyi* silk's mechanical property. *Macromolecules*, 42: 7877-7880.
- Gulrajani, M.L., 1988. Degumming of Silk. In: *Silk Dyeing Printing and Finishing*, Gulrajani, M.L. (Ed.). Indian Institute of Technology, Hauz Khas, New Delhi, pp: 63-95.
- Ito, T., J. Xu, K. Hamano, T. Inokuchi and M. Yamada, 1992. Amino acid composition of cocoon shell of the mulberry white caterpillar, *Rondotia menciæna* and the wild silk worm, *Bombyx mandarina*. *J. Seric. Sci. Jap.*, 61: 105-109.
- Karumar, S.R., 1999. *Chemical Technology in the pre treatment process of textiles*. 1st Edn., Elsevier Science, New York.

- Kato, H. and T. Hata, 1998. Degumming and dyeing properties of cocoon filaments with a special feature differed from conventional silkworm races. *Bull. Natl. Inst. Seric. Entomol. Sci.*, 20: 101-114.
- Kato, H., 1991. Tests for production of blended yarns with anisoshrinking from mori silk and reeled raw threads of wild silks. *J. Seric. Sci. Jap.*, 60: 432-444.
- Komatsu, K., 1975. Studies on dissolution behaviors and structural characteristic of silk sericin. *Bull. Sericult. Exp. Stn.*, 26: 135-256.
- Maji, T.K., D. Basu, C. Datta and A. Banerjee, 2002. Studies of mechanical and moisture regain properties of methyl methacrylate grafted silk fibers. *J. Applied Polym. Sci.*, 84: 969-974.
- Mondal, M., K. Trivedy and S.N. Kumar, 2007a. The silk proteins, sericin and fibroin in silkworm, *Bombyx mori* Linn., a review. *Caspian J. Environ. Sci.*, 5: 63-76.
- Mondal, M., K. Trivedy and S.N. Kumar, 2007b. Scanning electron microscopic study on the cross sections of cocoon filament and degummed fiber of different breeds/hybrids of mulberry silkworm, *Bombyx mori* Linn. *J. Entomol.*, 4: 362-370.
- Munro, J.M., 1987. *Cotton*. 2nd Edn., Longman Group Ltd., UK.
- Nakpathom, M., B. Somboon and N. Narumol, 2009. Papain enzymatic degumming of thai *Bombyx mori* silk fibers. *J. Micr. Soc. Thailand*, 23: 142-146.
- Nasreen, A., G.M. Cheema and M. Ashfaq, 1999. Rearing of silkworm *Bombyx mori* L. on alternate food plants. *Pak. J. Biol. Sci.*, 2: 843-845.
- Nawaz, S.M., N.A. Jamil, A. Farooq and T. Mahmood, 2002. Comparative study of shrinkage and moisture regain of silk, viscose rayon and polyester filament yarn. *Int. J. Agric. Biol.*, 4: 493-495.
- Ngoka, B.M., E.N. Kioko, S.K. Raina, J.M. Mueke and D.M. Kimbu, 2007. Semi-captive rearing of the African wild silkworm *Gonometa postica* (Lepidoptera: Lasiocampidae) on an indigenous and a non-indigenous host plant in Kenya. *Int. J. Trop. Insect Sci.*, 27: 183-190.
- Prasong, S., S. Yaowalak and S. Wilaiwan, 2009. Characteristics of silk fiber with and without sericin component: A comparison between *Bombyx mori* and *Philosamia ricini* silks. *Pak. J. Biol. Sci.*, 12: 872-876.
- Raina, S.K., 2004. *Commercial Insects: A Practical Guide for Raising and Utilising Silkmoths and Honey Bess in Africa*. Vol. 1-3, ICIPE Science Press, Nairobi.
- Ranganathian, C., 2003. Positron Lifetime study of thermally induced microstructural changes in nastari silk fibers. *Chinese J. Polymer Sci.*, 21: 325-332.
- Robson, R.M., 1985. *Silk Composition, Structure and Properties*. In: *Hand Book of Fibre Science and Technology*, Lewin, M. and E.M. Pearce (Eds.). Merce. Dekker Inc, New York, pp: 649-700.
- SAS, 2010. *The SAS Statistical System*. Version 9.2 (32). SAS Institute, Carry, NC.
- Salamone, J.C., 1999. *Concise Polymeric Materials Encyclopaedia*. CRC Press, USA.
- Sarovart, S., B. Sudatis, P. Meesilpa, B.P. Grady and R. Magaraphan, 2003. The use of sericin as an antioxidant and antimicrobial for polluted air treatment. *Rev. Adv. Mater. Sci.*, 5: 193-198.
- Schoeser, M., 2007. *Silk*. Yale University Press, USA.
- Sen, K. and M.K. Babu, 2004. Studies on Indian silk. I. Macrocharacterization and analysis of amino acid composition. *J. Applied Polymer Sci.*, 92: 1080-1097.
- Shamitha, G. and R.A. Purushotham, 2006. Studies on the filament of tasar silkworm, *Antheraea mylitta* D (Andhra local ecorace). *Curr. Sci.*, 90: 1667-1671.
- Singhvi, N.R. and P.C. Bose, 1991. Sericin: A deciding factor for the quality of cocoons and raw silk. *Indian Silk*, pp: 26-28.

- Snowwalker, T.N., 1993. Handbook of Silk Technology. Newage International Publishers Ltd., New Delhi.
- Sonthisombat, A. and P.T. Speakman, 2004. Silk: Queen of fibers-The concise story. <http://www.en.rmutt.ac.th/prd/Journal/Silk-with-figuresnew.pdf>.
- Srisuwan, Y. and P. Srihanam, 2009. Dissolution of *Philosamia ricini* silk film: Properties and functions in different solutions. *J. Applied Sci.*, 9: 978-982.
- Vishuprasad, N., 2004. Composite quality index of silk cocoons-application of discriminant analysis. *J. Acad. Bus. Econ.*, Vol. 4, No. 1.
- Wilaiwan, S., S. Yaowalak, B. Yodthong and S. Prasong, 2010. Silk fibroin/gelatin hybrid films for medical applications: Study on chlorhexidine diacetate. *J. Biol. Sci.*, 10: 455-459.
- Zhang, Y.Q., 2002. Application of natural silk protein sericin in biomaterials. *Biotechnol. Adv.*, 20: 91-100.



## Mechanical and Thermal Degradation Properties of Silk from African Wild Silkmoths

Addis Teshome,<sup>1,2</sup> John M. Onyari,<sup>2</sup> Suresh K. Raina,<sup>1</sup> Jacques M. Kabaru,<sup>2</sup> Fritz Vollrath<sup>3</sup>

<sup>1</sup>ICIPE—African Insect Science for Food and Health, Environmental Health Division, Nairobi 30772-00100, Kenya

<sup>2</sup>School of Physical Sciences and School of Biological Sciences, University of Nairobi, Nairobi 30197-00100, Kenya

<sup>3</sup>Silk Research Group, Department of Zoology, University of Oxford, Oxford OX1 3PS, United Kingdom

Correspondence to: A. Teshome (E-mail: additi09@gmail.com or akebede@icipe.org)

**ABSTRACT:** Variations among silk of four African wild silkmoths, *Argema mimosae*, *Anaphe panda*, *Gonometa postica*, and *Epiphora bauhinae*, was studied regarding their mechanical properties and thermal degradation behaviors. Cocoon shells and individual degummed fibers were examined using tensile testing, thermogravimetric analysis, and scanning electron microscope (SEM). *A. mimosae* and *G. postica* cocoon shells had marginally higher initial moduli and strains at maximum stress. The stress–strain curves of *Bombyx mori* and *A. panda* degummed fibers lacked clear yielding points. *G. postica* fibers had the highest breaking energy (76.4 J/cm<sup>3</sup>) and breaking strain (41.3%). The ultimate tensile strength was the highest for *B. mori* (427 MPa). Fiber pull-out and detachment was predominant in fracture surfaces of both the cocoon shells and the fibers. Wild cocoon shells and degummed fibers had higher temperature for dehydration loss than *B. mori*. *A. mimosae* fibers (11.9%) and *G. postica* cocoon shells (13.3 %) had the highest weight loss due to dehydration. *E. bauhinae* cocoon shells and *B. mori* fibers had the highest total weight losses of 97.2 and 93.4%, respectively. The African silks exhibited variations in their mechanical and thermal degradation properties related to their physical and chemical structure and composition. © 2012 Wiley Periodicals, Inc. *J. Appl. Polym. Sci.* 127: 289–297, 2013

**KEYWORDS:** degradation; yielding; fibers; fracture; thermal properties

Received 15 December 2011; accepted 13 April 2012; published online 4 May 2012

DOI: 10.1002/app.37873

### INTRODUCTION

Natural fibers from animals and plants are gaining increasingly in importance, once again. Silk is a unique class of structural animal fiber and has long been regarded as a superb natural material due to its characteristic high strength, elongation, feel, and luster.<sup>1</sup> The variation in composition, structure, and properties of silks from different arthropods has led to its considerations in wider applications expanding from more traditional textile industries to fields such as biomedical, biotechnological, and tissue engineering. The usefulness of silk fibers in these and many other applications is associated with its predominant failure mechanism under the conditions of the application and its adaptability to varied environmental conditions facilitated by the silk's molecular composition and hierarchical structure. These, in turn, are both affected by the conditions during its production such as spinning speed, relative humidity, temperature, pH, ionic strength, solvent composition, and mechanical stress as well as the degumming process.<sup>2–5</sup> The mechanical properties of silk fibers also depend on the structure of the silk

constituent proteins (sericin and fibroin) before and after silk fiber formation.<sup>6</sup> For example, sericin coating can add to the tensile properties of silk fibers, although these are primarily determined by their fibroin structure.<sup>7</sup> Sericin might also affect the transition of silk fibroin from the random coil or  $\alpha$ -helix to the  $\beta$ -sheet structure and further improve the mechanical properties of silk fibroin fibers.<sup>8</sup> High crystallinity confers the silk material greater strength by virtue of the network of hydrogen bonds between and within the proteins.<sup>9</sup>

Temperature and moisture are among the environmental stresses influencing properties and functions of silk cocoons and fibers. Cocoon shells are important in temperature regulation, water loss reduction from the pupae, and acquisition of heat.<sup>10</sup> Temperature also influences the amount of water absorbed by silk fibers resulting in alteration of physical properties. Chemical composition and structure of silk fibers determine the thermal tolerance behavior of the cocoon shells and fibers and the resulting weight loss due to dehydration and/or decomposition. Hence, it is appropriate to deploy Thermal Analysis to

**Table I.** Tensile Properties of Cocoon Shells of *A. mimosae*, *G. postica*, and *B. mori*

Species	Initial modulus (MPa)	Maximum stress (MPa)	Strain at Max stress (%)	Breaking energy (J/cm <sup>3</sup> )
<i>A. mimosae</i>	404.6 ± 59.8a	69.6 ± 7.0c	21.2 ± 1.0a	13.8 ± 1.9b
<i>G. postica</i>	397.4 ± 63.4a	47.2 ± 1.7b	23.3 ± 1.2a	11.4 ± 0.6b
<i>B. mori</i>	334.5 ± 28.3a	101.1 ± 4.2a	20.8 ± 1.2a	20.1 ± 0.7a

Means followed by the same letter in the same column are not statistically significant ( $P > 0.001$ ) according to least significant difference (LSD) test.

investigate the response of natural materials to temperature scans and to explore together with other data, the structure–property–function relations of natural cocoons.<sup>11</sup> Accordingly, we set out to explore in a comparative study the mechanical properties and thermal degradation behavior patterns of cocoon shells and degummed fibers from four African wild silkmoths.

## MATERIALS AND METHODS

### Mechanical Properties of Cocoon Shells

Cocoon shells of two African wild silkmoths, *Gonometa postica* and *Argema mimosae*, were selected because of their single cocoon shell structure. *Bombyx mori* (Race *icipa* II) obtained from the Commercial Insects Programme, International Centre of Insect Physiology and Ecology (*icipa*) were also used for comparison. Five cocoon shells were used for each species. Two full cocoon shell strips (dimensions of 5 × 15 mm<sup>2</sup>) were cut longitudinally from each cocoon from the middle sections. Instron 5542 tensile testing instrument (500-N load cell) was used for tensile testing and all tests were carried out at room temperature with gauge length of 5 mm and at a speed of 2 mm/min.

### Mechanical Properties of Single Fibers

Cleaned cocoon shells were degummed by boiling with 5 g/L of Na<sub>2</sub>CO<sub>3</sub> solution for 1 (*B. mori*), 1.5 (*G. postica*), 3 (*Epiphora bauhiniiae* and *A. mimosae*), and 5 h (*Anaphe panda*). Boiled cocoons were soaked in star soft solution of 50 mL/L of distilled water for 3 min and washed twice with hot and cold distilled water. Fibers of 100-mm long were obtained by pulling gently and were allowed to dry overnight in air before testing. Silk fibers were cut gently into 30 mm to make sure that the fibers were not stressed plastically during the process. Before being tested, each specimen was examined under an optical microscope to ensure that only single fibers were used. Every cut fiber was then mounted and taped across a hole, which is 10-mm long, of a rectangular cardboard that was then fixed in an Instron machine. Cardboards were cut on both sides and separated

into two parts to ensure tensile loading was completely transmitted to the fiber during test. All tests were conducted at gauge length of 10 mm and speed of 0.1 mm/s at 22°C and 55% relative humidity. Ten tests were made for each species to generate the average tensile stress–strain curve. The tensile parameters were calculated with a home designed program in Excel (Tensile Import v2.0). The J-integral method was used to determine the energy to break. Stress–strain curves were plotted using Origin Pro 8. SAS (SAS institute 2010) was used for statistical analysis of the data with one-way analysis of variance (ANOVA). Cross-sectional areas of the fibers were prepared by clamping orientated silk threads in a holder and cutting them across with a new razor blade before sputtering them with gold (JEOL JFC-1100E ion sputter) and viewed under SEM (JEOL Neoscope JCM-5000 (Nikon, UK)). Digital images of transverse sections on SEM micrographs were manually circled and analyzed with ImageJ 1.42q. Normalized cross-sectional areas were obtained by averaging 50 brins for each sample assuming that sample volume is conserved during the tensile tests.<sup>12</sup>

### Fractography Analysis

Cocoon shells and fibers after the tensile failure were analyzed by SEM to investigate the fracture mechanism.

### Thermogravimetric Analysis

Disks of cocoon shell and degummed fibers (7-mm diameter) were pressed out from middle section of the cocoon and compressed degummed floss, respectively, with a sharp hole-punch. The samples were loaded into a Q500 thermogravimetric analysis (TGA) from thermal analysis (TA) instruments. The samples were scanned from room temperature to 900 and 800°C for cocoon shells and degummed fibers, respectively, at a heating rate of 20°C/min, N<sub>2</sub> flow of 60 mL/min and air cool time of 40 min. Five tests were made for each species, and results were averaged. Samples of cocoon shell and degummed fiber disks after thermogravimetric analysis (TGA) were viewed under SEM.

**Table II.** Tensile Properties of Single Degummed Silk Fibers

Species	Initial modulus (MPa)	Ultimate tensile strength (MPa)	Ultimate tensile strain (%)	Breaking energy (J/cm <sup>3</sup> )
<i>A. panda</i>	6344.4 ± 798.9b	365.1 ± 51.1ab	17.7 ± 0.7c	43.3 ± 7.2cd
<i>A. mimosae</i>	8326.5 ± 742.0a	363.4 ± 6.5ab	20.7 ± 1.0bc	51.6 ± 2.9bc
<i>E. bauhiniiae</i>	7497 ± 331.7ab	247.7 ± 6.3c	20.8 ± 1.3b	34.5 ± 2.4d
<i>G. postica</i>	7153.9 ± 544.6ab	310 ± 37.1b	41.3 ± 1.4a	76.4 ± 8.2a
<i>B. mori</i>	8787 ± 555.1a	427.6 ± 10.6a	21.8 ± 0.5b	66 ± 2.8ab

Means followed by the same letter in the same column are not statistically significant ( $P > 0.001$ ) according to LSD test.

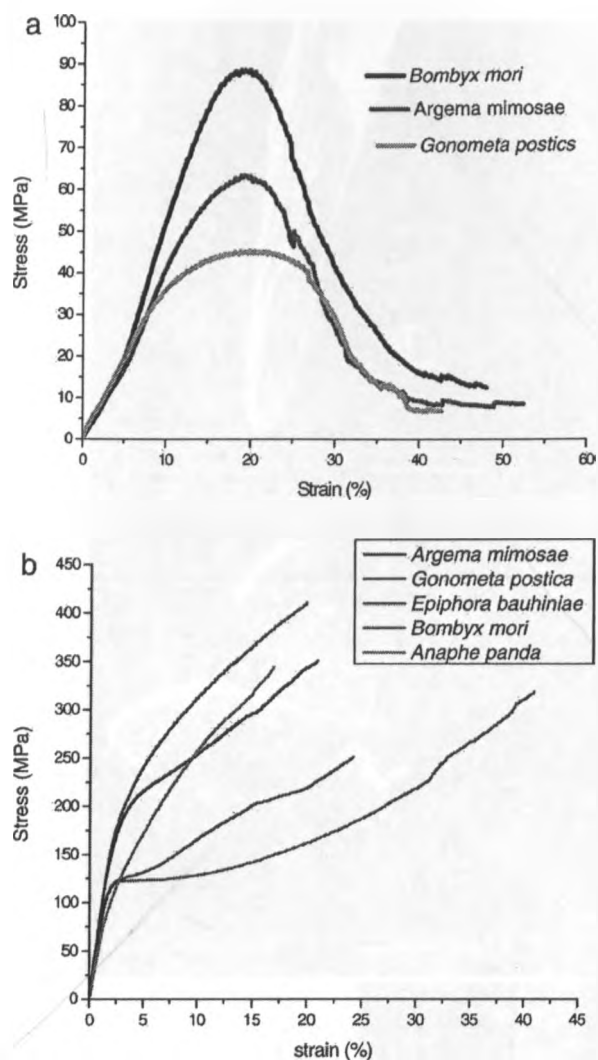


Figure 1. Stress-strain curves of cocoon shells and degummed fibers. [Color figure can be viewed in the online issue, which is available at [wileyonlinelibrary.com](http://wileyonlinelibrary.com).]

Table III. Cross-Sectional Area of Single Silk Fibers (Brin) and Thickness of Cocoon Shell Walls

Species	Area ( $\mu\text{m}^2$ )	n	Cocoon shell thickness (mm)	n
<i>A. panda</i>	$96.7 \pm 5.7c$	50	$0.379 \pm 0.01b$	50
<i>A. mimosae</i>	$388.5 \pm 14.5a$	50	$0.234 \pm 0.01d$	50
<i>E. bauhinae</i>	$100.4 \pm 5.3c$	50	$0.318 \pm 0.008c$	50
<i>G. postica</i>	$160.8 \pm 6.8b$	50	$0.536 \pm 0.008a$	50
<i>B. mori</i>	$60.2 \pm 2.1d$	50	$0.207 \pm 0.008e$	50

Means followed by the same letter in the same column are not statistically significant ( $P > 0.001$ ) according to LSD test.



Figure 2. SEM micrographs of fracture surfaces of cocoon shells after tensile failure.

## RESULTS

### Mechanical Properties

The measured data of the tensile properties of cocoon shells and degummed fibers are presented in Tables I and II, and

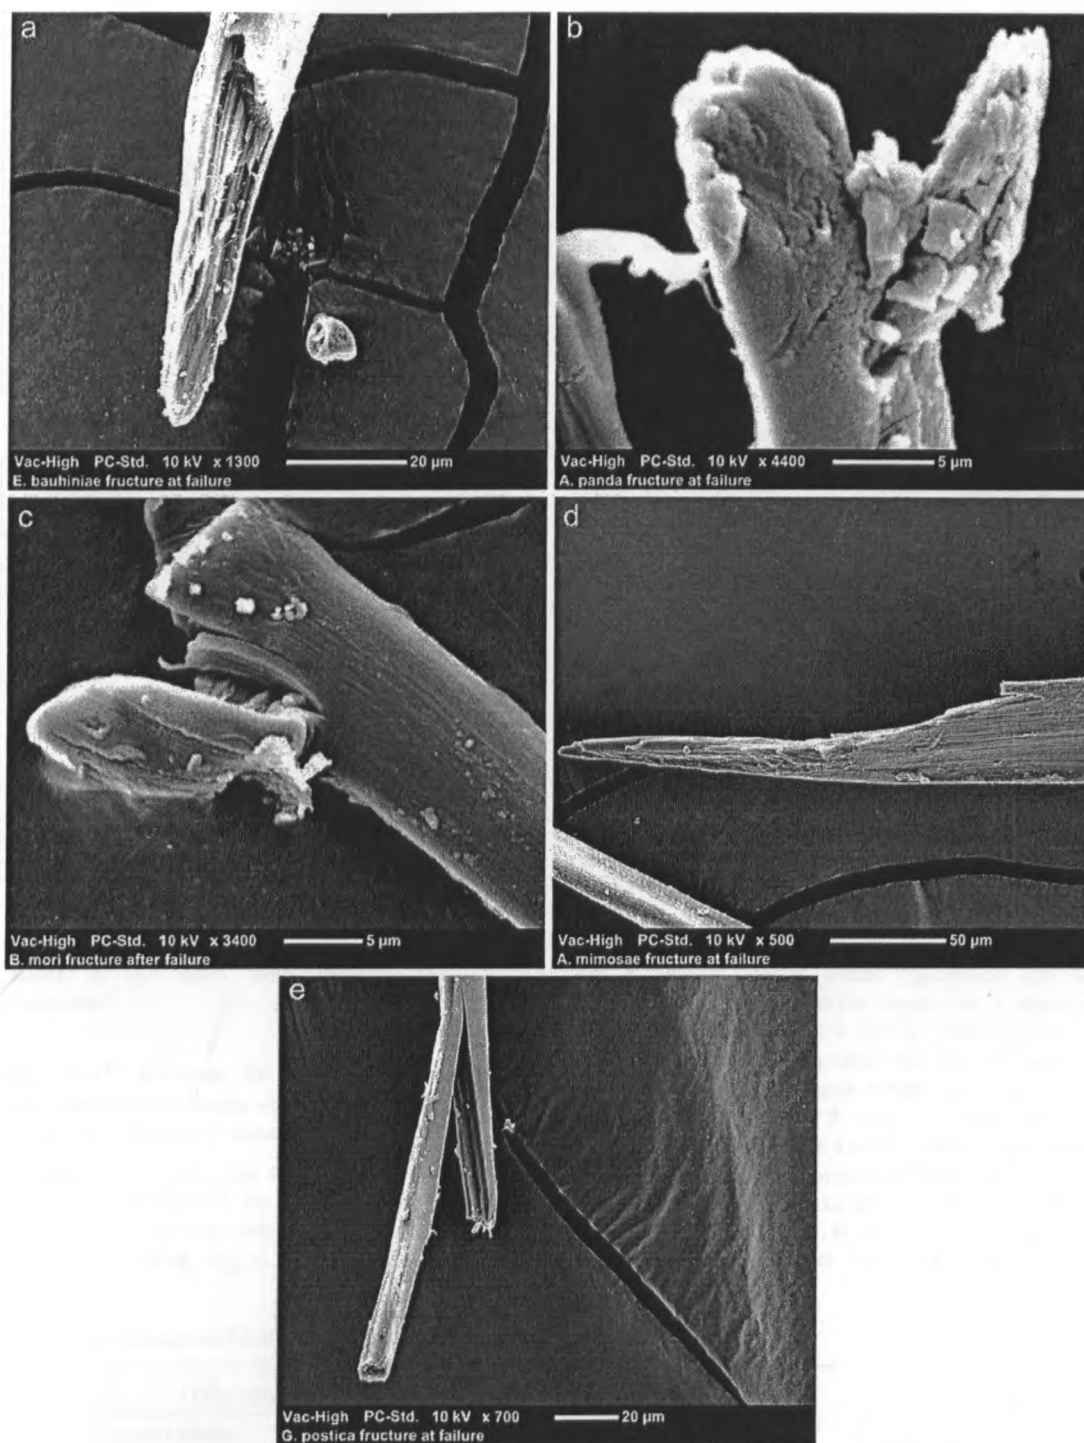


Figure 3. SEM micrographs of fracture surfaces of degummed fibers after tensile failure.

the average stress strain curves are presented in Figure 1(a,b). The results showed that the tensile properties of silk cocoon shells and degummed fibers differ between the species. For the cocoon shells, modulus reduced as strain increases and the binding points between fibers were observed to break

gradually. After a peak stress, there was rapid fall in stress, which indicated the continuous fiber bonding present in the cocoon shell that was wrecked, and simple entangled fibers were remained [Figure 1(a)]. *B. mori* cocoon shells had significantly higher maximum stress (101 MPa) and breaking

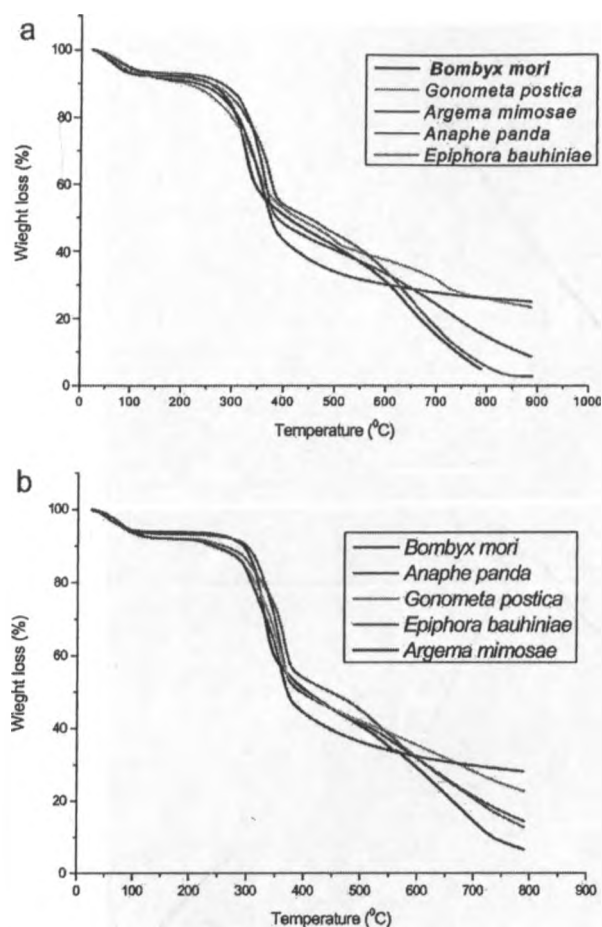


Figure 4. TGA curves cocoon shells and degummed fibers. [Color figure can be viewed in the online issue, which is available at [wileyonlinelibrary.com](http://wileyonlinelibrary.com).]

energy ( $20.1 \text{ J/cm}^3$ ). However, the wild cocoon shells had higher initial modulus and strain at maximum stress, though the values were not statistically significant (Table I).

Figure 1(b) shows that *B. mori* and *A. panda* fibers started with an elastic region followed directly by strain hardening where the stress increases nonlinearly with strain. The stress–strain curves of *A. mimosae*, *E. bauhiniae*, and *G. postica* fibers showed sig-

moidal shape, and an initial linear elastic region, yield region, and hardening regions were distinguished. *G. postica* fibers had the highest breaking energy ( $76.4 \text{ J/cm}^3$ ) and breaking strain (41.3%), whereas *E. bauhiniae* had the lowest breaking strain (247.7 MPa; Table II). *B. mori* had the highest breaking stress than the wild silk fibers (427.6 MPa), though it was not statistically significant with *A. panda* and *A. mimosae*. Despite the average cross-sectional area used to calculate the tensile properties, wild silk fibers showed noticeably higher standard deviation than *B. mori* indicating the considerable variation in the diameter of the fibers along their length and between fibers (Table III).

Fracture surfaces of the cocoon shells and single fibers were observed under SEM (Figures 2 and 3). Fiber debonding was observed after the tensile failure in all the species tested. Fibers of the cocoon shells were either broken or pulled out. *B. mori* and *G. postica* cocoons exhibited fiber pull-out. Detachment of the fibers was predominant in fracture surfaces with fairly clean and recognizable fiber surface without matrix adherence [Figure 2(a,c)]. *A. mimosae* cocoon shells were broken with a clear evidence of brittle failure, and few fibers were present holding the cocoon [Figure 2(b)]. *B. mori* and *A. panda* fibers seem to store the stress by stretching and then fail all at once [Figure 3(b,c)]. However, the rest of the fibers were without such process under stress and fracture smoothly. This appears to reflect the difference in the strain–stress curves.

#### TGA

Figure 4(a,b) illustrates the thermal decomposition behavior of cocoon shells and degummed fibers, respectively. The TG curves showed that weight loss due to dehydration of absorbed water molecules associated with cocoon shells occurred rapidly up to 101, 120, 125, 154, and 127°C for *B. mori*, *G. postica*, *E. bauhiniae*, *A. mimosae*, and *A. panda*, respectively. The dehydration loss from cocoon shells was the highest for *A. mimosae* (11.9%) and the lowest for *B. mori* (9.8%) (Table IV). A substantial weight loss followed the gradual decrease in weight as heating temperature increased. Rapid weight loss begun at 296, 311, 302, 309, and 303°C for *B. mori*, *E. bauhiniae*, *A. mimosae*, *A. panda*, and *G. postica* cocoon shells, respectively [Figure 4(a)]. The thermal decomposition of *G. postica* cocoon shells occurred in more steps than the rest of the species with rapid decompositions occurring at temperature ranges of 483–506 and 710–730°C. *A. mimosae* TGA curve showed that the cocoon

Table IV. Weight Loss of Degummed Fibers and Cocoon Shells after TGA

Species	Dehydration (%)		Decomposition (%)		Total weight loss (%)	
	Cocoon shells	Fibers	Cocoon shells	Fibers	Cocoon shells	Fibers
<i>A. panda</i>	$9.9 \pm 0.5b$	$11.1 \pm 0.4b$	$52.0 \pm 0.1b$	$51.5 \pm 0.3b$	$91.3 \pm 0.1b$	$85.9 \pm 4.0a$
<i>A. mimosae</i>	$11.9 \pm 0.1a$	$12.8 \pm 0.0a$	$61.2 \pm 0.5a$	$59.2 \pm 1.9a$	$74.9 \pm 0.5c$	$71.8 \pm 1.0b$
<i>E. bauhiniae</i>	$11.8 \pm 0.1a$	$11.9 \pm 0.0b$	$46.5 \pm 0.3d$	$47.2 \pm 1.2c$	$97.2 \pm 0.1a$	$87.3 \pm 2.3a$
<i>G. postica</i>	$11.5 \pm 0.8a$	$13.3 \pm 0.4a$	$50.4 \pm 1.1c$	$53.1 \pm 1.4b$	$71.2 \pm 1.5d$	$77.3 \pm 3.4b$
<i>B. mori</i>	$9.8 \pm 0.1b$	$8.5 \pm 0.3c$	$49.5 \pm 0.2c$	$54.6 \pm 0.3b$	$95.1 \pm 0.4a$	$93.4 \pm 2.4a$

Means followed by the same letter in the same column are not statistically significant ( $P > 0.001$ ) according to LSD test.

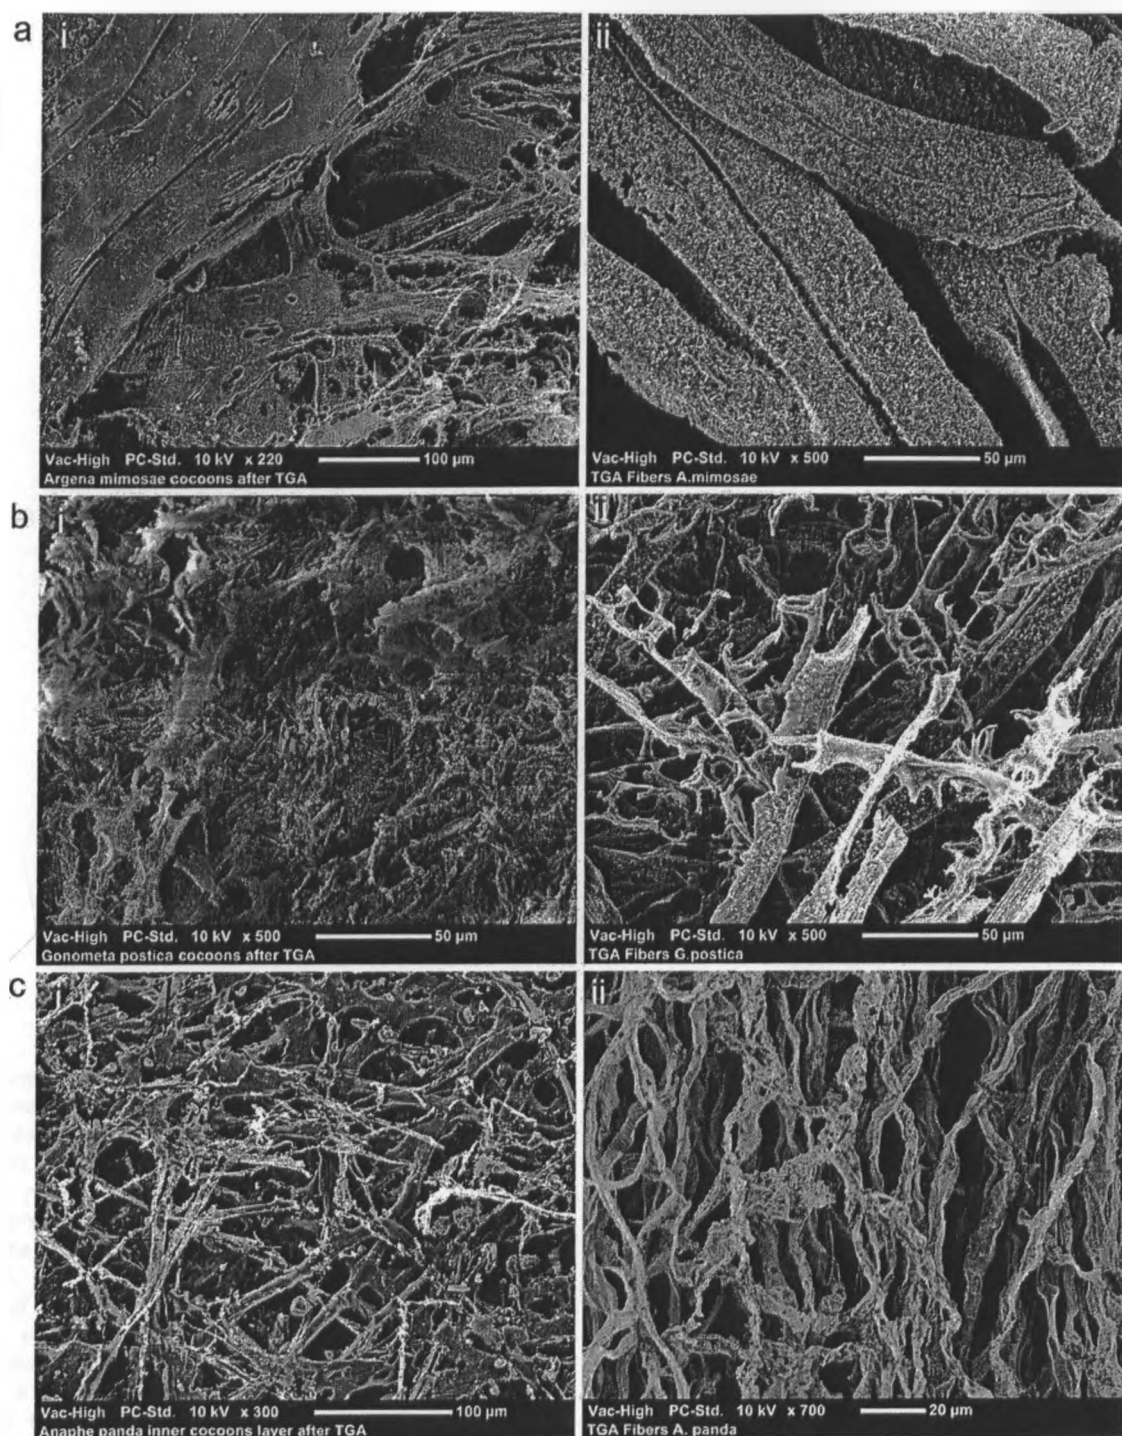


Figure 5. SEM micrographs of cocoon shells (i) and degummed fibers (ii) after heat treatment.

shells attained constant weight after the rapid weight loss, whereas the rest of the species continued to lose weight gradually. *E. bauhiniae* and *G. postica* cocoon shells had the highest and the lowest total weight losses, 97.2 and 71.2%, respectively.

The TG curves in Figure 4(b) showed the weight loss from degummed fibers. Water loss from degummed fibers occurred rapidly up to 99, 109, 113, 105, and 109°C for *B. mori*, *E. bauhiniae*, *A. mimosae*, *A. panda*, and *G. postica*, respectively, which was then followed by further gradual weight loss. The total

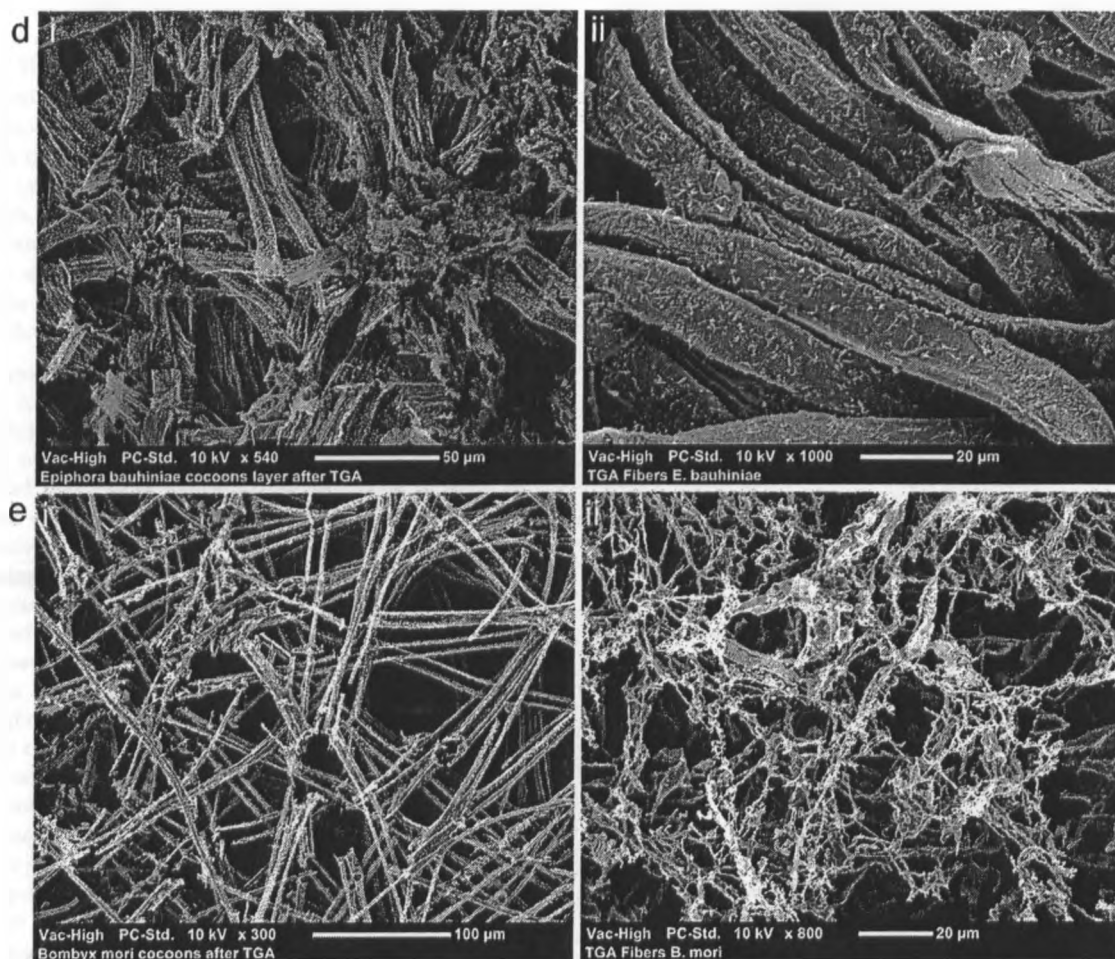


Figure 5. Continued.

dehydration loss was the highest for *G. postica* (13.3%) and the lowest for *B. mori* (8.5%) degummed fibers (Table IV). Major decomposition of degummed fibers commenced at 302, 290, 303, 312, and 305°C for *B. mori*, *E. bauhiniiae*, *A. mimosae*, *A. panda*, and *G. postica*, respectively. The average onset decomposition temperature was higher for degummed fibers than the cocoon shells except for *A. mimosae* and *E. bauhiniiae*. *A. panda* had the highest onset decomposition temperatures of 309 and 312°C for cocoon shell and degummed fibers, respectively. The multistep thermal degradation of *G. postica* cocoon shells could not be observed in degummed fibers. *B. mori* fibers had the highest total weight loss (93.4), though it is not significantly different from other species except *A. mimosae* and *G. postica*.

The SEM images showed that cocoon shells and degummed fibers maintained their shape in *A. mimosae*, *A. panda*, and *E. bauhiniiae*, whereas *B. mori* and *G. postica* were completely decomposed and lost their structure in the process [Figure 5(a–e)]. In *A. mimosae* and *E. bauhiniiae*, the broken individual fibrils became more evident and can be easily seen after the heat treatment.

## DISCUSSION

The results demonstrated the existence of distinct variations in the mechanical properties and in thermal degradation behaviors among the four African wild silk cocoon shells and degummed fibers. The stress–strain curves that are related to the applied stress to the resulting strain revealed that each species has its own unique stress–strain curve. This has previously been reported for mulberry and nonmulberry varieties.<sup>13,14</sup> *B. mori* and *A. panda* showed no well-defined yielding point and strain hardening region suggesting the presence of well-developed crystalline regions that are responsible for smaller and gradual elongation with increasing stress.<sup>15</sup> The study revealed that the African wild silk fibers have comparable mechanical properties to the commercial standard, *B. mori*. Sen and Babu<sup>15</sup> also reported that average breaking extension values are greater for nonmulberry varieties (21–24, 23–30, and 17–24% for Muga, Eri, and Tasar silk, respectively) than *B. mori* (12–15%). However, in our study, most of the wild silk fibers had lesser breaking elongation than *B. mori*. *Saturniidae* silk showed lower values of the elastic modulus and larger extensibility when compared with the *Thaumetopoeidae*, which is also found to be

true in our study.<sup>16</sup> In most of the results, the wild silk fibers showed nonsignificant difference in the measured tensile properties. The fracture properties of silk fibers are poorly reproducible and governed by microstructural defects rather than by intrinsic limitations of the silk polymer.<sup>17</sup> The morphological defects such as partial silk fibroin rupture observed in *G. postica* fibers can also be a possible cause for the drop of the tensile strength. The mechanical properties are also influenced by the fiber denier.<sup>18</sup> The tensile strength of the fibers is also attributed to the extent crystalline region with highly ordered structures and the ratio of other amino acids that confer elasticity in the amorphous domains.

The typical silk from *B. mori* cocoon has a tensile strength of about 0.5 GPa, breaking strain of 15–22%, and tensile elastic modulus 7–17 GPa.<sup>19,20</sup> Thus, for *B. mori*, the present findings match consistently with previous results. However, other studies reported that tensile modulus and the tensile strength of the normal compact cocoon are about 0.66 GPa and 53.98 MPa, respectively.<sup>21</sup> Zhao et al.<sup>22</sup> also reported comparable tensile modulus and breaking strain results for *B. mori* compact cocoon shells tested along longitudinal directions. However, they reported lower tensile stress (20 MPa). The variation in the measured data for cocoon shells might be attributed to several reasons. The irregular silk fiber arrangement and wrinkles throughout the cocoon shells that are related to the environmental conditions during cocoon formation and drying together with variation in cocoon thickness, and the entire spinning process contribute to the observed differences. The main reason for poor mechanical properties in cocoon shells of *G. postica* might be due to the presence of calcium oxalate crystals combined high gum contents leading to easy rupture and weak bonding between the fibers as can be evidenced from the SEM micrographs.

The study further showed that permanent decomposition of cocoon shells and fibers started very early for *B. mori* making the African wild silk fibers thermally relatively more stable. The wild cocoon shells had significantly higher temperature for dehydration, which suggests the presence of highly adsorbed water molecules (intrinsic structural water) and the variation in chemical composition of constituent proteins. The high heat stability of the cocoon shells proved their contribution as self-thermoregulation structures, and they will not be exposed to severe dehydration except under extreme environmental condition. In previous studies, similar results were reported for *B. mori* cocoon shells exhibiting dehydration and decomposition losses at 98 and 280°C, respectively.<sup>23</sup> They also suggested that the substantial weight decrease thought to be due to oxidation and cleavage reaction of the —OH chain of the silk fibers. The multistep decomposition of *G. postica* cocoon shells could be due to the presence of calcium oxalate crystals on their surface. *A. pernyi* silk fibers and other silks belonging to the family Saturniidae also undergo several steps of decomposition due to the difference in polymorphs of crystalline structure and amino acid composition.<sup>24</sup> The absence of change in structure of *A. mimosae* and *E. bauhinae* fibers

after thermal treatment might be due to the compactness of the fiber disks during the sample preparation process. In conclusion, the study confirmed that silks produced by the African wild silkmths have properties that have considerable promise for commercial applications. Although *B. mori* and the wild silks are both class of natural proteins, their overall properties are different. The molecular structure, weight, and percentage crystallinity seem to play a role in distinctly different properties of the silks.

#### ACKNOWLEDGMENTS

Thanks are due to *icipe*-African Insect Science for Food and Health for providing logistical and research support. The authors are highly indebted to Dr. Chris Holland, Ms. Fujia Chen, Dr. Tom Ghyesens, and other members of the Oxford Silk Research Group for their help, technical support, and expert suggestions. Funding was provided for Addis Teshome by the DAAD and for Fritz Vollrath by ERC (SP2-GA-2008-233409) and the AFOSR (F49620-03-1-0111).

#### REFERENCES

- Zhao, H. P.; Feng, X. Q.; Cui, W. Z.; Zou, F. Z. *Eng. Fract. Mech.* **2007**, *74*, 1953.
- Chen, X.; Shao, Z. Z.; Marinkovic, N. S.; Miller, L. M.; Zhou, P.; Chance, M. R. *Biophys. Chem.* **2001**, *89*, 25.
- Shao, Z. Z.; Vollrath, F. *Nature* **2002**, *418*, 741.
- Manjunatha, H. B.; Rajesh, R. K.; Aparna, H. S. *J. Insect Sci.* **2010**, *10*, 1.
- Zhang, Y.; Yang, H.; Shao, H.; Hu, X. *J. Biomed. Biotechnol.* **2010**, *1*, 1.
- Lin, Z.; Huang, W.; Zhang, J.; Fan, J.; Yang, D. *Proc. Natl. Acad. Sci. U. S. A.* **2009**, *106*, 8906.
- Jiang, P.; Liu, H.; Wang, C.; Wu, L.; Huang, J.; Guo, C. *Mater. Lett.* **2006**, *60*, 919.
- Ki, C. S.; Kim, J. W.; Oh, H. J.; Lee, K. H.; Park, Y. H. *Int. J. Biol. Macromol.* **2007**, *41*, 346.
- Sutherland T. D.; Young, J.; Weisman, S.; Hayashi, C. Y.; Merritt, D. *J. Annu. Rev. Entomol.* **2010**, *55*, 171.
- Danks, H. V. *Eur. J. Entomol.* **2004**, *101*, 4333.
- HansG. W.; McKarns, T. *Thermochim. Acta* **1990**, *169*, 1.
- Perez-Rigueiro, J.; Viney, C.; Llorca, J.; Elices, M. *J. Appl. Polym. Sci.* **1998**, *70*, 2439.
- Das, S.; Chattopadhyay, R.; Gulrajani, M. L.; Sen, K. *Autex Res. J.* **2005**, *5*, 81.
- Rajkhowa, R.; Gupta, V. B.; Kothar, V. K. *J. Appl. Polym. Sci.* **2000**, *77*, 2418.
- Sen, K.; Babu, M. K. *J. Appl. Polym. Sci.* **2004**, *92*, 1098.
- Lucas, F.; Shaw, J. T. B.; Smith, S. G. *J. Textile Inst.* **1955**, *46*, 440.
- Perez-Rigueiro, J.; Viney, C.; Llorca, J.; Elices, M. *J. Appl. Polym. Sci.* **2000**, *75*, 1270.
- Iizuka, E.; Kawano, R.; Kitani, Y.; Okachi, Y.; Shimizu, M.; Fukuda, A. *Indian J. Seric.* **1993**, *32*, 27.



19. Hakimi, O.; Knight, D.; Vollrath, F.; Vadgama, P. 2007. *Compos. B: Eng.* **2007**, *38*, 324.
20. Gosline, J. M.; Guerette, P. A.; Ortlepp, C. S.; Savage, K. N. *J. Exp. Biol.* **1999**, *202*, 3295.
21. Huang, S. Q.; Zhao, H. P.; Feng, X. Q.; Cui, W.; Lin, Z.; Xu, M. Q. *Acta Mech. Sin.* **2008**, *24*, 151.
22. Zhao, H. P.; Feng, X. Q.; Yu, S. W.; Cui, W. Z.; Zou, F. Z. *Polymer* **2005**, *46*, 9192.
23. Zhang, H.; Magoshi, J.; Becker, M.; Chen, J. Y.; Matsunaga, R. *J. Appl. Polym. Sci.* **2002**, *86*, 1817.
24. Kweon, H. Y.; Um, I. C.; Park, Y. H. *Polymer* **2000**, *41*, 7361.